



CHALMERS
UNIVERSITY OF TECHNOLOGY

Conductivity behaviour in novel quasi-solid-state electrolyte based on polyacrylonitrile and tetrahexylammonium iodide intended for dye

Downloaded from: <https://research.chalmers.se>, 2023-06-09 12:13 UTC

Citation for the original published paper (version of record):

Bandara, T., Svensson, T., Dissanayake, M. et al (2013). Conductivity behaviour in novel quasi-solid-state electrolyte based on polyacrylonitrile and tetrahexylammonium iodide intended for dye sensitized solar cells. *Journal of the National Science Foundation of Sri Lanka*, 41(3): 175-184. <http://dx.doi.org/10.4038/jnsfsr.v41i3.6056>

N.B. When citing this work, cite the original published paper.

RESEARCH ARTICLE

Conductivity behaviour in novel quasi-solid-state electrolyte based on polyacrylonitrile and tetrahexylammonium iodide intended for dye sensitized solar cells[†]

T.M.W.J. Bandara^{*1,2}, T. Svensson¹, M.A.K.L. Dissanayake³, M. Furlani¹, W.J.M.J.S.R. Jayasundara⁴, P.S.L. Fernando², I. Albinsson⁵ and B.E. Mellander¹

¹ Department of Applied Physics, Chalmers University of Technology, Sweden.

² Department of Physical Sciences, Faculty of Applied Sciences, Rajarata University of Sri Lanka, Mihintale.

³ Institute of Fundamental Studies, Hantana Road, Kandy.

⁴ Postgraduate Institute of Science, University of Peradeniya, Peradeniya.

⁵ Department of Physics, University of Gothenburg, Gothenburg, Sweden.

Submitted: 07 September 2012; Accepted: 14 February 2013

Abstract: The conduction of iodide ions in gel polymer electrolytes and the performance of dye sensitized solar cells containing such an electrolyte can be enhanced by incorporating a salt having a bulky cation. In this work, polyacrylonitrile (PAN) and Hex₄N⁺I⁻ based gel electrolytes with ethylene carbonate and propylene carbonate as plasticizers have been studied. The variation of conductivity and molar conductivity with salt concentration has been discussed in order to understand the mechanism of iodide ion conductivity in this system. Out of the various compositions studied, the electrolyte containing 120 % salt with respect to weight of PAN showed the highest conductivity, $2.0 \times 10^{-3} \text{ Scm}^{-1}$ at 25 °C and a glass transition at - 102.3 °C. The electrolytes exhibit predominantly ionic behaviour and because of the bulky cation a negligible cationic transport is shown. A quasi-solid-state dye sensitized solar cell was fabricated employing the optimized gel electrolyte. This cell showed an energy conversion efficiency of 3.1 % and a short circuit current density of 8.1 mAcm^{-2} under irradiation of 1000 Wm^{-2} .

Keywords: Dye sensitized, gel polymer electrolyte, ionic conductivity, molar conductivity, polyacrylonitrile, solar cell.

INTRODUCTION

The widely used energy resources today are fossil fuels and nuclear energy. However, the excessive consumption of fossil fuels during the last few decades and uneven distribution of fossil fuels in the world have lead to serious environmental problems, primarily due to the

emission of green house gases together with many other pollutants, while nuclear power is faced with safety issues and problems associated with radioactive waste disposal (Abbott *et al.*, 2010). In order to overcome these problems, the development of renewable and clean energy sources is important. Solar energy provides a good alternative as a renewable energy source and the use of solar cells provides a convenient method to convert solar energy directly into electricity. However, the high production cost of present day Si-based solar cells has become an obstacle to widespread utilization of solar cells. Therefore, the development of low cost, dye sensitized solar cells (DSSCs) has a great potential to offer a reliable method to convert solar energy to electricity (Chiba *et al.*, 2006; Li *et al.*, 2006; Hagfeldt *et al.*, 2010). Although liquid electrolyte based DSSCs have efficiencies around 10 %, they have several drawbacks such as electrolyte leakage, need for robust sealing, problems of electrode corrosion and of stability in the long run. In order to overcome these drawbacks, solid electrolyte based and gel electrolyte based DSSCs are currently being developed (Wu *et al.*, 2006; Bandara *et al.*, 2010a). However, the performance of DSSCs needs to be improved further in order to make them commercially viable devices. In this regard, the improvement of both the photo-electrode and the electrolyte is important in order to enhance the performance. This study is focused on the preparation of a dependable gel polymer electrolyte to be used in DSSCs and the understanding of its ionic transport properties.

* Corresponding author (awijendr@yahoo.com)

[†] Part of this work has been presented at the Solar Asia 2011 International Conference held on 28 – 30 July 2011 at the Institute of Fundamental Studies, Kandy.

Although synthetic polymers have been used as structural materials and electric insulators for a long time, it is only during the past few decades that they have emerged as ionically conducting materials (Wright, 1975; Armand *et al.*, 1979). Due to numerous advantages inherent in synthetic polymers, lithium ion conducting polymers are being developed as electrolyte membranes in lithium rechargeable-batteries and iodide ion conducting polymers are being developed as electrolytes for dye sensitized photo-electrochemical (PEC) solar cells. Out of these polymer electrolytes, solid polymer electrolytes such as those based on polyethylene oxide (PEO) complexed with suitable ionic salts still have low ionic conductivities and therefore, need to be further optimized in order to obtain electrolytes with reasonably high ionic conductivity to be used in lithium batteries or PEC solar cells. However, quasi solid or gel electrolytes, formed by incorporating the host polymer, the ionic salt and plasticizers such as ethylene carbonate (EC) and propylene carbonate (PC) offer a compromise between a solid electrolyte and a gel electrolyte. These gel electrolytes possess ionic conductivities close to their liquid counterparts and superior mechanical properties compared to liquid electrolytes.

Various host polymers and plasticizers have been incorporated with different iodide salts in order to develop gel polymer electrolytes intended for PEC solar cells (Ileperuma *et al.*, 2004; Ileperuma *et al.*, 2008; Bandara *et al.*, 2010a, c). The reports on incorporation of different alkaline metal iodides (MI) ($M = \text{Li, Na, K, Cs}$) in PAN based (Tennakone *et al.*, 1999) and polyethylene oxide (PEO) based (Shen *et al.*, 2008) polymer electrolytes for PEC solar cells are of interest since the effect of changing the size of the cation on the performance of the electrolyte and solar cells have been studied. The study on electrolytes containing PAN have shown that the short circuit photocurrent density (J_{sc}) enhances with the increasing size of the cation (M^+) for Li, Na, K and Cs. This can be understood because the J_{sc} depends on the mobility of iodide ions, which is enhanced when the cation size is large (Tennakone *et al.*, 1999). From these studies it is clear that the conductivity of iodide ion conducting gel polymer electrolytes and the performance of DSSCs containing such electrolytes can be enhanced by incorporating a salt containing a bulky cation compared to the iodide ion. Hence, for this purpose quaternary-ammonium iodides are appropriate candidate materials.

The iodide ion (I^-) conductivity contribution to the overall ionic conductivity of the electrolyte in a DSSC is a major factor, which determines the J_{sc} and the efficiency of the solar cell. This is because the iodide

ion, while participating in the redox reaction also shuttles between the photo-electrode and the counter electrode. Quarternary ammonium salts such as Pr_4NI , Bu_4NI and Hex_4NI are therefore used as ionic salts in DSSC electrolytes.

Polyacrylonitrile (PAN) based gel polymer electrolytes have been reported to have reasonably good ionic conductivities and they have been used in quasi solid-state PEC solar cells (Ileperuma *et al.*, 2004; Ileperuma *et al.*, 2008; Bandara *et al.*, 2010a). In PAN based gel electrolytes, it is generally believed that the electrolytic solution formed by dissolving the ionic salt in EC/PC is 'trapped' in cages formed by the PAN polymer matrix yielding higher ionic conductivities. Tetrapropylammonium iodide ($\text{Pr}_4\text{N}^+\text{I}^-$) has been used with PEO and PAN host polymers and reasonably good cell performance has been reported, reaching about 3 % overall cell efficiency for the latter system (Dissanayake *et al.*, 2002; Ileperuma *et al.*, 2004) DSSCs containing an electrolyte composed of PAN and tetrabutylammoniumiodide ($\text{Bu}_4\text{N}^+\text{I}^-$) salt has also been reported to show very good cell performance (Ileperuma *et al.*, 2008; Ileperuma *et al.*, 2011). However, it appears that there is a lack of reports in the literature on systematic studies on understanding the anion transport behaviour in these polymer electrolytes. In comparison, a large number of studies have been reported on cation transport behaviour in polymer electrolytes intended for use in lithium batteries, electro-chromic devices and other devices (Stephan, 2006).

Ionic radii of Pr_4N^+ and Bu_4N^+ ions are 4.6 and 5.0 Å respectively, which are significantly larger than those of the alkali-metal ions (Gill, 1979; Shimizu *et al.*, 1999). When the size of the cation increases, it enhances the salt dissociation and the anion transference number leading to high anionic conductivity, which is important for the performance of DSSCs (Ileperuma *et al.*, 2004; Bandara *et al.*, 2010a, b). The radius of the tetrahexylammonium (Hex_4N^+) ion is larger than that of Pr_4N^+ and Bu_4N^+ ions, besides Hex_4N^+ ions form an ionic liquid structure with the association of iodide ion owing to its large size. To date there are no reports on PAN based gel electrolytes using $\text{Hex}_4\text{N}^+\text{I}^-$ salt. In this study, quasi solid-state (gel) polymer electrolytes were prepared using PAN as the host polymer and $\text{Hex}_4\text{N}^+\text{I}^-$ as the ionic salt and ethylene carbonate (EC) and propylene carbonate (PC) as plasticizers. Besides the optimization of ionic conductivity in the electrolyte by systematically varying the salt concentration, the samples were characterized by using thermal and DC polarization measurements. The concentration dependence of conductivity as well as molar conductivity has been discussed in detail and

a possible mechanism was suggested. Finally, a quasi-solid-state solar cell was fabricated using the optimized electrolyte and the cells were characterized using current voltage curves.

METHODS AND MATERIALS

PAN, $\text{Hex}_4\text{N}^+\text{I}^-$, iodine, EC and PC all with purity greater than 98 %, purchased from Aldrich were used as starting materials. PAN and $\text{Hex}_4\text{N}^+\text{I}^-$ were vacuum dried for 24 h in a vacuum oven at 50 °C prior to use. For preparing the electrolyte samples, the weights of PAN (0.10 g), EC (0.40 g) and PC (0.40 g) were kept unchanged and the weight of $\text{Hex}_4\text{N}^+\text{I}^-$ was varied in order to determine the optimum composition giving the highest conductivity. The amount of iodine in the electrolyte was maintained so that the molar ratio $\text{Hex}_4\text{N}^+\text{I}^- : \text{I}_2$ was 10 : 1. For the electrolyte sample preparation, the selected compositions of chemicals were heated to about 80 °C and stirred for a few minutes until a homogeneous, viscous solution was obtained. The resulting slurry was cast on to a glass plate and pressed by another glass plate in order to obtain a polymer electrolyte film for measurements. The complex impedance measurements were performed using a HP 4292A RF impedance analyzer in the frequency range 10 Hz – 10 MHz and temperature range of 20 – 80 °C. Disc shaped electrolyte films of diameter ~ 10.5 mm and thickness ~ 0.5 mm, sandwiched between two polished stainless steel blocking electrodes were used for impedance measurements.

DC polarization tests were carried out at room temperature by sandwiching a disc shaped electrolyte sample between two stainless steel blocking electrodes and alternatively between two iodine non blocking electrodes. The thermal properties of the samples were analyzed using a Mettler Toledo DSC 30 differential scanning calorimeter between - 140 °C and 100 °C in consequent heating and cooling cycles with a rate of 10 °Cmin⁻¹.

A TiO_2 nano-porous layer was coated on FTO (Solaronix SA) glass having a sheet resistance of 7 ohm/square using Degussa P25 powder. For this layer preparation, 0.5 g of Degussa P25 powder (TiO_2) was ground well for ~ 30 min with ~ 2 mL of HNO_3 (pH = 1) in an agate mortar. The resulting colloidal suspension was diluted with HNO_3 (pH = 1) to get a 5 % (w/w) solution. It was subsequently stirred overnight at 60 °C and a 25 % (w/w) mixture was obtained. To this ~ 0.1 g of carbowax and a few drops of Triton X 100 (surfactant) were added and mixed well. This colloidal suspension was casted on FTO substrate using doctor blade method to obtain porous TiO_2 layers of about 5 – 10 μm thickness after

sintering at 450 °C for 30 min. The TiO_2 coated electrodes were immersed in an ethanolic solution of dye sensitizer ruthenium 535-bis TBA (Solaronix SA) while both were hot (~ 60 °C). After 24 h absorption, the electrodes were withdrawn from the dye solution and washed with acetone to remove unabsorbed dye and loosely bound TiO_2 particles from the dye-coated electrode.

Quasi – solid-state PEC solar cells were fabricated by sandwiching polymer electrolyte films of thickness about 0.1 mm between the dye-coated TiO_2 electrode and a platinum coated glass electrode (mirror type) in the configuration glass/FTO/ TiO_2 /dye/electrolyte/Pt/glass. All the fabricated solar cells were characterized by measuring I - V curves using a computer controlled eDAQ Potentiostat and e-coder under ~ 1000 Wm^{-2} irradiation (1.5 AM) with a LOT-Oriel GmbH solar simulator.

RESULTS AND DISCUSSION

Ionic conductivity

The conductivity Arrhenius plots for PAN/EC/PC : $\text{Hex}_4\text{N}^+\text{I}^-$ gel electrolyte samples for different PAN : $\text{Hex}_4\text{N}^+\text{I}^- = 100 : x$ weight ratios up to $x = 120$ % are shown in Figure 1. Out of these samples, the highest conductivity is shown for the electrolyte sample containing 120 wt % $\text{Hex}_4\text{N}^+\text{I}^-$ for all the measured temperatures. This corresponds to an electrolyte composition of PAN: EC:PC: $\text{Hex}_4\text{N}^+\text{I}^- = 1 : 4 : 4 : x/100$ by weight. The subsequent conductivity Arrhenius plots for salt mass fractions from 120 – 200 % are shown in Figure 2. All the samples shown in Figure 2, which represent high salt concentrations have reasonably good conductivities. However, 120 % and 140 % salt containing electrolytes seem to have slightly higher conductivities especially at low temperatures. The sample with 120 % $\text{Hex}_4\text{N}^+\text{I}^-$ has an ionic conductivity of $2.0 \times 10^{-3} \text{ Scm}^{-1}$ at 25 °C and $2.9 \times 10^{-3} \text{ Scm}^{-1}$ at 50 °C. The conductivity variation with inverse temperature shows more or less Arrhenius behaviour within the measured temperature range. Hence, the activation energy E_a could be calculated by fitting the data to the Arrhenius equation.

$$\sigma T = B \exp\left(-\frac{E_a}{kT}\right) \quad \dots(1)$$

where, B is the pre-exponential factor, E_a the activation energy, k the Boltzmann constant, and T the absolute temperature. The fitted curves to the Arrhenius equation are also shown in Figure 1 for samples containing less than 120 % $\text{Hex}_4\text{N}^+\text{I}^-$.

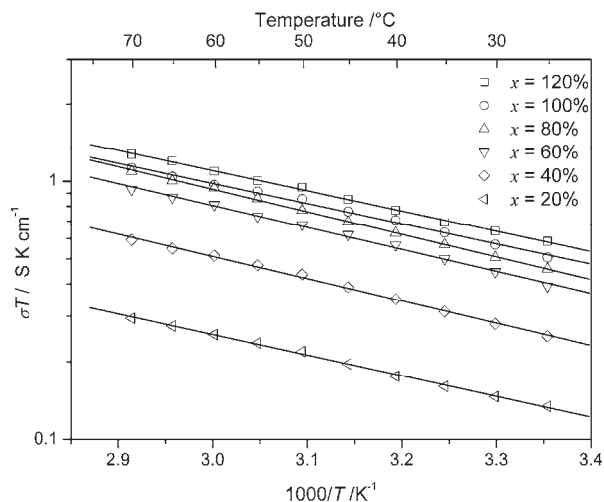


Figure 1: σT vs $1000/T$ for PAN/EC/PC electrolytes containing x wt % of $\text{Hex}_4\text{N}^+\text{I}^-$ with respect to PAN mass fraction. Fitted lines to the Arrhenius equation are also shown.

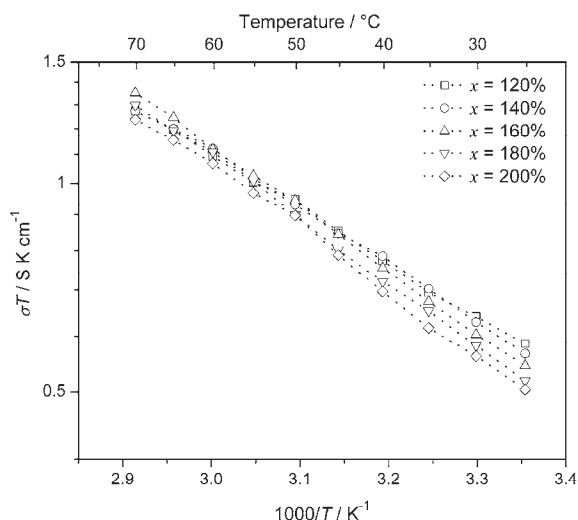


Figure 2: σT vs $1000/T$ for PAN/EC/PC: $\text{Hex}_4\text{N}^+\text{I}^-$ electrolytes containing x wt % of $\text{Hex}_4\text{N}^+\text{I}^-$ with respect to weight of PAN. The dotted lines shown are guides to the eye. Fitted lines to the Arrhenius equation are not shown.

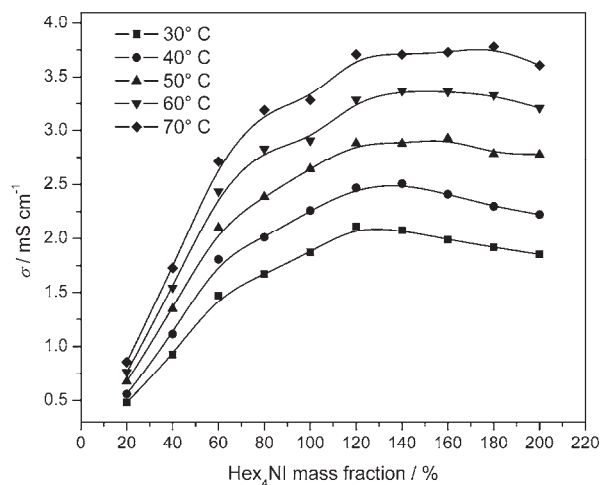


Figure 3: Conductivity as a function of $\text{Hex}_4\text{N}^+\text{I}^-$ mass fraction (x) with respect to PAN in PAN/EC/PC : $\text{Hex}_4\text{N}^+\text{I}^-$ electrolyte at different temperatures.

In Figure 2, the fitted curves for high salt compositions are not shown as they lie close to each other and cannot be distinguished clearly from one another. Instead, only dotted lines connecting experimental points are shown as guides to the eye. The calculated activation energies E_a for all the samples shown in Table 1 are in the 0.15 – 0.18 eV range.

Figure 3 shows the variation of ionic conductivity as a function of the mass fraction of the salt (x %) with respect to PAN at temperatures 30, 40, 50, 60, and 70 °C. A conductivity increase is shown for the low salt composition more or less up to 120 % salt mass fraction. However, a steeper conductivity increase is shown for low salt compositions up to about the 60 % salt containing sample. This conductivity increase with added salt at low concentrations can be attributed essentially to an increase of the number of free ions due to ionic dissociation and to some extent from their mobility with the increasing amount of $\text{Hex}_4\text{N}^+\text{I}^-$. The less steep conductivity increase shown for salt mass fractions from 60 – 120 % may be due to (a) the reduction of the number of free ions due to the formation of ion pairs and higher ionic aggregates; (b) the decrease in the ionic mobility caused by the increase in viscosity of the electrolyte medium. At 120 % salt composition, the electrolyte shows the highest conductivity for lower temperatures and this sample gave the minimum conductivity activation energy as shown in Table 1. Hence, at higher salt concentrations, further addition of salt will not result in a conductivity increase. Several processes appear to be responsible for this trend. The decrease in mobility caused by the viscosity increase would have contributed to this behaviour along with the formation of a large number of ion pairs and higher ionic aggregates, which does not contribute to a further conductivity increase. In this concentration region non-dissociated salt in the electrolyte may also block or limit

Table 1: The activation energy- E_a , and the glass transition temperature- T_g , for electrolytes containing different mass fractions of, x wt %, of $\text{Hex}_4\text{N}^+\text{I}^-$

x wt %	20	40	60	80	100	120	140	160	180	200
E_a / eV	0.16	0.17	0.17	0.17	0.16	0.15	0.16	0.18	0.18	0.18
T_g / °C	-101.68	-101.75	-101.77	-101.90	-101.94	-102.30	-102.19	-102.04	-101.95	-101.90

the ionic mobility. These competing effects become clearer when the equivalent conductivity (molar conductivity) vs square root of salt concentration is plotted as shown in Figure 4. A somewhat similar analysis has been provided for other polymer electrolyte systems (Albinsson *et al.*, 1993; Albinsson *et al.*, 1994).


Figure 4 shows the graphs of equivalent conductivity (molar conductivity) vs square root of salt concentration for this gel electrolyte system. Interestingly, the equivalent conductivity shows a maximum at the 60 % salt composition, whereas the conductivity maximum in Figure 3 is seen at the 120 % salt composition. This clearly suggests that the ionic mobility starts to decrease from the 60 % salt composition.

In order to explain the observed variation of molar conductivity vs square root of salt concentration (\sqrt{C}) shown in Figure 4, we will resort to the fact that these gel electrolytes are formed essentially by ‘trapping’ the EC/PC based electrolytic solution in the matrix formed by PAN. PC is a solvent with low molecular weight and high dielectric constant. While the high dielectric constant favours salt dissociation, the low viscosity would lead to high ionic mobility in a pure PC based electrolytic solution at low salt concentrations. In the present gel electrolyte, the electrolytic solution is formed by dissolving the ionic salt $\text{Hex}_4\text{N}^+\text{I}^-$ in the co-solvent ethylene carbonate (EC) and propylene carbonate (PC). Based on the above reasoning, we would expect the conducting properties of the gel electrolyte system in the present study to be determined essentially by the properties of the electrolytic solution at all concentrations.

As seen from Figure 4, at low salt concentrations up to about 60 wt % of $\text{Hex}_4\text{N}^+\text{I}^-$, the molar conductivity shows only a very slight increase, although one expects this to remain essentially constant. An increasing molar conductivity at low salt concentrations had been reported for several other electrolyte systems in this concentration range (Sigvartsen *et al.*, 1989; Albinsson *et al.*, 1993). A common explanation for this effect is the formation of triple ions in this concentration region as originally

proposed by Fuoss and Kraus (1933) for electrolytic solutions. Another possible explanation is that the ionic re-dissociation occurs in this concentration region thereby increasing the fraction of free charge carriers with concentration. An additional effect in the present gel electrolyte may come from lowering the T_g of the polymer, although this effect is expected to be very small as the interaction of the PAN matrix on ionic transport in this type of gel electrolytes is believed to be not so significant.

As discussed above, it is generally believed that the conductivities of the gel electrolytes incorporating these electrolytic solutions are determined to a large extent by the conductivities of the electrolytic solutions used. Therefore, based on the reasoning given for electrolytic solutions, the molar conductivity of the gel electrolyte system at higher salt concentrations would be determined to a large extent by the viscosity of the electrolyte medium and its dielectric constant. It is interesting to note the almost linear behaviour of molar conductivity drops with

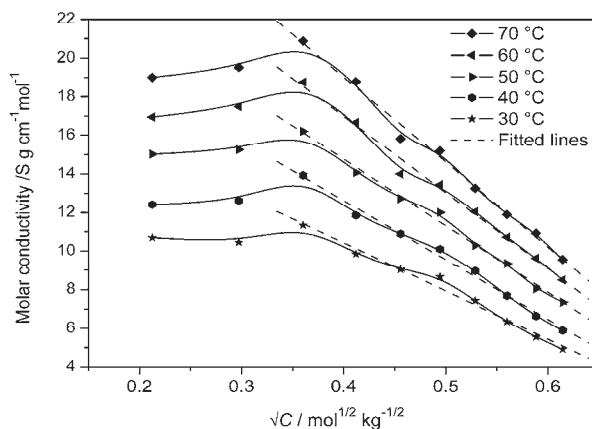**Figure 4:** Molar conductivity as a function of square root of salt concentration in PAN/EC/PC: $\text{Hex}_4\text{N}^+\text{I}^-$ electrolyte at different temperatures. Dotted lines represent fitted lines to the equation $\lambda = A_1 - A_2\sqrt{C}$ for data in the high salt concentration region.

increasing square root of salt concentration depicted in Figure 4 for salt concentrations higher than 60 % Hex₄N⁺I⁻. In the absence of simple conductance theories for high salt concentrations in electrolytic solutions or polymer electrolytes, we would attempt to use the conductance-viscosity relationship applicable to electrolytic solutions to explain the conductance behaviour in this region. A similar behaviour has been reported by Southall *et al.* (1996) to explain the observed molar conductance vs salt concentration in DMF- LiCF₃SO₃ and TG-LiCF₃SO₃ liquid electrolyte systems. Both these organic solvents [N,N –dimethyl formaldehyde (DMF) and tetraethylene glycol dimethyl ether or Tetraglyme (TG)] are of low molecular weight and high dielectric constant, similar to EC/PC co solvent used in the present work.

In order to analyze the data shown in Figure 4, it is considered that the charge transport in the gel electrolyte system predominantly occurs by the motion of anions (I⁻) and that the mobility of the counter ion (Hex₄N⁺) is negligible. The ionic conductivity may then be expressed as follows through the Nernst-Einstein equation,

$$\sigma = ne^2D/kT \quad \dots(2)$$

where D is the diffusion coefficient of the mobile species, n is the number density of charge carriers, e is the electronic charge and k is the Boltzmann's constant. The diffusion coefficient is related to the viscosity of the electrolyte through the Stokes-Einstein equation,

$$D = kT/6\pi r\eta \quad \dots(3)$$

where r is the effective radius of the diffusing species. From the above two equations, one can relate the conductivity to the viscosity of the electrolyte medium as

$$\sigma = ne^2/6\pi r\eta \quad \dots(4)$$

Comparing the conductivity and molar conductivity values for a given salt concentration at different temperatures (Figures 3 and 4), it can be seen that the number density of charge carriers, n , remains essentially unchanged with temperature for the entire composition range. Based on this, we expect the molar conductivity (σ/n) to follow a reciprocal variation with viscosity with increasing salt concentration beyond 60 %. From the above analysis, it is clear that the almost linear drop in molar conductivity with salt concentration seen in Figure 4 for salt concentrations higher than 60 % Hex₄N⁺I⁻ is very likely due to the increase of the viscosity of the electrolyte medium with the increase in salt concentration.

A detailed modelling of viscosity and conductivity for concentrated organic liquid electrolytes has been reported by Chagnes *et al.* (2002) for some lithium salts dissolved in gamma-butyrolactone. They were able to obtain a linear fit to molar conductivity vs cube root of the concentration in the 0.1 –1.6 M concentration region. In the present study a linear drop of molar conductivity was observed with the square root of salt concentration in the concentration region of 0.13 – 0.38 kgmol⁻¹ and the data in this concentration region were fitted successfully to the empirical equation;

$$\lambda = A_1 - A_2\sqrt{C} \quad \dots(5)$$

where A_1 and A_2 are constants. The calculated values A_1 and A_2 are given in Table 2 for different temperatures.

Table 2: The values obtained for A_1 and A_2 by fitting to equation 5 at different temperatures.

Temperature / °C	A_1 / S kg m ⁻¹ mol ⁻¹	A_2 / S kg ^{3/2} m ⁻¹ mol ^{-3/2}
30	2.0	- 2.5
40	2.5	- 3.1
50	2.9	- 3.5
60	3.3	- 3.9
70	3.7	- 4.4

The Debye-Huckle-Onsager theory can explain the conductivity vs concentration behaviour of electrolytic solutions at low salt concentrations. A similar behaviour is expected for polymer gel electrolytes where an electrolyte solution is trapped by a polymer matrix, such as the gel system studied here. However, to our knowledge there is no accepted theory to explain the conductivity vs concentration behaviour for electrolytic solutions or gel polymer electrolytes at higher salt concentrations. We believe that the present work would contribute towards a better understanding of these systems.

DSC measurements

Figure 5 shows the differential scanning calorimetric (DSC) thermograms of PAN/EC/PC: Hex₄N⁺I⁻ electrolyte samples with different Hex₄N⁺I⁻ mass fractions (x %) taken during the 2nd heating run. The measurements of samples obtained during the 2nd cycle were selected for this study in order to eliminate the effects of previous

thermal history of the sample. In the DSC thermograms shown in Figure 5, a first order endothermic phase transition preceded by an exothermic cold-crystallization is observed, in particular for samples with more than 120 % salt content. This can be attributed to the undercooling during the temperature decrease and thus a cold crystallization is followed by the crystallite melting of the EC rich phase.

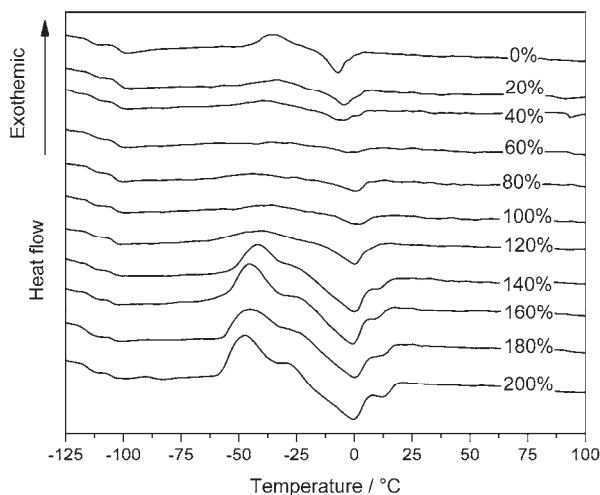


Figure 5: DSC thermograms of PAN/EC/PC polymer electrolytes containing x wt % of $\text{Hex}_4\text{N}^+\text{T}^-$ with respect to PAN weight under heating rate $10\text{ }^\circ\text{C min}^{-1}$.

A clear glass transition around $-102\text{ }^\circ\text{C}$ can be observed for all the samples. The glass transition temperatures, T_g , (mid point) obtained in this work using the 2nd heating cycle are given in Table 1. According to reported literature for PAN/EC/PC gel electrolytes with other salts, the glass transition appears around $-100\text{ }^\circ\text{C}$ (Jayathilaka *et al.*, 2003).

In general, for most polymer electrolytes, the glass transition temperature (T_g) is related to the flexibility of the polymeric host material and the mobility of charge carriers (Tominaga *et al.*, 2005; Wang *et al.*, 2005). The minimum value T_g , $-102.3\text{ }^\circ\text{C}$ was observed for the electrolyte containing 120 wt % $\text{Hex}_4\text{N}^+\text{T}^-$ and as expected this salt concentration gives the maximum conductivity. However, the conductivity increase shown in Figure 3 can be caused by both the increasing number of mobile ions as well as by the increase of mobility caused by an increase of segmental flexibility of polymer chain. A liquid-like charge transport mechanism where the liquid electrolyte is trapped in polymer cages has been suggested for this

kind of PAN based electrolytes (Jayathilaka *et al.*, 2003; Ileperuma *et al.*, 2011). However, the present T_g data shows that there can be an appreciable contribution from the flexibility of the polymer matrix to the conductivity, since the variation of T_g in the present system is in agreement with the observed conductivity variation with the composition shown in Figure 3.

It is interesting to observe the somewhat unusual behaviour in the DSC thermograms of this gel electrolyte system in the temperature range of $-75\text{ }^\circ\text{C}$ to $25\text{ }^\circ\text{C}$ as a function of salt concentration. The melting peak, which is observed in this temperature range and evidently associated with the melting of EC or EC-rich phase in the electrolyte, could be seen very clearly in the gel polymer without $\text{Hex}_4\text{N}^+\text{T}^-$ (0 % trace). This EC melting peak has diminished when the salt is added up to about 60 % salt concentration and then disappeared almost completely at 60 % composition. Then a slight re-appearance is visible for salt concentrations up to 120 %. Above 120 %, the transition peaks become more significant, may be related to the increase of ion association. The salt, apparently, first ‘suppresses’ the melting of EC-rich phase and then ‘releases’ it again with the increase in salt concentrations. We have also calculated the heat of enthalpy associated with this phase transition and observed that the heat of enthalpy follows a similar trend by exhibiting a jump as the salt concentration passes the 120 % value.

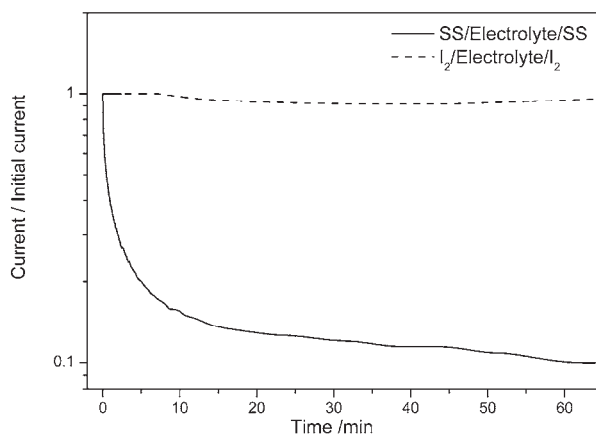


Figure 6: Current/initial current vs time plot for the PAN/EC/PC: $\text{Hex}_4\text{N}^+\text{T}^-$ electrolyte sample containing 120 % salt mass fraction with respect to PAN taken from DC polarization measurements at $25\text{ }^\circ\text{C}$. Solid line and dotted line are corresponding to the SS/Electrolyte/SS and SS/ I_2 /Electrolyte/ I_2 /SS configurations, respectively.

DC polarization measurements

DC polarization measurements (Ileperuma *et al.*, 1988; Watanabe *et al.*, 1988) obtained for the electrolyte sample containing 120 % salt using 1.0 V bias voltage at 25 °C is shown in Figure 6. When SS/electrolyte/SS configuration was used with stainless steel blocking electrodes, a steep current drop is observed within the first 10 minutes and the current subsequently reached to an approximately steady value after about 60 minutes. This suggests that the gel electrolyte is predominantly an ionic conductor with negligible electronic conductivity (Ileperuma *et al.*, 2002). DC Polarization measurements in the SS/I₂/electrolyte/I₂/SS symmetrical configuration with non-blocking iodine pellet electrodes showed no appreciable current drop with time during the measured time period. This ensures that the gel electrolyte is predominantly an iodide/triiodide ion conductor.

Solar cell characterization

The *V-I* characteristic curve for the quasi solid-state cells fabricated with configuration ITO/dye sensitized TiO₂/electrolyte/Pt coated ITO is shown in Figure 7. For this cell the gel electrolyte with 120 wt % Hex₄N⁺I⁻ / PAN/EC/PC electrolyte and the dye sensitizer ruthenium 535-bis TBA were used. The short-circuit photocurrent density (J_{SC}) and open-circuit voltage (V_{OC}) of the cell are 8.1 mAcm⁻² and 0.79 V, respectively under the irradiation of 1000 Wm⁻². The power density vs cell potential is also shown in Figure 7. The maximum output power density, 31 Wm⁻² is shown at the current density $J_{opt} = 6.6$ mAcm⁻² and at the voltage $V_{opt} = 0.47$ V. The short circuit current density, 8.1 mAcm⁻² is rather a good value compared to other quasi sold-state solar cells reported using quaternary ammonium iodide salts and ruthenium dye complexes (Ileperuma *et al.*, 2002, 2004; Li *et al.*, 2006). This higher current density in our system can be attributed to high iodide ion conductivity in the electrolyte due to the bulky Hex₄N⁺I⁻ cation.

The fill factor and efficiency of the cell is calculated using;

$$ff = \frac{J_{opt} V_{opt}}{J_{SC} V_{OC}} \quad \dots(6)$$

and

$$\eta = \frac{J_{SC} V_{OC} ff}{\text{Total incident power density}} \quad \dots(7)$$

The fill factor of the cell is 48.5 % and the overall energy conversion efficiency of the cell is 3.1 %. The rather poor fill factor of the cell that led to low efficiency could possibly be due to the TiO₂ photoelectrode, which was fabricated in a very simple way without attempting to optimize it by minimizing the electron-hole recombination. The main emphasis of this study was to optimize the electrolyte material. We believe that optimizing the TiO₂ photo-anode and selecting a better dye sensitizer can help in improving the cell efficiencies.

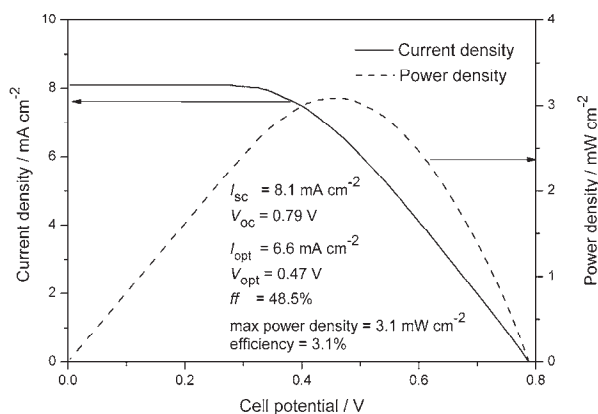


Figure 7: Photocurrent vs cell potential difference curves for the DSSC fabricated using PAN/EC/PC electrolyte containing 120 wt % Hex₄N⁺I⁻ under irradiation of a 1000 W m⁻² Xenon lamp.

CONCLUSION

Gel type polymer electrolyte films based on PAN host polymer was prepared by incorporating the salt, Hex₄N⁺I⁻ and plasticizers EC and PC. The electrolyte containing 120 % salt with respect to PAN weight showed the maximum conductivity out of the samples measured. This optimum conductivity electrolyte showed 2.0×10^{-3} Scm⁻¹ conductivity at 25 °C with a low T_g value of - 102.3 °C.

The linear drop of molar (equivalent) conductivity with the square root of the concentration at salt mass fraction above 60 % Hex₄N⁺I⁻ in the concentration region from 0.13 - 0.38 molkg⁻¹, is evidently governed by the increase in viscosity of the electrolyte medium. As inferred from the DC polarization tests, these gel electrolytes are predominantly iodide ion conductors with negligible electronic conductivity. DSC thermograms

of the gel electrolyte system showed a rather unusual behaviour of the melting peak of the EC rich phase as the salt concentration is increased. Dye sensitized solar cells fabricated using this electrolyte showed 3.1 % energy conversion efficiency and 8.1 mAcm⁻² of short circuit current density under irradiation of 1000 Wm⁻². It should be possible to further improve the cell efficiency by optimizing the photo-anode using better fabrication methods.

Acknowledgement

Research support from the National Research Council Sri Lanka (NRC 11-196), IPPS Uppsala and the Swedish Research Council is gratefully acknowledged.

REFERENCES

- Abbott D. (2010). Keeping the energy debate clean: how do we supply the world's energy needs? *Proceedings of the IEEE* **98**(1): 42 – 66.
DOI: <http://dx.doi.org/10.1109/JPROC.2009.2035162>
- Albinsson I., Mellander B-E. & Stevens J.R. (1993). Ion association effects and ionic conductivity in polymer electrolytes. *Solid State Ion* **60**: 63 – 66.
DOI: [http://dx.doi.org/10.1016/0167-2738\(93\)90275-8](http://dx.doi.org/10.1016/0167-2738(93)90275-8)
- Albinsson I., Mellander B-E. & Stevens J.R. (1994). Ion conductivity, electrical relaxation and ion association in poly (propylene glycol) complexed with ammonium triflate. *Solid State Ion* **72**: 177 – 182.
DOI: [http://dx.doi.org/10.1016/0167-2738\(94\)90144-9](http://dx.doi.org/10.1016/0167-2738(94)90144-9)
- Armand M.B., Chabagno M.J. & Duclot M.J. (1979). *Fast Ion Transport in Solids* (ed P. Vashishta, J.N. Mandy & G.K. Shenoy). Elsevier, New York, USA.
- Bandara T.M.W.J., Dissanayake M.A.K.L., Albinsson I. & Mellander B-E. (2010a). Dye-sensitized, nano-porous TiO₂ solar cell with poly(acrylonitrile): MgI₂ plasticized electrolyte. *Journal of Power Sources* **195**(11): 3730 – 3734.
DOI: <http://dx.doi.org/10.1016/j.jpowsour.2009.11.148>
- Bandara T.M.W.J., Ekanayake P., Dissanayake M.A.K.L., Albinsson I. & Mellander B-E. (2010b). A polymer electrolyte containing ionic liquid for possible applications in photoelectrochemical solar cells. *Journal of Solid State Electrochemistry* **14**(7): 1221 – 1227.
DOI: <http://dx.doi.org/10.1007/s10008-009-0951-x>
- Bandara T.M.W.J., Dissanayake M.A.K.L., Albinsson I. & Mellander B-E. (2010c). Dye sensitized solar cells with poly(acrylonitrile) based plasticized electrolyte containing MgI₂. *Electrochimica Acta* **55** (6): 2044 – 2047.
DOI: <http://dx.doi.org/10.1016/j.electacta.2009.11.031>
- Chagnes A., Carre B., Willmann P. & Lemordant D. (2002). Modeling viscosity and conductivity of lithium salts in gamma-butyrolactone. *Journal of Power Sources* **109**(11): 203 – 213.
DOI: [http://dx.doi.org/10.1016/S0378-7753\(02\)00073-3](http://dx.doi.org/10.1016/S0378-7753(02)00073-3)
- Chiba Y., Islam A., Watanabe Y., Komiya R., Koide N. & Han L. (2006). Dye-sensitized solar cells with conversion efficiency of 11.1%. *Japanese Journal of Applied Physics* **45** (25): L638–L640.
DOI: <http://dx.doi.org/10.1143/JJAP.45.L638>
- Dissanayake M.A.K.L., Bandara L.R.A.K., Bokalawala R.S.P., Jayathilaka P.A.R.D., Ileperuma O.A. & Somasunderam S. (2002). A novel gel polymer electrolyte based on polyacrylonitrile (PAN) and its application in a solar cell. *Materials Research Bulletin* **37**(5): 867 – 874.
DOI: [http://dx.doi.org/10.1016/S0025-5408\(02\)00712-2](http://dx.doi.org/10.1016/S0025-5408(02)00712-2)
- Fuoss R.M. & Kraus C.A. (1933). Properties of electrolytic solutions. IV. the conductance minimum and the formation of triple ions due to the action of coulomb forces. *Journal of the American Chemical Society* **55**: 2387 – 2399.
DOI: <http://dx.doi.org/10.1021/ja01333a026>
- Gill D.S. (1979). Evaluation of solvated radii of ions in non-aqueous solvents. *Electrochimica Acta* **24**: 701 – 703.
DOI: [http://dx.doi.org/10.1016/0013-4686\(79\)87054-1](http://dx.doi.org/10.1016/0013-4686(79)87054-1)
- Hagfeldt A., Boschloo G., Sun L., Kloo L. & Pettersson H. (2010). Dye-sensitized solar cells. *Chemical Reviews* **110**: 6595 – 6663.
DOI: <http://dx.doi.org/10.1021/cr900356p>
- Ileperuma O.A., Dissanayake M.A.K.L. & Somasundaram S. (2002). Dye-sensitized photoelectrochemical solar cells with polyacrylonitrile based solid polymer electrolytes. *Electrochimica Acta* **47**: 2801 – 2807.
DOI: <http://dx.doi.org/10.1016/j.solmat.2004.02.040>
- Ileperuma O.A., Dissanayake M.A.K.L., Somasunderam S. & Bandara L.R.A.K. (2004). Photoelectrochemical solar cells with polyacrylonitrile-based and polyethylene oxide-based polymer electrolytes. *Solar Energy Materials and Solar Cells* **84**: 117 – 124.
DOI: <http://dx.doi.org/10.1246/cl.2008.36>
- Ileperuma O.A., Kumara G.R.A. & Murakami K. (2008). Quasi-solid polymer electrolytes based on polyacrylonitrile and plasticizers for indoline dye sensitized solar cells of efficiency 5.3%. *Chemistry Letters* **37**(1): 36 – 37.
DOI: <http://dx.doi.org/10.1016/j.jpphotochem.2010.10.024>
- Ileperuma O.A., Kumara G.R.A., Yang H-S. & Murakami K. (2011). Quasi-solid electrolyte based on polyacrylonitrile for dye-sensitized solar cells. *Journal of Photochemistry and Photobiology A: Chemistry* **217**: 308 – 312.
DOI: [http://dx.doi.org/10.1016/S0013-4686\(02\)00166-4](http://dx.doi.org/10.1016/S0013-4686(02)00166-4)
- Jayathilaka P.A.R.D., Dissanayake M.A.K.L., Albinsson I. & Mellander B-E. (2003). Dielectric relaxation, ionic conductivity and thermal studies of the gel polymer electrolyte system PAN/EC/PC/LiTFSI. *Solid State Ion* **156**: 179 – 195.
DOI: [http://dx.doi.org/10.1016/S0167-2738\(02\)00616-1](http://dx.doi.org/10.1016/S0167-2738(02)00616-1)
- Li B., Wang L., Kang B., Wang P. & Qiu Y. (2006). Review of recent progress in solid-state dye-sensitized solar cells. *Solar Energy Materials and Solar Cells* **90**: 549 – 573.
DOI: <http://dx.doi.org/10.1016/j.solmat.2005.04.039>
- Shen X., Xu W., Xu J., Liang G., Yang H. & Yao M. (2008). Quasi-solid-state dye-sensitized solar cells based on gel electrolytes containing different alkali metal iodide salts. *Solid State Ion* **179**: 2027 – 2030.
DOI: <http://dx.doi.org/10.1016/j.ssi.2008.06.027>

21. Shimizu A. & Taniguchi Y. (1990). NMR studies on reorientational motion of hydrated D₂O molecules in tetraalkylammonium bromide dilute aqueous solutions. *Chemical Society of Japan* **63**: 3255 – 3259. DOI: <http://dx.doi.org/10.1246/bcsj.63.3255>
22. Sigvartsen T., Gestblom B., Noreland E. & Songstad J. (1989). Conductometric and dielectric behaviour of solutions of tetrabutylammonium perchlorate in solvents of low and medium permittivity. *Acta Chemica Scandinavica* **43**: 103 – 115. DOI: <http://dx.doi.org/10.3891/acta.chem.scand.43-0103>
23. Southall J.P., Hubbard H.V.S.A., Johnston S.F., Rogers V., Davies G.R., McIntyre J.E. & Ward I.M. (1996). Ionic conductivity and viscosity correlations in liquid electrolytes for incorporation into PVDF gel electrolytes. *Solid State Ion* **85** (1-4): 51 – 60. DOI: [http://dx.doi.org/10.1016/0167-2738\(96\)00040-9](http://dx.doi.org/10.1016/0167-2738(96)00040-9)
24. Stephan M. (2006). Review on gel polymer electrolytes for lithium batteries. *European Polymer Journal* **42**(1): 21 – 42. DOI: <http://dx.doi.org/10.1016/j.eurpolymj.2005.09.017>
25. Tennakone K., Senadeera G.K.R., Perera V.P.S., Kottegoda I.R.M. & Silva L.A.A.D. (1999). Dye-sensitized photoelectrochemical cells based on porous SnO₂/ZnO composite and TiO₂ films with a polymer electrolyte. *Journal of Materials Chemistry* **11**: 2474 – 2477. DOI: <http://dx.doi.org/10.1021/cm990165a>
26. Tominaga Y., Asai S., Sumita M., Panero S. & Scrosati B. (2005). A novel composite polymer electrolyte: effect of mesoporous SiO₂ on ionic conduction in poly(ethylene oxide)–LiCF₃SO₃ complex. *Journal of Power Sources* **146**: 402 – 406. DOI: <http://dx.doi.org/10.1016/j.jpowsour.2005.03.035>
27. Wang Y.-J., Pan Y., Wang L., Pang M.-J. & Chen L. (2005). Conductivity studies of plasticized PEO-Lithium chlorate–FIC filler composite polymer electrolytes. *Materials Letters* **59**: 3021 – 3026. DOI: <http://dx.doi.org/10.1016/j.matlet.2005.05.011>
28. Watanabe M., Nagano S., Sanui K. & Ogata N. (1988). Estimation of Li⁺ transport number in polymer electrolytes by the combination of complex impedance and potentiostatic polarization measurements. *Solid State Ion* **28-30**: 911 – 917.
29. Wright P.V. (1975). Electrical conductivity in ionic complexes of poly (ethylene oxide). *British Polymer Journal* **7**(5): 319 – 327. DOI: <http://dx.doi.org/10.1002/pi.4980070505>
30. Wu J., Lan Z., Wang D., Hao S., Lin J., Huang Y., Yin S. & Sato T. (2006). Gel polymer electrolyte based on poly(acrylonitrile-co-styrene) and a novel organic iodide salt for quasi-solid state dye-sensitized solar cell. *Electrochimica Acta* **51**: 4243 – 4249. DOI: <http://dx.doi.org/10.1016/j.electacta.2005.11.047>