



## **Ionic Liquids: A Simple Model to Predict Ion Conductivity Based on DFT Derived Physical Parameters**

Downloaded from: <https://research.chalmers.se>, 2025-04-25 06:41 UTC

Citation for the original published paper (version of record):

Nilsson Hallén, J., Ahlström, B., Marczewski, M. et al (2019). Ionic Liquids: A Simple Model to Predict Ion Conductivity Based on DFT Derived Physical Parameters. *Frontiers in Chemistry*, 7(MAR). <http://dx.doi.org/10.3389/fchem.2019.00126>

N.B. When citing this work, cite the original published paper.



# Ionic Liquids: A Simple Model to Predict Ion Conductivity Based on DFT Derived Physical Parameters

Jonathan Nilsson-Hallén, Bodil Ahlström<sup>†</sup>, Maciej Marczewski<sup>†</sup> and Patrik Johansson\*

Department of Physics, Chalmers University of Technology, Gothenburg, Sweden

## OPEN ACCESS

### Edited by:

Moisés Canle,  
University of A Coruña, Spain

### Reviewed by:

Milan Vraneš,  
University of Novi Sad, Serbia  
Luis M. Varela,  
University of Santiago de Compostela,  
Spain

### \*Correspondence:

Patrik Johansson  
patrik.johansson@chalmers.se

### <sup>†</sup>Present Address:

Bodil Ahlström,  
National Electric Vehicle Sweden AB,  
Trollhättan, Sweden  
Maciej Marczewski,  
Faculty of Chemistry, Warsaw  
University of Technology, Warsaw,  
Poland

### Specialty section:

This article was submitted to  
Green and Sustainable Chemistry,  
a section of the journal  
Frontiers in Chemistry

**Received:** 30 September 2018

**Accepted:** 18 February 2019

**Published:** 12 March 2019

### Citation:

Nilsson-Hallén J, Ahlström B,  
Marczewski M and Johansson P  
(2019) Ionic Liquids: A Simple Model  
to Predict Ion Conductivity Based on  
DFT Derived Physical Parameters.  
Front. Chem. 7:126.  
doi: 10.3389/fchem.2019.00126

A model able to a priori predict ion conductivities of ionic liquids (ILs) is a desired design tool. We here propose a set of simple conductivity models for ILs composed of small ions by only using data easily derived from standard DFT calculations as input; ion volume, ion mass, ion moment of inertia, and the ion-ion interaction strength. Hence these simple models are totally without any need for experimental parametrization. All model are made from fits of 22 ILs based on 12 different cations and 5 different anions, resulting in correlations vs. experiment of  $R^2 \approx 0.95$  and MAE of 25–36%. Given their (very) simple layout and how fast they can be applied (and re-used), the models allow for ample screening of new IL designs, while not aimed for perfect predictions *per se*.

**Keywords:** ionic liquid, conductivity, DFT, model, ion

## INTRODUCTION

Ionic liquids (ILs) represent an interesting class of materials that during the last few decades have been intensely studied (Plechko and Seddon, 2008; Castner and Wishart, 2010; Thematic issue: Physical chemistry of ionic liquids, 2010; Thematic issue: Ionic liquids, 2012), partly driven by the many potential applications suggested, such as electrolytes in electrochemical energy storage and conversion devices e.g., batteries, fuel cells, solar cells, etc (Armand et al., 2009; Lewandowski and Swiderska-Mocek, 2009; Thematic issue: Ionic liquids for energy applications, 2013). Due to the large number of possible ILs, often estimated to  $10^{12}$ – $10^{14}$ , or even up to  $10^{18}$  (!) (Plechko and Seddon, 2008), methods for predicting the properties of ILs *a priori* to any time-consuming synthesis attempts are highly desirable. Any such method needs to take stance at the ion level and should preferably be general, accurate, non-empirical, and fast. Indeed, there are many different standard modeling approaches applied to ILs from *ab initio*, DFT, MD, to *ab initio* molecular dynamics (AIMD) (Del Pópolo et al., 2005; Tsuzuki et al., 2005; Borodin, 2009; Kirchner, 2009; Maginn, 2009; Angenendt and Johansson, 2010; Johansson et al., 2010; Ueno et al., 2010; Liu and Maginn, 2012; Tsuzuki, 2012), and more analytical methods (Abbott, 2004, 2005; Matsuda et al., 2007; Slattery et al., 2007; Tochigi and Yamamoto, 2007; Preiss et al., 2010; Eiden et al., 2011). All aim at predicting/estimating melting points (Slattery et al., 2007; Preiss et al., 2010), viscosities (Abbott, 2004; Matsuda et al., 2007; Slattery et al., 2007; Tochigi and Yamamoto, 2007; Ueno et al., 2010; Eiden et al., 2011), and not the least the ionic conductivities (Abbott, 2005; Del Pópolo et al., 2005; Tsuzuki et al., 2005; Matsuda et al., 2007; Slattery et al., 2007; Tochigi and Yamamoto, 2007; Borodin, 2009; Johansson et al., 2010; Ueno et al., 2010; Eiden et al., 2011; Liu and Maginn, 2012; Tsuzuki, 2012). While in general highly successful for their purposes, they often, however, have either limited accuracy, are time-consuming or require ion-specific or empirical parameters.

From an experimental point of view ion conductivity data are most often provided as Arrhenius plots,  $\sigma = f(1/T)$ , and can for ILs be accurately fitted using the Vogel-Tamman-Fulcher (VTF) equation (Vila et al., 2006),

$$\sigma = \sigma_{\infty} \exp\left(-\frac{E_a}{k_b(T - T_0)}\right) \quad (1)$$

where  $\sigma_{\infty}$  is the conductivity at infinite temperature,  $E_a$  is the activation energy, and  $T_0$  is a constant related to transformation of the observed glass transition temperature,  $T_g$ , to the ideal.

The general features of the VTF equation, together with a lot of other types of expressions, were here used as starting points to generate models for the ionic conductivity of ILs. Many previous IL conductivity models have shown a strong dependency on the ion volumes, but require ion-specific, most often anion-specific, parameters (Tsuzuki et al., 2005; Matsuda et al., 2007; Slattery et al., 2007; Borodin, 2009; Angenendt and Johansson, 2010; Ueno et al., 2010; Tsuzuki, 2012) or resort to analyzing ILs with very similar anions (Johansson et al., 2010). In order to avoid this, which severely limits the generality, we have included not only the ion volumes, but also ion (reduced) masses—as proven to affect the viscosity (Abbott, 2004, 2005; Matsuda et al., 2007), and ion moments of inertia as input parameters to a wide variety of (VTF-based) models. Furthermore, as a combination of (at least) two ions, a cation and an anion, is needed to create any IL, the strength of the specific ion-ion interaction was used as another parameter—more or less as a proxy for the activation energy ( $E_a$ ) in the VTF expression—even if the connection between these is far from obvious (Tsuzuki et al., 2005; Borodin, 2009; Angenendt and Johansson, 2010; Johansson et al., 2010; Ueno et al., 2010; Tsuzuki, 2012). We would also like to stress that we here avoid any additional complexity of IL nano-structuration by only studying ILs with rather short cation alkyl chain lengths. We have also chosen to include imidazolium based ILs with the C2 position methylated as these seem to introduce a specific behavior in terms of ion-ion interaction. All the parameters are obtained starting from standard density functional theory (DFT) calculations on ions and cation-anion ion pairs—and can thus be used to create models totally without any experimental parametrization—one major advantage of the approach chosen.

The various models developed in this study have been fitted and evaluated against in-house measured ionic conductivities. While this clearly limits the statistics of the study in terms of quantity, it improves the quality as it avoids the errors that can result from gathering data from many different sources—important as reported IL conductivities are very sensitive to impurities, not the least water, and the set-up/sample history. From this approach the best fits are reported as largely phenomenological models using some few statistical measures and then discussed in terms of e.g., sensitivity vs. the different input parameters computed and the ILs chosen to study.

## MATERIALS AND METHODS

In total 22 different ILs were used as received from Solvionic with the highest purity available (99.9 or 99.5%). The temperature

**TABLE 1** | Name (acronym), volume (V), mass (M), and moment of inertia (I) of ions.

| Name   | V [Å <sup>3</sup> ] | M [u] | I [Å <sup>2</sup> u] |
|--|---------------------|-------|----------------------|
| 1-ethyl-3-methylimidazolium (EMI)                    | 156                 | 111   | 315                  |
| 1-butyl-3-methylimidazolium (BMI)                    | 196                 | 139   | 577                  |
| 1-hexyl-3-methylimidazolium (HMI)                    | 246                 | 167   | 1,041                |
| 1,3-dimethyl-2-propylimidazolium (PMMI)              | 204                 | 139   | 536                  |
| 1,3-dimethyl-2-butylimidazolium (BMMI)               | 224                 | 153   | 760                  |
| trimethyl-butylammonium (Me <sub>3</sub> BuN)        | 111                 | 193   | 429                  |
| trimethyl-hexylammonium (Me <sub>3</sub> HexN)       | 148                 | 240   | 934                  |
| diethylmethylpropylammonium (Et <sub>2</sub> MeProN) | 212                 | 130   | 438                  |
| 1-propyl-1-methylpyrrolidinium (MPPyr)               | 199                 | 128   | 409                  |
| 1-butyl-1-methylpyrrolidinium (BMPyr)                | 222                 | 142   | 638                  |
| 1-pentyl-1-methylpyrrolidinium (MPePyr)              | 242                 | 156   | 896                  |
| 1-propyl-1-methylpiperidinium (MPPip)                | 221                 | 142   | 483                  |
| tetrafluoroborate (BF <sub>4</sub> )                 | 71                  | 87    | 95                   |
| hexafluorophosphate (PF <sub>6</sub> )               | 96                  | 145   | 201                  |
| trifluoromethanesulfonate (Tf)                       | 115                 | 149   | 276                  |
| bis(fluorosulfonyl)imide (FSI)                       | 136                 | 180   | 446                  |
| bis(trifluoromethanesulfonyl)imide (TFSI)            | 199                 | 280   | 1,214                |

dependent ionic conductivity was measured using a Novocontrol broadband dielectric spectrometer in the frequency range  $10^{-1}$ - $10^7$  Hz. A liquid parallel plate cell, BDS 1308 Novocontrol, with two stainless steel electrodes with a Teflon spacer ( $\varnothing = 13.2$  mm,  $d = 0.99$  mm) was assembled in an Ar glove box ( $H_2O$  and  $O_2 < 1$  ppm) and loaded into a cryo-furnace with  $N_2$  gas flow. Data were collected during heating from 298.15 to 368.15 K in steps of 10 K and stabilization times of 30 min. The DC conductivities were obtained from the low frequency plateau of the conductivity isotherms by plotting the real part of the complex conductivity as a function of frequency.

Computationally low-energy conformers of all cations (12) and anions (5) (Table 1) constituting the totally 22 ILs investigated experimentally were initially generated by the molecular mechanics based scan routine in Spartan 06<sup>1</sup>. Amongst the cations we use the most popular families: imidazolium, EMI etc., and pyrrolidinium, MPPyr (Pyr13) etc. From these the geometries and energies were optimized by DFT, first at the B3LYP/6-311+G\* level and subsequently further with M06-2X/6-311+G\* (Vosko et al., 1980; Lee et al., 1988; Becke, 1993; Zhao and Truhlar, 2007), and their 2nd derivatives calculated to ensure the geometries to be local minima energy structures. From the DFT results the ion volumes were calculated as averages of 10 runs using a Monte Carlo (MC) integration scheme of a  $0.001 e/\text{bohr}^3$  density envelope and 100 integration points/ $\text{bohr}^3$ . The moments of inertia of the ions were calculated as the arithmetic mean of the three principal eigenvalues obtained from the routine in the VMD software (Humphrey et al., 1996).

The lowest energy conformers (B3LYP) for each of the ions were used to generate cation-anion ion pairs, with 20 starting

<sup>1</sup>Spartan '06, Wavefunction Inc.


**TABLE 2** | Cation-anion ion-pair,  $E_{\text{int}}$ , and glass transition temperature ( $T_g$ ) of the ILs.

| Cation-Anion               | $E_{\text{int}}$ (M06-2X/6-311+G*) [kJmol <sup>-1</sup> ] | $T_g$ [K]                      |
|----------------------------|---|--------------------------------|
| EMI-Tf                     | -378.9  | -                              |
| EMI-FSI                    | -362.3  | -                              |
| EMI-TFSI                   | -360.5  | 181 (Fredlake et al., 2004)    |
| BMI-BF <sub>4</sub>        | -385.0  | 188 (Fredlake et al., 2004)    |
| BMI-PF <sub>6</sub>        | -363.6  | 197 (Fredlake et al., 2004)    |
| BMI-Tf                     | -376.5  | 191 (Tokuda et al., 2006)      |
| BMI-TFSI                   | -367.3  | 187 (Fredlake et al., 2004)    |
| HMI-PF <sub>6</sub>        | -362.2  | 195 (Harris et al., 2007)      |
| HMI-Tf                     | -374.6  | 189 (Gómez et al., 2013)       |
| HMI-TFSI                   | -363.7  | 189 (Gómez et al., 2013)       |
| PMMI-TFSI                  | -364.2  | -                              |
| BMMI-TFSI                  | -363.7  | -                              |
| Me <sub>3</sub> BuN-TFSI   | -343.9  | 199 (Tokuda et al., 2006)      |
| Me <sub>3</sub> HexN-TFSI  | -353.5  | 202 (Taggougui et al., 2008)   |
| Et <sub>2</sub> MeProN-FSI | -340.7  | -                              |
| MPPyr-FSI                  | -343.3  | 190 (Zhou et al., 2008)        |
| MPPyr-TFSI                 | -346.8  | 188 (Calvar et al., 2013)      |
| BMPyr-Tf                   | -361.5  | 197 (Calvar et al., 2013)      |
| BMPyr-TFSI                 | -351.2  | 191 (Calvar et al., 2013)      |
| MPePyr-TFSI                | -352.1  | -                              |
| MPPip-FSI                  | -332.9  | -                              |
| MPPip-TFSI                 | -338.5  | 192 (Paduszynski et al., 2011) |

configurations for each pair generated by our in-house developed software SECIL (Angenendt and Johansson). All structures were optimized in two steps; i) B3LYP/6-311+G\* - providing a selection of 10 structures/ion pair based on energy and transferred to ii) M06-2X/6-311+G\*. Not all SECIL generated configurations reach SCF convergence, but most B3LYP minima produce M06-2X minima, as verified by the 2nd derivatives. All DFT and MC calculations were made using the Gaussian 03 and 09 program packages (Frisch et al., 2004, 2010). From the M06-2X/6-311+G\* data the ion-ion interaction energy,  $E_{\text{int}} = E_{(\text{ion pair})} - \Sigma(E_{\text{cation}} + E_{\text{anion}})$ , was calculated—as a measure of specific ion-ion interaction strength (Table 2). Due to the main aim of arriving at a proof-of-concept method, and not the most performant, and the many other model omissions and simplifications, no comparisons to other DFT functionals (or higher *ab initio* methods) nor any basis set size effect investigations or basis set super-position error corrections were made.

Using the ion volume ( $V$ ), mass ( $M$ ), moment of inertia ( $I$ ) and ion pair ( $E_{\text{int}}$ , reduced mass) data generated, potential models for the conductivity as function of temperature were formulated and tested with OriginPro 2015<sup>2</sup>, using the Levenberg-Marquardt iteration algorithm to fit the data to a predefined function. The most promising models were further combined to achieve better fits, while kept physically sound.

<sup>2</sup>OriginLab, Northampton, MA, USA

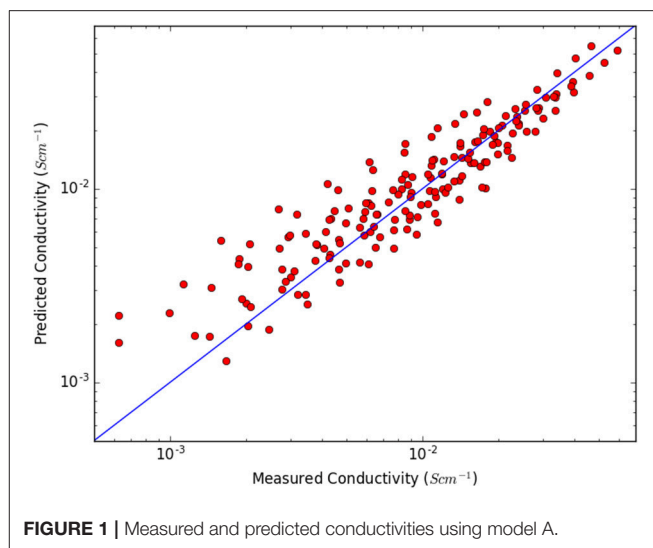**FIGURE 1** | Measured and predicted conductivities using model A.

## RESULTS AND DISCUSSION

The computational data generated span an appreciable range of IL ion volumes (71–246 Å<sup>3</sup>), masses (87–280 u), moments of inertia (95–1214 Å<sup>2</sup>u), and interaction energies (–333 to –385 kJmol<sup>-1</sup>). The first model found with an appreciable fit to the conductivity data, 176 data points for the 22 ILs, is **A** (Figure 1):

$$\sigma = \frac{b}{V_{\text{tot}}^2 I_+} \exp\left(c \frac{E_{\text{int}}}{T - T_0}\right) \quad (\text{A})$$


where the input parameters  $V_{\text{tot}}$  is the sum of the cation and anion volumes,  $I_+$  is the moment of inertia of the cation, and  $E_{\text{int}}$  is the interaction energy, while  $b$ ,  $c$ , and  $T_0$  are fitting parameters. That the conductivity is inversely proportional to the ion volumes, as in **A**, can easily be understood as larger ions both move slower and hinder movement of other ions and this has indeed been found previously (Slattery et al., 2007; Johansson et al., 2010; Tsuzuki, 2012), but why it should be proportional to the inverse of the volume squared is unclear.

It has previously been shown that the viscosity of ILs is affected by the IL ion masses (Abbott, 2004, 2005; Matsuda et al., 2007) and as the conductivity is related to the fluidity, the inverse of the viscosity through the fractional Walden rule, it is reasonable to assume that these could affect the conductivity. The reduced masses,  $M_{\text{red}}$ , are indeed almost linearly proportional to the volumes  $V_{\text{tot}}$  (Figure 2).


Why a second model, **A2**, with one of the terms exchanged, was investigated—with almost equally good fit (Figure 3):

$$\sigma = \frac{b}{V_{\text{tot}} M_{\text{red}} I_+} \exp\left(c \frac{E_{\text{int}}}{T - T_0}\right) \quad (\text{A2})$$

In both models **A** and **A2**  $T_0$  has to some extent been treated as a normal fitting parameter. This enables a true prediction of conductivity without any prior IL synthesis, but given the coupling of  $T_0$  to  $T_g$ , experimental  $T_g$  data as input might

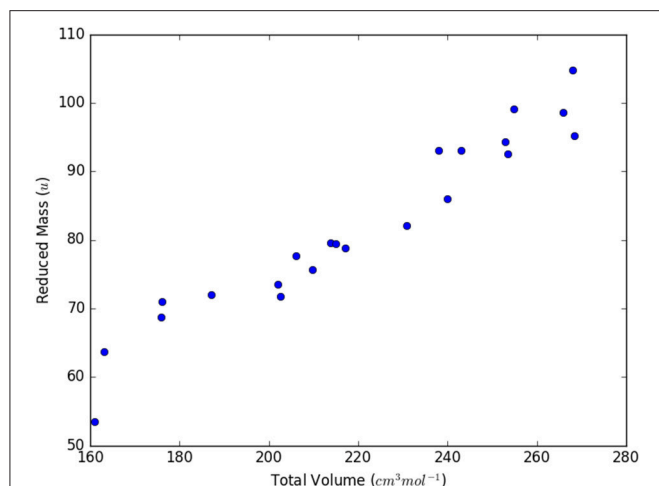

**FIGURE 2** | Correlation between total volume and reduced mass for the IL ion pairs.

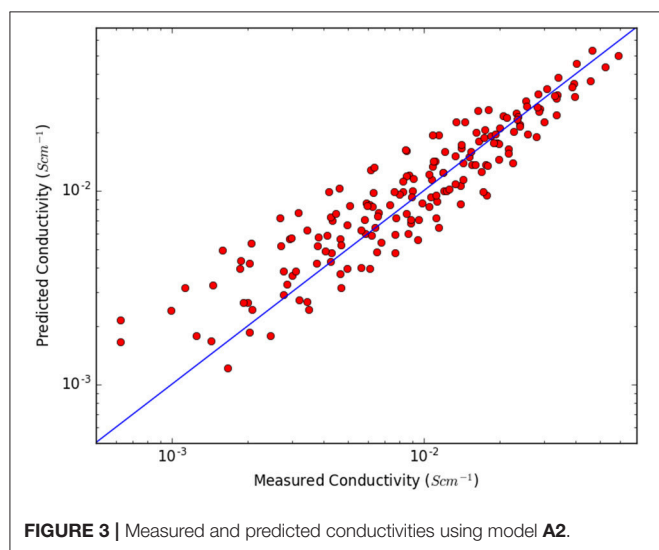

**FIGURE 3** | Measured and predicted conductivities using model A2.

improve the fits and models. In the literature  $T_g$  for 15 of the 22 ILs used were found (Table 2) covering the range 181–202 K (which arguably is a rather limited span in temperature). Applying these data to A and A2 result in models B and B2, respectively:

$$\sigma = \frac{b}{V_{tot}^2 I_+} \exp\left(\frac{E_{int}}{T - (T_g + d)}\right) \quad (\text{B})$$

$$\sigma = \frac{b}{V_{tot} M_{red} I_+} \exp\left(\frac{E_{int}}{T - (T_g + d)}\right) \quad (\text{B2})$$

where  $d$  is an additional fitting parameter and indeed the fits are slightly improved. Using the reduced data set (15/22) in A and A2 did not improve their fits and thus the improvement indeed comes from the inclusion of  $T_g$  (keeping in mind the limited T range). All models with their parameter values and statistical measures are summarized in Table 3.

**TABLE 3** | Fitting parameter values, correlation coefficients ( $R^2$ ), and mean absolute errors (MAE) for the four IL conductivity models.

| Model | $b$ [ $\text{Scm}^{-1}\text{\AA}^8\text{u}$ ] | $c$ [ $\text{KkJ}^{-1}$ ] | $T_0/d$ [K]     | $R^2$  | MAE [%] |
|-------|---|---------------------------|-----------------|--------|---------|
| A     | $1.29 \pm 0.45 \times 10^7$                   | $-1.01 \pm 0.26$          | $204 \pm 18.0$  | 0.9538 | 35.3    |
| A2    | $2.52 \pm 0.88 \times 10^6$                   | $-0.90 \pm 0.25$          | $211 \pm 18.0$  | 0.9508 | 36.5    |
| B     | $1.09 \pm 0.38 \times 10^7$                   | $-0.82 \pm 0.23$          | $34.6 \pm 15.9$ | 0.9627 | 24.8    |
| B2    | $3.19 \pm 1.22 \times 10^6$                   | $-1.01 \pm 0.28$          | $22.6 \pm 17.6$ | 0.9600 | 26.1    |

## CONCLUDING REMARKS

Two VFT based models for IL conductivity without any experimental input have been developed using volume, mass, and moment of inertia of the constituting ions and the energy of the interaction between cation and anion. In contrast to earlier models there are no anion-specific parameters needed, and in addition moments of inertia of the cations are for the first time included. For the latter feature we initially believed a larger principal moment of inertia to be likely to have a decisive influence due to the elongated shape of many of the ions. However, no such behavior was found in the fits why the arithmetic mean of the three principal values is used. The main influence by the cation moment of inertia is due to many anions being close to spherical. All models without  $I_+$  performed much worse than the fits here obtained and the inclusion of experimental glass transition temperatures improves the fit, but not to any large extent. From a physical point of view, the ion mass may influence the conductivity, why both A2 and B2, replacing one of the volume terms with the reduced masses of the ion pairs, could improve the fit if applied to a larger and more diverge data set (even if they here actually reduce the goodness of the fit). As VFT models in general captures ion conductivities of ILs (and other systems) quite well all of the above in terms of overall agreement come as no major surprise. Phenomenologically all the four (VFT) models show the expected behavior; as the volumes, moments of inertia, and masses of the ions increase, the conductivity will approach zero (0), and if they decrease the conductivity will increase. Likewise, if the ion-ion interaction energy increases to infinity the conductivity will approach zero and the conductivity increases with temperature. The inclusion of experimental glass transition temperatures did improve the fit, but there is a rather narrow temperature range for the  $T_g$  used. We stress that we do refrain from trying to connect the input parameters to any direct physical interpretation—such as why the prefactor in the VFT equations seem to relate to the ion volume squared, and how in the exponential the ion-ion interaction energy relate to the activation energy, etc. We do, however, believe it to be straightforward to produce input to these models for any IL of choice—remembering our deliberately set limits of no nano-structured ILs—for which this model is likely to fail—dependent on how the ion mobility is affected. The DFT calculations will be the time-determining step, even if most data required only needs to be calculated once for each ion, the interaction energy of each ion pair must be obtained separately for each IL.

## AUTHOR CONTRIBUTIONS

JN-H performed the fits based on input from PJ and BA and made a first draft of the paper. MM measured all experimental data. PJ outlined the idea and wrote the final manuscript.

## REFERENCES

- Abbott, A. P. (2004). Application of hole theory to the viscosity of ionic and molecular liquids. *Chem. Phys. Chem* 5, 1242–1246. doi: 10.1002/cphc.200400190
- Abbott, A. P. (2005). Model for the conductivity of ionic liquids based on an infinite dilution of holes. *Chem. Phys. Chem.* 6, 2502–2505. doi: 10.1002/cphc.200500283
- Angenendt, K., and Johansson, P. SECIL- Software Engine for Configuration of Ionic Liquids.
- Angenendt, K., and Johansson, P. (2010). Ionic liquid structures from large density functional theory calculations using mindless. *Configurations J. Phys. Chem. C* 114, 20577–20582. doi: 10.1021/jp104961r
- Armand, M., Endres, F., MacFarlane, D. R., Ohno, H., and Scrosati, B. (2009). Ionic-liquid materials for the electrochemical challenges of the future. *Nat. Mater.* 8, 621. doi: 10.1038/nmat2448
- Becke, A. D. (1993). Density-functional thermochemistry. III. The role of exact exchange. *J. Chem. Phys.* 98, 5648.
- Borodin, O. (2009). Relation between heat of vaporization, ion transport, molar volume, and cation–anion binding energy for ionic liquids. *J. Phys. Chem. B* 113, 12353–12357. doi: 10.1021/jp9070357
- Calvar, N., Gómez, E., Macedo, E. A., and Domínguez, Á. (2013). Thermal analysis and heat capacities of pyridinium and imidazolium ionic liquids. *Thermochim. Acta* 565, 178–182. doi: 10.1016/j.tca.2013.05.007
- Castner, E. W. Jr. and Wishart, J. F. (2010). Spotlight on ionic liquids. *J. Chem. Phys.* 132, 120901. doi: 10.1063/1.3373178
- Del Pópulo, M. G., Lynden-Bell, R. M., and Kohanoff, J. (2005). *Ab Initio* molecular dynamics simulation of a room temperature ionic liquid. *J. Phys. Chem. B* 109, 5895–5902. doi: 10.1021/jp044414g
- Eiden, P., Bulut, S., Köchner, T., Friedrich, C., Schubert, T., Krossing, I., et al. (2011). *In silico* predictions of the temperature-dependent viscosities and electrical conductivities of functionalized and non-functionalized ionic liquids. *J. Phys. Chem. B* 115, 300–309. doi: 10.1021/jp108059x
- Fredlake, C. P., Crosthwaite, J. M., Hert, D. G., Aki, S. N. V. K., and Brennecke, J. F. (2004). Thermophysical properties of imidazolium-based ionic liquids. *J. Chem. Eng. Data* 49, 954–964. doi: 10.1021/je034261a
- Frisch, M. J., Trucks, G. W., Schlegel, H. B., Scuseria, G. E., Robb, M. A., Cheeseman, J. R., et al. (2004). *Gaussian 03*. (Wallingford, CT).
- Frisch, M. J., Trucks, G. W., Schlegel, H. B., Scuseria, G. E., Robb, M. A., Cheeseman, J. R., et al. (2010). *Gaussian 09*. (Wallingford, CT).
- Gómez, E., Calvar, N., Domínguez, Á., and Macedo, E. A. (2013). Thermal analysis and heat capacities of 1-Alkyl-3-methylimidazolium ionic liquids with NTf<sub>2</sub><sup>-</sup>, TFO<sup>-</sup>, and DCA<sup>-</sup> anions. *Ind. Eng. Chem. Res.* 52, 2103–2110. doi: 10.1021/ie3012193
- Harris, K. R., Kanakubo, M., and Woolf, L. A. (2007). Temperature and pressure dependence of the viscosity of the ionic liquids 1-hexyl-3-methylimidazolium hexafluorophosphate and 1-butyl-3-methylimidazolium bis(trifluoromethylsulfonyl)imide. *J. Chem. Eng. Data* 52, 1080–1085. doi: 10.1021/je700032n
- Humphrey, W., Dalke, A., and Schulten, K. (1996). VMD: visual molecular dynamics. *J. Mol. Graph.* 14, 33–38.
- Johansson, P., Fast, L. E., Matic, A., Appetecchi, G. B., and Passerini, S. (2010). The conductivity of pyrrolidinium and sulfonylimide based ionic liquids: A combined experimental and computational study. *Power Sources J.* 195, 2074–2076. doi: 10.1016/j.jpowsour.2009.10.029
- Kirchner, B. (2009). Ionic liquids from theoretical investigations. *Top. Curr. Chem.* 290, 213–262. doi: 10.1007/128\_2008\_36
- Lee, C., Yang, W., and Parr, R. G. (1988). Development of the Colle-Salvetti correlation-energy formula into a functional of the electron density. *Phys. Rev. B* 37, 785.
- Lewandowski, A., and Swiderska-Mocek, A. (2009). Ionic Liquids as electrolytes for li-ion batteries—an overview of electrochemical studies. *Power Sources J.* 194, 601–609. doi: 10.1016/j.jpowsour.2009.06.089
- Liu, H., and Maginn, E. (2012). An MD study of the applicability of the walden rule and the nernst–einstein model for ionic liquids. *Chem. Phys. Chem.* 13, 1701–1707. doi: 10.1002/cphc.201200016
- Maginn, E. J. (2009). Molecular simulation of ionic liquids: current status and future opportunities. *J. Phys. Cond. Matt.* 21:373101. doi: 10.1088/0953-8984/21/37/373101
- Matsuda, H., Yamamoto, H., Kurihara, K., and Tochigi, K. (2007). Prediction of the ionic conductivity and viscosity of ionic liquids by QSPR using descriptors of group contribution type. *J. Comp. Aid Chem.* 8, 114–127. doi: 10.2751/jcac.8.114
- Paduszynski, K., Chiyen, J., Ramjugernath, D., Letcher, T. M., and Domanska U (2011). Liquid–liquid phase equilibrium of (piperidinium-based ionic liquid+ an alcohol) binary systems and modelling with NRHB and PCP-SAFT. *Fluid Phase Equilibria* 305, 43–52. doi: 10.1016/j.fluid.2011.03.005
- Plechikova, N. V., and Seddon, K. R. (2008). Applications of ionic liquids in the chemical industry. *Chem. Soc. Rev.* 37, 123. doi: 10.1039/B006677J
- Preiss, U., Bulut, S., and Krossing, I. (2010). *In silico* prediction of the melting points of ionic liquids from thermodynamic considerations: a case study on 67 salts with a melting point range of 337°C. *J. Phys. Chem. B* 114, 11133–11140. doi: 10.1021/jp104679m
- Slattery, J. M., Daguinet, C., Dyson, P. J., Schubert, T. J. S., and Krossing, I. (2007). How to predict the physical properties of ionic liquids: a volume-based approach. *Angew. Chem.* 119, 5480–5484. doi: 10.1002/anie.200700941
- Taggougui, M., Diaw, M., Carré, B., Willmann, P., and Lemordant, D. (2008). Solvents in salt electrolyte: Benefits and possible use as electrolyte for lithium-ion battery. *Electrochim. Acta* 53, 5496–5502. doi: 10.1016/j.electacta.2008.03.012
- Thematic issue: Ionic liquids (2012). *Faraday Discuss.* 154.
- Thematic issue: Ionic liquids for energy applications (2013). *MRS Bull.* 38.
- Thematic issue: Physical chemistry of ionic liquids (2010). *Phys. Chem. Chem. Phys.* 12.
- Tochigi, K., and Yamamoto, H. (2007). Estimation of ionic conductivity and viscosity of ionic liquids using a QSPR model. *J. Phys. Chem. C* 111, 15989–15994. doi: 10.1021/jp073839a
- Tokuda, H., Tsuzuki, S., Susan, M. A., Hayamizu, K., and Watanabe, M. (2006). How ionic are room-temperature ionic liquids? an indicator of the physicochemical properties. *J. Phys. Chem. B* 110, 19593–19600. doi: 10.1021/jp064159v
- Tsuzuki, S. (2012). Factors controlling the diffusion of ions in ionic liquids. *Chem. Phys. Chem.* 13, 1664–1670. doi: 10.1002/cphc.201100870
- Tsuzuki, S., Tokuda, H., Hayamizu, K., and Watanabe, M. (2005). Magnitude and directionality of interaction in ion pairs of ionic liquids: relationship with ionic conductivity. *J. Phys. Chem. B* 109, 16474–16481. doi: 10.1021/jp0533628
- Ueno, K., Tokuda, H., and Watanabe, M. (2010). Ionicity in ionic liquids: correlation with ionic structure and physicochemical properties. *Phys. Chem. Chem. Phys.* 12, 1649–1658. doi: 10.1039/b921462n
- Vila, J. Ginés, P., Pico, J. M., Franjo, C., Jiménez, E., Varela, L.M., et al. (2006). Temperature dependence of the electrical conductivity in EMIM based ionic liquids. Evidence of Vogel–Tamman–Fülcher behavior. *Fluid Phase Equilibria* 242, 141–146. doi: 10.1016/j.fluid.2006.01.022
- Vosko, S. H., Wilk, L., and Nusair, M. (1980). Accurate spin-dependent electron liquid correlation energies for local spin density calculations: a critical analysis. *Can. J. Phys.* 58, 1200.

## ACKNOWLEDGMENTS

This study was initiated within the project The Physics of Ionic Liquids funded by a basic research grant from the Swedish Research Council (VR)—gratefully acknowledged.

- Zhao, Y., and Truhlar, D. G. (2007). The M06 suite of density functionals for main group thermochemistry, thermochemical kinetics, noncovalent interactions, excited states, and transition elements: two new functionals and systematic testing of four M06-class functionals and 12 other functionals. *Theor. Chem. Acc.* 120, 215–241. doi: 10.1007/s00214-007-0310-x
- Zhou, Q., Henderson, W. A., Appetecchi, G. B., Montanino, M., and Passerini, S. (2008). Physical and electrochemical properties of N-alkyl-N-methylpyrrolidinium bis(fluorosulfonyl)imide ionic liquids: PY13FSI and PY14FSI. *J. Phys. Chem. B* 112, 13577–13580. doi: 10.1021/jp805419f

**Conflict of Interest Statement:** The authors declare that the research was conducted in the absence of any commercial or financial relationships that could be construed as a potential conflict of interest.

Copyright © 2019 Nilsson-Hallén, Ahlström, Marczewski and Johansson. This is an open-access article distributed under the terms of the Creative Commons Attribution License (CC BY). The use, distribution or reproduction in other forums is permitted, provided the original author(s) and the copyright owner(s) are credited and that the original publication in this journal is cited, in accordance with accepted academic practice. No use, distribution or reproduction is permitted which does not comply with these terms.