



## Effect of diluent on the extraction of europium(iii) and americium(iii) with N,N,N',N'-tetraoctyl diglycolamide (TODGA)

Downloaded from: <https://research.chalmers.se>, 2025-12-05 00:14 UTC

Citation for the original published paper (version of record):

Kajan, I., Florianova, M., Ekberg, C. et al (2021). Effect of diluent on the extraction of europium(iii) and americium(iii) with N,N,N',N'-tetraoctyl diglycolamide (TODGA). RSC Advances, 11(58): 36707-36718.  
<http://dx.doi.org/10.1039/d1ra07534a>

N.B. When citing this work, cite the original published paper.


Cite this: *RSC Adv.*, 2021, 11, 36707

# Effect of diluent on the extraction of europium(III) and americium(III) with *N,N,N',N'*-tetraoctyl diglycolamide (TODGA)

Ivan Kajan, <sup>\*,a</sup> Markéta Florianová,<sup>b</sup> Christian Ekberg<sup>c</sup> and Artem V. Matyskin <sup>†c</sup>

Solvent extraction of  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  via *N,N,N',N'*-tetraoctyl diglycolamide (TODGA) dissolved in different molecular diluents was studied. The diluent types used in this work were primary and secondary alcohols, secondary ketones and alkanes. Effects of concentration of extracting agent, temperature, diluent type and its carbon chain length on the extractions were determined. Distribution ratios of  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  showed high dependence on the diluent type as well as the carbon chain length within the same type of diluent. The highest distribution ratios for both  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  as well as the separation factors of  $\text{Eu}^{3+}$  over  $\text{Am}^{3+}$  were observed in the alkane diluents. Unexpectedly high distribution ratios for  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  were observed in polar diluents with 5 carbon atoms in the chain, clearly standing out against the general trends. It was found that  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  extraction via TODGA is enthalpy driven in all the studied diluents and that extraction is more exothermic in alkane diluents. Analysis of the stoichiometry of the extracted complexes shows that the average ligand number of TODGA molecules in the extracted complex is lower for  $\text{Am}^{3+}$  compared to  $\text{Eu}^{3+}$  except for with alkane diluents.

Received 12th October 2021  
Accepted 8th November 2021

DOI: 10.1039/d1ra07534a

rsc.li/rsc-advances

## 1 Introduction

Solvent extraction is a separation technique commonly used in many various industries including mining and nuclear fuel reprocessing, as well as being one of the foreseen methods for recycling rare earth elements from nickel-metal hydride batteries, permanent magnets or modern electronics.<sup>1–4</sup> Its ease of use for industrial application offers efficient application and high purity of extracted metal. A tremendous effort during the last decades has been put into the development of new, more selective, extracting agents for the extraction processes. At the same time basic phenomena in the particular solvent extraction processes are poorly understood. One of them is the effect of the diluent on the extraction process. Diluent is defined as: “the liquid or homogeneous mixture of liquids in which extractant(s) and possible modifier(s) may be dissolved to form the solvent phase.”<sup>5</sup> The organic diluent is the major constituent of the organic phase in the solvent extraction systems. It was already shown in the past that

diluent has a substantial effect on the outcome of the extraction with respect to both distribution ratios as well as separation factors between different elements.<sup>6–15</sup> Despite the strong experimental evidence of diluent effect, its full theoretical explanation is challenging and predictions are still very uncertain. Few theoretical explanations for the diluent effect were proposed. The first introduction of diluent effect to the predictions of distribution ratios in solvent extraction was proposed by Schmidt.<sup>15</sup> An empirical diluent parameter was included to predict the distribution ratios of zinc extracted by tri-*n*-octyl-amine in different diluents. Unfortunately, the proposed predictions were valid only for a limited number of diluents even with only one extracting agent. Another explanation of diluent effect is based on the energetic balance between the cost of cavity formation within the diluent into which the extracted molecule is placed and the energetic gain from interaction between the diluent and the extracted molecule.<sup>3,16</sup> In order to get a deeper understanding into the energetic cost of the cavity creation Hildebrand used the heat of vaporization to predict the cohesive forces within liquids. The model is based on the proportionality of the heat of vaporization to the intermolecular binding energy.<sup>17,18</sup> This idea was further developed by Hansen dividing the solubility parameter into three vectors consisting of the hydrogen bonding, polar and dispersion interactions.<sup>19</sup> Hansen's model has been successfully applied on mutual solubility of polymers in solvents or plasticizers. However, in solvent extraction, simple correlations of extraction constants ( $K_d$ ) against solubility

<sup>a</sup>Laboratory of Radiochemistry, Paul Scherrer Institute, 5232 Villigen, Switzerland.  
E-mail: ivan.kajan@psi.ch

<sup>b</sup>Department of Nuclear Chemistry, Faculty of Nuclear Sciences and Physical Engineering, Czech Technical University, Břehova 7, 11519 Prague 1, Czech Republic

<sup>c</sup>Nuclear Chemistry and Industrial Material Recycling Group, Department of Chemistry and Chemical Engineering, Chalmers University of Technology, 41296 Gothenburg, Sweden

<sup>†</sup> Present address: Chemistry Division, Los Alamos National Laboratory, P. O. Box 1663, 87545 Los Alamos, New Mexico, United States of America.


parameters are not sufficient for predictions of the extraction outcome.<sup>20</sup> At the same time systematic experimental studies on the diluent effect are very scarce.<sup>21</sup>

In order to further investigate the effects of diluent on extraction, the aim of this study is the systematic evaluation of the molecular diluent effect on the extraction of trivalent europium and americium from nitric acid solutions with *N,N,N',N'*-tetraoctyl diglycolamide as an extracting agent. The family of diglycolamides are known extracting agents for trivalent lanthanides and actinides in solvent extraction, with expected application in partitioning and transmutation of a nuclear fuel<sup>22–25</sup> and in radiopharmaceutical industry for <sup>225</sup>Ac production.<sup>26–29</sup> While the behavior of diglycolamides with respect to equilibrium distribution ratios, acid extraction and kinetics was extensively evaluated,<sup>30–42</sup> the effect of the diluent on the extraction was evaluated only in a few studies.<sup>42–47</sup> From the available data, correlations of diluent properties against the distribution ratios seems rather difficult. It was shown that in nonpolar diluents benzene rings give decrease in the extraction of americium.<sup>32,43</sup> At the same time, distribution ratios of americium and lanthanides in the polar nitrobenzene media are high.<sup>32,48</sup>

Correlations of distribution ratios against dielectric constants of used diluents seem to be also non-conclusive.<sup>49</sup> Dielectric constant of the diluent appears to have effect on the stoichiometry of the extracted americium complex giving lower ligand number in diluents with higher dielectric constants.<sup>32,43,44,48,49</sup> In the diluents with higher polarity (*e.g.* dichloroethane, octanol) 1 : 2 metal : TODGA complex was observed whereas in low polarity diluents (*e.g.* chloroform, toluene, dodecane) 1 : 3 or 1 : 4 metal : TODGA molecules were detected.<sup>43,44</sup> At the same time it was shown that the nature of the diluent does not affect the results of time resolved laser fluorescence measurements luminescence spectra of Eu<sup>3+</sup>.<sup>38,45</sup>

In order to bring deeper insight into diluent effects, we performed a systematic study of the molecular diluent influence on solvent extraction of americium and europium by *N,N,N',N'*-tetraoctyl diglycolamide (TODGA) from nitric acid media. Three different groups of diluents consisting of alkanes, long chained alcohols and ketones were studied. The effect of the carbon chain length, was evaluated from 5 to 10 carbons in order to target the subtle changes in the polarity of used diluents. Moreover, standard molar Gibbs energy ( $\Delta G_{298}^0$  K), enthalpy ( $\Delta H_{298}^0$  K), and entropy ( $\Delta S_{298}^0$  K) changes for the extraction of Eu<sup>3+</sup> and Am<sup>3+</sup> from 4 M HNO<sub>3</sub> into TODGA dissolved in different diluents was

studied to get better understanding of thermodynamic effect of molecular diluent on these solvent extraction processes.

## 2. Experimental

### 2.1. Organic and aqueous phase preparation

Aliphatic organic diluents (ACS grade,  $\geq 99.0\%$ ) were obtained from Sigma Aldrich and were used as supplied. TODGA ( $>99\%$  by HPLC) was obtained from Technocomm Ltd (Scotland). Organic phases for experiments were prepared volumetrically by mixing TODGA with various diluents. For the primary and secondary alcohols as well as ketones the TODGA concentration in the organic phase was 20 mmol L<sup>-1</sup>. For the alkane diluents the TODGA concentration was 2 mmol L<sup>-1</sup>. Aqueous phases were prepared by gravimetric dilution (Sartorius, 98648-018-34) of 65 volume% HNO<sub>3</sub> (puris. p.a. grade, J.T. Baker) with deionized water (18 MΩ cm at 25 °C from Milli-Q system) to 4 mol L<sup>-1</sup>. The aqueous phases were spiked with trace amounts of radioactive <sup>152</sup>Eu and <sup>241</sup>Am (approximately 10<sup>-7</sup> mol L<sup>-1</sup> and 10<sup>-8</sup> mol L<sup>-1</sup>, respectively) obtained from PSI stocks. The complete composition of extraction systems and extraction conditions studied in this work are shown in the Table 1.

### 2.2. Measurements of distribution ratios

The distribution ratios for the trace amounts of <sup>152</sup>Eu and <sup>241</sup>Am were determined by contacting 1 mL of the aqueous phase containing 4 mol L<sup>-1</sup> HNO<sub>3</sub> (as the representative HNO<sub>3</sub> concentration in the high active raffinate solution<sup>50</sup>) and europium and americium tracers with the same volume of organic phase containing TODGA dissolved in respective diluent. Contacting was done by the shaking of the organic and aqueous phases for 120 minutes in shaking machine (IKA Vibrax VXR Basic) at 1000 rpm. This time (120 min) was determined in the initial tests to be sufficient in order to reach distribution equilibrium for both europium and americium. Shaking machine was equipped with sample holder coupled with a heated circulating water bath (Julabo, F250) to maintain constant temperature. After the contacting, the samples were allowed to settle by gravity for 120 minutes. After phase separation, 500 μL and 800 μL aliquots were taken from organic and aqueous phases, respectively. Aqueous phase (800 μL) was transferred to the second vial from which a second 500 μL aliquot was taken in order to avoid cross contamination with the organic phase. The samples were kept in the temperature-controlled setup from the phase contacting stage till the first sampling of 500 μL and 800 μL aliquots for organic and aqueous phases respectively. This

**Table 1** Composition of extraction systems and extraction conditions used

| Diluent family     | Length of the carbon chain | TODGA concentration (mmol L <sup>-1</sup> ) | Temperature (K) | Nitric acid concentration (mol L <sup>-1</sup> ) |
|--------------------|----------------------------|---|-----------------|--|
| Alkanes            | 6–10                       | 1, 2, 5                                     | 288, 298, 308   | 4  |
| Primary alcohols   | 5–10                       | 5, 20, 40                                   | 288, 298, 308   | 4  |
| Secondary alcohols | 5–10                       | 5, 20, 40                                   | 288, 298, 308   | 4  |
| Secondary ketones  | 5–10                       | 5, 20, 40                                   | 288, 298, 308   | 4  |



decreases the possible experimental errors in the determination of the extraction constants that are highly temperature sensitive.

After the sampling, count-rates of  $^{152}\text{Eu}$  at 121.8 keV and  $^{241}\text{Am}$  at 59.6 keV in aqueous and organic phases were measured *via* a p-type High Purity Germanium detector (HPGe) coupled with digital spectrum analyzer. Genie 2000 software was used to analyze obtained gamma spectra. Dead time during the data acquisition was kept below 5%. The effect of density differences between the aqueous and organic phases on transmission of  $\gamma$ -rays from the samples was evaluated by EFFTRAN code<sup>51</sup> and was found to be less than 0.5% thus below the random uncertainty originating from the counting statistics. The extraction of americium and europium by pure diluent in the absence of TODGA was investigated in the screening experiments which were performed in the same manner as experiments with TODGA described above.

The distribution ratios were calculated as the ratio of equilibrium concentration of solute ( $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$ ) in the organic phase over its concentration in the aqueous phase represented by its measured radioactivity (eqn (1)).

$$D_m = \frac{[M]_{(\text{org})}}{[M]_{(\text{aq})}} = \frac{A_{M(\text{org})}}{A_{M(\text{aq})}} \quad (1)$$

The separation factors were subsequently calculated as the ratio of the distribution ratios of europium and americium as shown in eqn (2)

$$\text{SF}_{\text{Eu/Am}} = \frac{D_{\text{Eu}}}{D_{\text{Am}}} \quad (2)$$

Experiments were performed in duplicates or triplicates and the uncertainties of all data are given as one standard deviation.

It is well known that extraction of  $\text{HNO}_3$  *via* some organic phases containing TODGA occurs.<sup>33,38–41,49,52</sup> Therefore, two sets of experiments were performed – with the organic phase pre-saturated with 4 M  $\text{HNO}_3$  as well as with a non-preconditioned set of diluents. Saturation of the organic solvent (diluent and TODGA) was performed by contacting the solvent with the same volume of 4 M  $\text{HNO}_3$  by shaking machine for 60 minutes and then the phases were let to separate by gravity for 120 minutes. This procedure was performed only with polar diluents, as alkanes did not show any appreciable extraction of nitric acid thus behaving like true inert diluents.

### 2.3. Extraction of nitric acid into diluent

In order to obtain insight into the ability of the pure diluent to extract nitric acid from the aqueous solutions experiments were performed in the similar way as described in the work by Geist.<sup>53</sup> Organic diluent (25 mL) was contacted with the equal volume of water and shook for 30 minutes. Phases were separated by centrifugation and 25 mL of organic phase was then transferred and contacted with the equal volume of nitric acid solutions of varied concentration ( $0.1\text{--}4 \text{ mol L}^{-1}$ ) in shaking machine at 2000 rpm.

After subsequent centrifugation, 20 mL of the organic phase was transferred to the different vial and contacted with distilled MQ water in order to back-extract nitric acid from the organic phase. The acid concentration in the back-extracted solutions as well as in the initial aqueous solutions was determined by potentiometric titrations using Metrohm Titrino and  $0.01 \text{ mol L}^{-1}$  and  $0.1 \text{ mol L}^{-1}$  standard NaOH solutions. These experiments were performed in triplicates. The mass balance calculations showed that single contacting of the loaded organic phase with distilled water is sufficient for the complete back-extraction of  $\text{HNO}_3$  into aqueous phase.

### 2.4. Determination of the stoichiometry of the extracted species

The stoichiometry of extracted complexes with respect to average number of TODGA ligand surrounding the extracted metal was determined by the conventional slope analysis. The slope analysis was performed by the least squares linear regression of the logarithmic plots of distribution ratios against the logarithmic values of TODGA concentration in the organic phase for each diluent. As only trace amounts of  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  were used in the tests ( $10^{-7} \text{ mol L}^{-1}$  and  $10^{-8} \text{ mol L}^{-1}$ , respectively), the concentration of the free TODGA at the equilibrium was assumed to be equal to its initial value. For the calculations of apparent extraction constants, activities in the aqueous phase rather than concentrations were used. Extended Specific Ion Interaction Theory (ESIT) developed by Ciavatta<sup>54</sup> was used to compute activity coefficients of free nitrate ions in aqueous phase. According to the mechanism of Eu and Am extraction *via* TODGA (eqn (4) below), only neutral, uncharged species exist in organic phase. It can be assumed that activity coefficients of neutral species are equal to one,<sup>54</sup> therefore concentrations of  $M(\text{NO}_3)_n(\text{TODGA})_{m(\text{org})}$  were used for all computations.

In order to interpret the linear regression results following assumptions were applied:

- Tracer amounts of  $\text{Am}^{3+}$  and  $\text{Eu}^{3+}$  don't contribute to the ionic strength.
- $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  are not hydrolyzed in  $4 \text{ mol L}^{-1} \text{HNO}_3$ .<sup>55</sup>
- Activity coefficients for neutral species are equal to one.<sup>54</sup>

There is some evidence from experimental spectroscopic data (mostly Raman and Infra-Red), Nuclear Magnetic Resonance data and molecular dynamic simulations for the existence of weak  $\text{HNO}_3^0$  ion pairs in relatively concentrated aqueous solutions of nitric acid.<sup>56–61</sup> Comprehensive review of the experimental data is available<sup>62</sup> and according to this review values of  $\text{HNO}_3^0$  stability (dissociation) constants at infinite dilution ( $K_a^0$ ) vary significantly, from 10 to 40. Such a large difference in  $K_a^0$  can be explained by the problems associated with experimental or theoretical determination of stability constants of weak ion pairs and strongly indicates that uncertainty associated with this value is large.<sup>63,64</sup> In this work apparent stability constant of  $\text{HNO}_3^0$  at  $4 \text{ mol L}^{-1}$  ( $K_a$ ) and its  $1\sigma$  standard deviation was estimated based on literature data as  $25 \pm 10$ . This value is in a good agreement with most of the literature values discussed by Levanov and co-workers.<sup>62</sup> The degree



of  $\text{HNO}_3$  dissociation at  $4 \text{ mol L}^{-1}$  ( $\alpha$ ) can be calculated from estimated dissociation constant ( $K_a = 25$ ) using Ostwald dilution law and it can be shown that 88% of  $\text{HNO}_3$  is dissociated.

The assumed extraction mechanism is presented in eqn (3):<sup>30</sup>



where  $m$  (number of TODGA molecules) in the extracted specie was determined by slope analysis.

The apparent equilibrium extraction constant ( $K_{\text{ex}}$ ) for the reaction in eqn (3) is defined as:

$$K_{\text{ex}} = \frac{[\text{M}(\text{NO}_3)_3\text{TODGA}_{m(\text{org})}]}{[\gamma_{\text{M}^{n+}}\text{M}_{(\text{aq})}^{n+}][\gamma_{\text{NO}_3^-}[\text{NO}_{3(\text{aq})}^-]]^n[\text{TODGA}_{(\text{org})}]^m} \sim \frac{D_m}{\text{---}} \quad (4)$$

Activity coefficients of free nitrate in the aqueous phase were calculated with extended SIT theory according to ref. 65:

$$\log_{10} \gamma_{\text{NO}_3^-} = -z_i^2 D_H + \sum_j \varepsilon_{\text{H}^+}(i, j, I_m) + \varepsilon_{\text{NO}_3^-}(i, j, I_m) \log_{10}(I_m) m_j \quad (5)$$

where  $\varepsilon(\text{H}^+, \text{NO}_3^-) = 0.07$ .<sup>66</sup>

Thus when combined with distribution ratio (eqn (1)) the equation can be rearranged into the form of eqn (6).

$$\log D_m = m \log [\text{TODGA}_{(\text{org})}] + n \log [\gamma_{\text{NO}_3^-} \text{NO}_{3(\text{aq})}^-] + \log K_{\text{ex}} \quad (6)$$

For the polar diluents, TODGA concentration of 5, 20 and 40  $\text{mmol L}^{-1}$  were used, whereas for alkanes concentration of TODGA was 1, 2 and 5  $\text{mmol L}^{-1}$ . All the extraction experiments for stoichiometry determination were performed at  $298 \pm 0.2 \text{ K}$ . For the free nitrate concentration in the aqueous phase equilibrium values obtained from the nitric acid extraction experiments were used.

The activity coefficients of TODGA in the organic diluents taken to be equal to unity in this work. However, the transport of water, nitric acid and nitrate groups into the organic phase during the contacting could possibly lead to the binding of the free TODGA ligand. Therefore, the determined stoichiometry from the slope analysis has only limited validity within the range of tested TODGA concentrations. The uncertainties of the linear regression are presented as one standard deviation.

## 2.5. Determination of the thermodynamic parameters

Solvent extraction of  $\text{Am}^{3+}$  and  $\text{Eu}^{3+}$  via TODGA was studied at different temperatures (288 K, 298 K and 308 K). Distribution ratios determined at these temperatures were used to compute extraction constant ( $K_{\text{ex}}$ ). For the calculation of  $K_{\text{ex}}$  in different diluents the stoichiometry of  $\text{Eu}(\text{Am})\text{TODGA}$  complexes for each type of diluent derived from slope analysis presented in the Table 3 were used. Natural logarithm of  $K_{\text{ex}}$  was plotted as a function of temperature ( $T^{-1}$ ) and standard enthalpy change and the standard entropy change were derived from this plot (Van't Hoff's plot) using eqn (7). The standard change of Gibbs energy was thereafter calculated using eqn (8).

$$\ln K_{\text{ex}} = \frac{-\Delta H_R^0}{RT} + \frac{\Delta S_R^0}{R} \quad (7)$$

$$\Delta G^0 = \Delta H^0 - T\Delta S^0 \quad (8)$$

## 3. Results and discussion

### 3.1. Distribution ratios and separation factors

Experiments with pure diluents without TODGA showed that extraction of europium or americium into pure diluent doesn't occur.

The obtained distribution ratios for  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  in the different pristine diluents at  $298 \pm 0.2 \text{ K}$  are presented in Fig. 1A and B, respectively. The results for the diluents pre-saturated with acid are shown in Fig. 2A and B. As it is shown in Fig. 1A and B, and Fig. 2A and B in extraction experiments performed

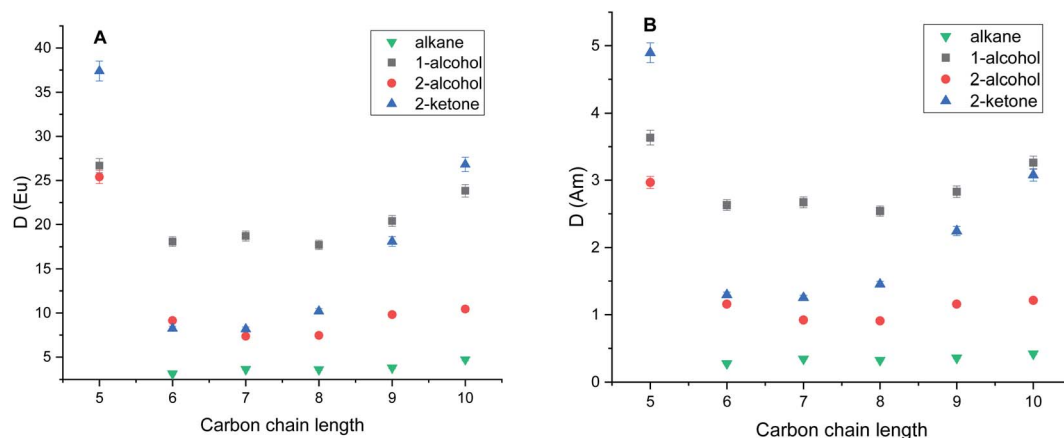


Fig. 1 Dependence of distribution ratios of  $\text{Eu}^{3+}$  (A) and  $\text{Am}^{3+}$  (B) on the diluent type and its carbon chain length in pristine solvents. The concentration of TODGA was  $20 \text{ mmol L}^{-1}$  for polar diluents and  $2 \text{ mmol L}^{-1}$  for alkanes.





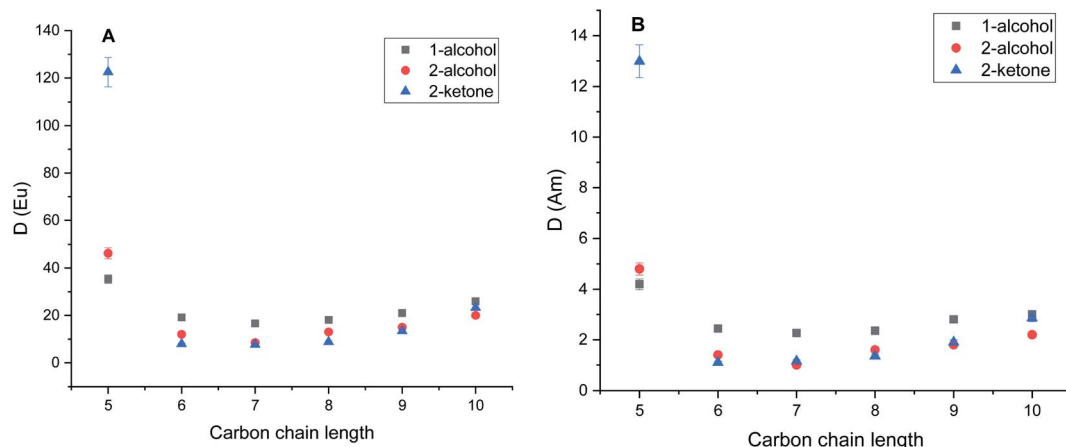


Fig. 2 Dependence of distribution ratios of  $\text{Eu}^{3+}$  (A) and  $\text{Am}^{3+}$  (B) on the diluent type and its carbon chain length in solvents, pre-saturated with  $\text{HNO}_3$ .

with TODGA dissolved in polar diluents, the distribution ratios of both europium and americium showed significant dependence on the diluent type as well as carbon chain length. This behavior was observed in both pre-conditioned as well as pristine solvents. Significant increase of the distribution ratios was observed in diluents with 5 carbon atoms in chain, regardless of the diluent type used. Concentration of TODGA in alkane diluents was kept  $2 \text{ mmol L}^{-1}$  in order to keep  $D$ -ratios below 150. In the case of alkanes, pentane was not used as diluent due to its low viscosity.

It is clear from Fig. 1A and B that the type of diluent as well as the length of the carbon chain have a substantial effect on the distribution ratio of europium and americium. Generally, the distribution ratio in polar diluents increases with the increase of the carbon chain length except for chain with 5 carbon atoms. Carbon chain length has a profound effect in the case of ketone diluents. It is note-worthy to point out on the difference between primary and secondary alcohols with respect to distribution ratios while position of the hydroxyl group further in carbon chain leads to the significant decrease of the

distribution ratio. In the case of alkane diluents, the change of the distribution ratios was insignificant with the increase of the carbon chain length. In solvents pre-saturated with nitric acid a slight increase of the distribution ratio was observed while penta-2-one showed significant increase in distribution ratios for both  $\text{Am}^{3+}$  and  $\text{Eu}^{3+}$ . The increase of distribution ratios can be addressed to the higher free nitrate concentration in the aqueous phase at the extraction equilibrium. However, the trends regarding the diluent type as well as the carbon chain were the same as in pristine solvents. The separation factors between  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  presented in the Fig. 3 show a similar behavior as the distribution ratios of Eu and Am with respect to their dependence on carbon chain length.

The observed separation factors in the secondary alcohols were higher for all carbon chain lengths when compared to primary alcohols despite aforementioned lower distribution ratios. We observed the significant increase in the separation factors in the alkane diluents when compared to the polar ones. In alkane diluents, the separation factor did not show statistically significant variations with the increase of carbon chain

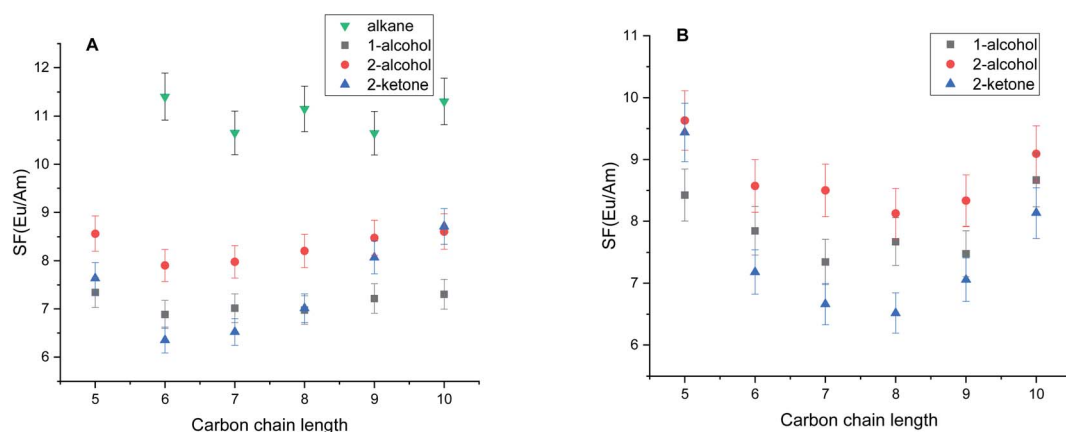


Fig. 3 The dependence of separation factors between  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  on the diluent type and its carbon chain length (A) pristine solvent (B) pre-saturated solvent. The concentration of TODGA was  $20 \text{ mmol L}^{-1}$  for polar diluents and  $2 \text{ mmol L}^{-1}$  for alkanes.



unlike in other diluent types. In solvents pre-saturated with nitric acid slight increase of separation factors for  $\text{Eu}^{3+}$  from  $\text{Am}^{3+}$  was observed in all three polar diluent families while maintaining the similar visual trend over the carbon chain length as in non-conditioned solvents.

### 3.2. Extraction of nitric acid into the diluent

The extraction of nitric acid into various diluents is shown in Fig. 4. Alkane diluent type is omitted in presented results, as this diluent type did not extract nitric acid and behaves like an inert diluent. As shown in Fig. 4, the extraction of nitric acid into organic phase always increases with its initial concentration in aqueous phase, and decreases with the carbon chain length of the diluent. The non-linear behavior (Fig. 4) could be an effect of the organic phase dielectric properties changes due to the pre-saturating of the diluent with the water before the nitric acid introduction. The water extraction by diluents was clearly visible when following the water level in graduated cylinder during contacting, however not quantified by *i.e.* Karl Fischer titrations. The data for the water absorption quantities in the pure diluents are known and available from the IUPAC compilations.<sup>67–74</sup>

Higher concentrations of nitric acid in organic phase may result in change of intermolecular interactions and thus contribute to deviation from linearity. Therefore, it cannot be

assumed that the same forces will act on the nitric acid in the case of different diluents.

While differences of acid extraction between primary and secondary alcohols are minor (if any), ketones with more than 6 carbon atoms in the alkyl chain extract significantly less nitric acid than alcohol diluents. For example the equilibrium concentration of nitric acid in the organic phase is *ca.* 11% lower for 2-heptanone when compared to 2-heptanol and 20% lower in case of 2-decanone *versus* 2-decanol. The lower concentration of nitric acid in long carbon chained ketones yielding to lower dielectric constant of the saturated diluent. This behavior might explain the increase of the distribution ratios for  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  for the longer carbon chained ketones as shown in Fig. 1. The lower extraction of nitric acid is presumably caused by the inability of longer carbon chain ketones to act as a hydrogen bonding donors. In general, the extraction of acid followed the order according to alkyl chain length  $5 > 6 > 7 > 8 > 9-10$  for all diluent types. Equilibrium concentrations of nitric acid in the aqueous phase after contacting with each diluent was determined and are listed in the Table 2.

### 3.3. Stoichiometry of the extracted species

The stoichiometry of the extracted species were determined by the slope analysis of the distribution ratios plotted against the

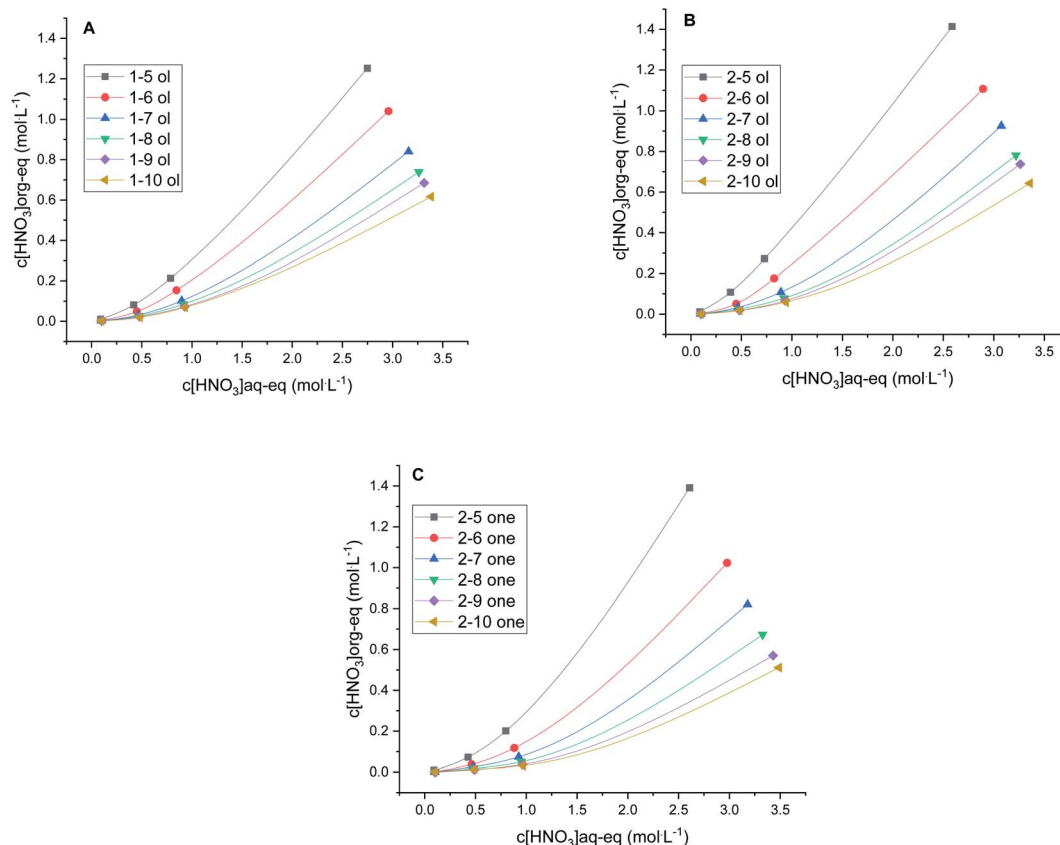


Fig. 4 Equilibrium concentrations of nitric acid in organic phase against its equilibrium concentration in the aqueous phase (A) primary alcohols, (B) secondary alcohols, (C) secondary ketones. Full lines in plots are only for the eye guidance.



**Table 2** Equilibrium concentrations of nitric acid in the aqueous phase after contacting 4 mol L<sup>-1</sup> HNO<sub>3</sub> solution with different diluents

| Diluent    | $C_{\text{(eq)}}\text{HNO}_{3\text{(aq)}} \text{ (mol L}^{-1}\text{)}$ | Diluent    | $C_{\text{(eq)}}\text{HNO}_{3\text{(aq)}} \text{ (mol L}^{-1}\text{)}$ | Diluent     | $C_{\text{(eq)}}\text{HNO}_{3\text{(aq)}} \text{ (mol L}^{-1}\text{)}$ |
|------------|--|------------|--|-------------|--|
| 1-Pentanol | 2.75 ± 0.03  | 2-Pentanol | 2.59 ± 0.03  | 2-Pentanone | 2.60 ± 0.03  |
| 1-Hexanol  | 2.96 ± 0.03  | 2-Hexanol  | 2.90 ± 0.03  | 2-Hexanone  | 2.98 ± 0.03  |
| 1-Heptanol | 3.16 ± 0.03  | 2-Heptanol | 3.09 ± 0.03  | 2-Heptanone | 3.19 ± 0.03  |
| 1-Octanol  | 3.25 ± 0.03  | 2-Octanol  | 3.22 ± 0.03  | 2-Octanone  | 3.33 ± 0.03  |
| 1-Nonanol  | 3.31 ± 0.03  | 2-Nonanol  | 3.27 ± 0.03  | 2-Nonanone  | 3.42 ± 0.03  |
| 1-Decanol  | 3.39 ± 0.03  | 2-Decanol  | 3.36 ± 0.03  | 2-Decanone  | 3.43 ± 0.03  |

TODGA concentration in the organic phase in the logarithmic scale. By this method the apparent stoichiometry of the extraction reaction was determined with respect to the TODGA molecules surrounding the extracted metal complex. The obtained results are presented in the Table 3.

The obtained data indicate that stoichiometry of extracted europium and americium complexes differ from each other in all the types of polar diluents. However, the apparent stoichiometry does not vary significantly with the change of the carbon chain length within the same diluent type. The slope analysis shows that Eu<sup>3+</sup> is extracted predominantly as 1 : 3 complex whereas Am<sup>3+</sup> as a mix of 1 : 2 and 1 : 3 complexes in the polar diluents. The determined stoichiometry in alkane diluents indicates extraction of 1 : 3 and 1 : 4 complexes within the presented concentration range of TODGA for both Eu<sup>3+</sup> and Am<sup>3+</sup>. In general, the observed values are consistent with the previously reported stoichiometries of extracted complexes of An<sup>3+</sup> and Ln<sup>3+</sup> with diglycolamides.<sup>38,45,75–78</sup> It is noteworthy that 1 : 4 coordination, although observed also in other works<sup>30,38,79</sup> is not possible within the first solvation shell of Eu<sup>3+</sup> and Am<sup>3+</sup> due to geometrical hindering.<sup>80</sup> As spectroscopic methods *i.e.* Time Resolved Laser Fluorescence Spectroscopy (TRLFS) target the inner coordination sphere of the extracted ion the outer sphere coordination remains unresolved. One can therefore speculate about the explanation of the observed effect due to additional complexation by TODGA molecule in the second

solvation shell<sup>81</sup> or as the consequence of TODGA aggregation into the form of micelles.<sup>82</sup>

### 3.4. Thermodynamic parameters

The extraction of europium as well as of americium was exothermic in all tested diluents. In alkane diluents, the decrease of distribution ratios with increasing temperature was the steepest. This behavior is in agreement with previously reported results.<sup>44,75</sup> The derived thermodynamic parameters for the extraction of Eu<sup>3+</sup> and Am<sup>3+</sup> from 4 mol L<sup>-1</sup> HNO<sub>3</sub> by TODGA dissolved in various diluents are shown in Tables 4 and 5. The values of nitrate concentrations listed in Table 2 were used to calculate activity coefficients of free nitrate using extended SIT. In general, the observed values show similar behavior as in the previously published studies mainly with respect to exothermic behavior and negative entropy change values.<sup>75,83,84</sup> From the derived thermodynamic parameters, the Gibbs energy change ( $-\Delta G^0$ ) follows the order alkanes  $\gg$  primary alcohols  $\approx$  secondary alcohols  $\approx$  ketones. However the change of enthalpy of extractions shows difference between primary or secondary alcohols and ketones, where the latter show smaller exothermic nature of extraction. This also leads to the different ( $\Delta H^0/\Delta S^0$ ) ratios for each diluent family probably according to the disturbances in the structure of diluents during the extraction process. This explanation is feasible when taking in account more ordered structure of alcohol diluents

**Table 3** Values of slopes from log–log plots of the extraction of Eu<sup>3+</sup> and Am<sup>3+</sup> from 4 M HNO<sub>3</sub> by TODGA in various organic diluents. Uncertainties are given as two standard deviations. Pearson's *R* was >0.99 for all performed regressions

| Diluent    | Eu <sup>3+</sup> : TODGA | Am <sup>3+</sup> : TODGA | Diluent     | Eu <sup>3+</sup> : TODGA | Am <sup>3+</sup> : TODGA |
|------------|--------------------------|--------------------------|-------------|--------------------------|--------------------------|
| Hexane     | 3.40 ± 0.05              | 3.40 ± 0.05              | 2-Pentanol  | 2.82 ± 0.02              | 2.46 ± 0.02              |
| Heptane    | 3.7 ± 0.1                | 3.7 ± 0.1                | 2-Hexanol   | 2.81 ± 0.02              | 2.43 ± 0.02              |
| Octane     | 3.7 ± 0.1                | 3.7 ± 0.1                | 2-Heptanol  | 2.80 ± 0.02              | 2.44 ± 0.03              |
| Nonane     | 3.5 ± 0.1                | 3.4 ± 0.1                | 2-Octanol   | 2.80 ± 0.01              | 2.44 ± 0.04              |
| Decane     | 3.3 ± 0.1                | 3.3 ± 0.1                | 2-Nonanol   | 2.83 ± 0.05              | 2.46 ± 0.02              |
|            |                          |                          | 2-Decanol   | 2.82 ± 0.03              | 2.53 ± 0.03              |
| Diluent    | Eu <sup>3+</sup> : TODGA | Am <sup>3+</sup> : TODGA | Diluent     | Eu <sup>3+</sup> : TODGA | Am <sup>3+</sup> : TODGA |
| 1-Pentanol | 2.80 ± 0.01              | 2.35 ± 0.03              | 2-Pentanone | 2.84 ± 0.01              | 2.40 ± 0.05              |
| 1-Hexanol  | 2.74 ± 0.01              | 2.28 ± 0.02              | 2-Hexanone  | 2.84 ± 0.09              | 2.40 ± 0.05              |
| 1-Heptanol | 2.74 ± 0.005             | 2.32 ± 0.02              | 2-Heptanone | 2.90 ± 0.05              | 2.40 ± 0.05              |
| 1-Octanol  | 2.74 ± 0.005             | 2.25 ± 0.02              | 2-Octanone  | 3.00 ± 0.05              | 2.50 ± 0.05              |
| 1-Nonanol  | 2.77 ± 0.01              | 2.31 ± 0.02              | 2-Nonanone  | 3.00 ± 0.02              | 2.50 ± 0.05              |
| 1-Decanol  | 2.86 ± 0.01              | 2.33 ± 0.02              | 2-Decanone  | 3.00 ± 0.03              | 2.50 ± 0.05              |





**Table 4** Standard molar Gibbs energy  $\Delta G_{298\text{ K}}^0$ , enthalpy  $\Delta H_{298\text{ K}}^0$ , and entropy  $\Delta S_{298\text{ K}}^0$  changes and natural logarithm of apparent extraction constants for the extraction of  $\text{Eu}^{3+}$  in tested systems. In polar diluents, concentration of TODGA was 20 mmol  $\text{L}^{-1}$ , whereas in alkanes 2 mmol  $\text{L}^{-1}$  concentration of TODGA was used

| Diluent     | $\ln K_{\text{ex}298\text{ K}}$ | $\Delta G_{298\text{ K}}^0$ (kJ $\text{mol}^{-1}$ ) | $\Delta H_{298\text{ K}}^0$ (kJ $\text{mol}^{-1}$ ) | $\Delta S_{298\text{ K}}^0$ [J (mol K) $^{-1}$ ] |
|-------------|---------------------------------|---|---|--|
| 1-Pentanol  | 11.6 $\pm$ 0.5                  | −28.6 $\pm$ 2.0                                     | −41.8 $\pm$ 2.1                                     | −44.2 $\pm$ 2.2                                  |
| 1-Hexanol   | 10.6 $\pm$ 0.4                  | −26.3 $\pm$ 1.9                                     | −40.4 $\pm$ 2.0                                     | −47.3 $\pm$ 2.4                                  |
| 1-Heptanol  | 10.4 $\pm$ 0.4                  | −25.7 $\pm$ 1.8                                     | −40.2 $\pm$ 2.0                                     | −48.4 $\pm$ 2.4                                  |
| 1-Octanol   | 10.2 $\pm$ 0.4                  | −25.3 $\pm$ 1.8                                     | −46.6 $\pm$ 2.3                                     | −71.5 $\pm$ 3.6                                  |
| 1-Nonanol   | 10.4 $\pm$ 0.4                  | −25.7 $\pm$ 1.8                                     | −45.7 $\pm$ 2.3                                     | −67.2 $\pm$ 3.4                                  |
| 1-Decanol   | 10.6 $\pm$ 0.4                  | −26.3 $\pm$ 1.9                                     | −43.2 $\pm$ 2.2                                     | −56.9 $\pm$ 2.8                                  |
| 2-Pentanol  | 11.8 $\pm$ 0.5                  | −29.3 $\pm$ 2.1                                     | −46.4 $\pm$ 2.3                                     | −57.4 $\pm$ 2.9                                  |
| 2-Hexanol   | 10.3 $\pm$ 0.4                  | −25.5 $\pm$ 1.8                                     | −40.5 $\pm$ 2.0                                     | −50.3 $\pm$ 2.5                                  |
| 2-Heptanol  | 9.7 $\pm$ 0.4                   | −24.2 $\pm$ 1.7                                     | −41.4 $\pm$ 2.1                                     | −57.8 $\pm$ 2.9                                  |
| 2-Octanol   | 9.6 $\pm$ 0.4                   | −23.8 $\pm$ 1.7                                     | −42.3 $\pm$ 2.1                                     | −62.3 $\pm$ 3.1                                  |
| 2-Nonanol   | 9.9 $\pm$ 0.4                   | −24.6 $\pm$ 1.7                                     | −36.4 $\pm$ 1.8                                     | −39.5 $\pm$ 2.0                                  |
| 2-Decanol   | 10.0 $\pm$ 0.4                  | −24.8 $\pm$ 1.8                                     | −40.0 $\pm$ 2.0                                     | −51.1 $\pm$ 2.6                                  |
| 2-Pentanone | 12.3 $\pm$ 0.5                  | −30.4 $\pm$ 2.1                                     | −46.3 $\pm$ 2.3                                     | −53.4 $\pm$ 2.7                                  |
| 2-Hexanone  | 10.2 $\pm$ 0.4                  | −25.3 $\pm$ 1.8                                     | −28.4 $\pm$ 1.4                                     | −10.4 $\pm$ 0.5                                  |
| 2-Heptanone | 10.2 $\pm$ 0.4                  | −25.2 $\pm$ 1.8                                     | −30.1 $\pm$ 1.5                                     | −16.5 $\pm$ 0.8                                  |
| 2-Octanone  | 10.6 $\pm$ 0.4                  | −26.2 $\pm$ 1.9                                     | −23.1 $\pm$ 0.12                                    | 10.3 $\pm$ 0.5                                   |
| 2-Nonanone  | 11.0 $\pm$ 0.                   | −27.3 $\pm$ 1.9                                     | −29.5 $\pm$ 1.5                                     | −7.3 $\pm$ 0.4                                   |
| 2-Decanone  | 11.4 $\pm$ 0.5                  | −28.2 $\pm$ 2.0                                     | −32.9 $\pm$ 1.6                                     | −15.6 $\pm$ 0.8                                  |
| Hexane      | 18.2 $\pm$ 0.7                  | −45.0 $\pm$ 3.2                                     | −126.7 $\pm$ 6.3                                    | −273.9 $\pm$ 13.7                                |
| Heptane     | 19.5 $\pm$ 0.8                  | −48.4 $\pm$ 3.4                                     | −124.4 $\pm$ 6.2                                    | −255.0 $\pm$ 12.8                                |
| Octane      | 19.2 $\pm$ 0.8                  | −47.7 $\pm$ 3.4                                     | −125.1 $\pm$ 6.3                                    | −260.0 $\pm$ 13.0                                |
| Nonane      | 19.4 $\pm$ 0.8                  | −48.1 $\pm$ 3.4                                     | −124.2 $\pm$ 6.2                                    | −255.3 $\pm$ 12.8                                |
| Decane      | 18.8 $\pm$ 0.8                  | −46.7 $\pm$ 3.3                                     | −120.3 $\pm$ 6.0                                    | −247.2 $\pm$ 12.4                                |

**Table 5** Standard molar Gibbs energy  $\Delta G_{298\text{ K}}^0$ , enthalpy  $\Delta H_{298\text{ K}}^0$ , and entropy  $\Delta S_{298\text{ K}}^0$  changes and natural logarithm of apparent extraction constants for the extraction of  $\text{Am}^{3+}$  in tested systems. In polar diluents, concentration of TODGA was 20 mmol  $\text{L}^{-1}$ , whereas in alkanes 2 mmol  $\text{L}^{-1}$  concentration of TODGA was used

| Diluent     | $\ln K_{\text{ex}298\text{ K}}$ | $\Delta G_{298\text{ K}}^0$ (kJ $\text{mol}^{-1}$ ) | $\Delta H_{298\text{ K}}^0$ (kJ $\text{mol}^{-1}$ ) | $\Delta S_{298\text{ K}}^0$ [J (mol K) $^{-1}$ ] |
|-------------|---------------------------------|---|---|--|
| 1-Pentanol  | 7.8 $\pm$ 0.3                   | −19.3 $\pm$ 1.4                                     | −31.6 $\pm$ 1.6                                     | −41.3 $\pm$ 2.1                                  |
| 1-Hexanol   | 6.9 $\pm$ 0.3                   | −17.1 $\pm$ 1.2                                     | −30.5 $\pm$ 1.5                                     | −45.1 $\pm$ 2.3                                  |
| 1-Heptanol  | 6.8 $\pm$ 0.3                   | −16.8 $\pm$ 1.2                                     | −29.4 $\pm$ 1.5                                     | −42.3 $\pm$ 2.1                                  |
| 1-Octanol   | 6.4 $\pm$ 0.3                   | −15.8 $\pm$ 1.1                                     | −34.7 $\pm$ 1.7                                     | −63.7 $\pm$ 3.2                                  |
| 1-Nonanol   | 6.6 $\pm$ 0.3                   | −16.4 $\pm$ 1.2                                     | −34.6 $\pm$ 1.7                                     | −61.1 $\pm$ 3.1                                  |
| 1-Decanol   | 6.7 $\pm$ 0.3                   | −16.6 $\pm$ 1.2                                     | −34.5 $\pm$ 1.7                                     | −60.0 $\pm$ 3.0                                  |
| 2-Pentanol  | 8.3 $\pm$ 0.3                   | −20.5 $\pm$ 1.4                                     | −35.1 $\pm$ 1.8                                     | −49.2 $\pm$ 2.5                                  |
| 2-Hexanol   | 6.7 $\pm$ 0.3                   | −16.7 $\pm$ 1.2                                     | −27.2 $\pm$ 1.4                                     | −35.3 $\pm$ 1.8                                  |
| 2-Heptanol  | 6.3 $\pm$ 0.3                   | −15.5 $\pm$ 1.1                                     | −28.8 $\pm$ 1.4                                     | −44.6 $\pm$ 2.2                                  |
| 2-Octanol   | 6.1 $\pm$ 0.2                   | −15.0 $\pm$ 1.1                                     | −29.7 $\pm$ 1.5                                     | −49.1 $\pm$ 2.5                                  |
| 2-Nonanol   | 6.4 $\pm$ 0.3                   | −15.8 $\pm$ 1.1                                     | −24.2 $\pm$ 1.2                                     | −28.3 $\pm$ 1.4                                  |
| 2-Decanol   | 6.6 $\pm$ 0.3                   | −16.2 $\pm$ 1.1                                     | −22.3 $\pm$ 1.1                                     | −20.4 $\pm$ 1.0                                  |
| 2-Pentanone | 8.6 $\pm$ 0.3                   | −21.2 $\pm$ 1.5                                     | −35.8 $\pm$ 1.8                                     | −48.7 $\pm$ 2.4                                  |
| 2-Hexanone  | 6.5 $\pm$ 0.3                   | −16.1 $\pm$ 1.1                                     | −16.7 $\pm$ 0.8                                     | −1.9 $\pm$ 0.1                                   |
| 2-Heptanone | 6.3 $\pm$ 0.3                   | −15.7 $\pm$ 1.1                                     | −18.8 $\pm$ 0.9                                     | −10.5 $\pm$ 0.5                                  |
| 2-Octanone  | 6.8 $\pm$ 0.3                   | −16.7 $\pm$ 1.2                                     | −13.2 $\pm$ 0.7                                     | 12.0 $\pm$ 0.6                                   |
| 2-Nonanone  | 7.2 $\pm$ 0.3                   | −17.7 $\pm$ 1.3                                     | −18.1 $\pm$ 0.9                                     | −1.2 $\pm$ 0.1                                   |
| 2-Decanone  | 7.2 $\pm$ 0.3                   | −17.8 $\pm$ 1.3                                     | −23.7 $\pm$ 1.2                                     | −19.8 $\pm$ 1                                    |
| Hexane      | 15.5 $\pm$ 0.6                  | −38.5 $\pm$ 2.7                                     | −121.1 $\pm$ 6.1                                    | −277.4 $\pm$ 13.9                                |
| Heptane     | 16.6 $\pm$ 0.7                  | −41.0 $\pm$ 2.9                                     | −114.7 $\pm$ 5.7                                    | −247.2 $\pm$ 12.4                                |
| Octane      | 16.8 $\pm$ 0.7                  | −41.6 $\pm$ 2.9                                     | −116.8 $\pm$ 5.8                                    | −252.2 $\pm$ 12.6                                |
| Nonane      | 16.8 $\pm$ 0.7                  | −41.7 $\pm$ 3.0                                     | −118.5 $\pm$ 5.9                                    | −257.5 $\pm$ 12.9                                |
| Decane      | 15.7 $\pm$ 0.6                  | −39.0 $\pm$ 3.0                                     | −112.4 $\pm$ 5.6                                    | −246.4 $\pm$ 12.3                                |

when compared to ketones, due to the ability alcohols to form hydrogen bonds within the diluent.

## 4. Conclusions

The performed studies indicate that diluent plays significant role in the solvent extraction of  $\text{Eu}^{3+}$  and  $\text{Am}^{3+}$  with TODGA as



an extracting agent. Examinations of the effect of carbon chain length revealed that carbon chain length has significant impact on the extraction outcome in the polar diluents. Diluents with 5 carbon atoms in aliphatic chain showed higher distribution ratios as well as separation factors than longer chained homologues, leading to the concave shaped distribution ratios dependence on the carbon chain length. However, the extraction behavior in 5 carbon chain diluents could not be reasonably explained. It was shown that the diluents apart from alkanes extract a significant amount of nitric acid during the contacting with aqueous phase. This in conjunction with water absorption will lead to significant changes of the dielectric constant organic phase and the electrical forces affecting the solubility of the extracted species in the organic phase. The determined *D*-values and separation factors correlate with the amount of extracted HNO<sub>3</sub> and water into the organic phase for diluents with carbon chain C6–C10. However, this correlation is not straightforward between the different diluent types as well as for C5 diluents which could mean that more than one phenomenon might take place.

Extraction process for both Eu<sup>3+</sup> and Am<sup>3+</sup> with TODGA is enthalpy driven in all studied diluent types. Performed studies suggest that in the alkanes extractions behave significantly more exothermic than in the other diluents. Moreover, in the case of alkanes, both distribution ratios as well as separation factors are significantly higher than in any other type of diluents.

The stoichiometry investigation indicates that at least three different metal complexes are extracted into the organic phase dependable on the used diluent. The average ligand number of TODGA molecules in the extracted complex was typically lower for Am<sup>3+</sup> when compared with Eu<sup>3+</sup> except for alkane diluents.

## Author contributions

I. K.: conceptualization, resources, methodology, formal analysis, investigation, visualization, writing – original draft, writing – review & editing. M. F.: methodology, investigation, writing – review & editing. C. E.: formal analysis, writing – review & editing. A. V. M. methodology, formal analysis, investigation, writing – original draft, writing – review & editing.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors are grateful to Dr Mikhail S. Tyumentsev and Dr Robert Eichler for valuable scientific discussion which helped to improve this work. The work was funded by Swissnuclear grant WIR-2 (LRC\_20\_02).

## References

- 1 Y. A. El-Nadi, Solvent Extraction and Its Applications on Ore Processing and Recovery of Metals: Classical Approach, *Sep. Purif. Rev.*, 2017, **46**(3), 195–215.
- 2 M. Petranikova, I. Herdzik-Koniecko, B.-M. Steenari and C. Ekberg, Hydrometallurgical processes for recovery of valuable and critical metals from spent car NiMH batteries optimized in a pilot plant scale, *Hydrometallurgy*, 2017, **171**, 128–141.
- 3 J. C. M. M. C. G. R. Rydberg, *Solvent Extraction Principles and Practice, Revised and Expanded*, CRC Press, Boca Raton, 2004.
- 4 K. Binnemans, P. T. Jones, B. Blanpain, T. Van Gerven, Y. Yang, A. Walton and M. Buchert, Recycling of rare earths: a critical review, *J. Cleaner Prod.*, 2013, **51**, 1–22.
- 5 A. D. McNaught and AWUPAC, *Compendium of Chemical Terminology: the Gold Book*, ed. S. J. Chalk, Blackwell Scientific Publications, Oxford, 2nd edn, 1997.
- 6 N. B. Devi and B. Nayak, Liquid–liquid extraction and separation of copper(II) and nickel(II) using LIX®984N, *J. South. Afr. Inst. Min. Metall.*, 2014, **114**, 937–943.
- 7 D. Dyrssen and L. D. Hay, Solvent extraction of <sup>152,154</sup>Eu and <sup>241</sup>Am by Di-*n*-butyl Phosphate (DBP) in Different Organic Solvents, *Acta Chem. Scand.*, 1960, **14**, 1100–1111.
- 8 T. V. Healy, Synergism in the solvent extraction of di-, tri- and tetravalent metal ions—II: Synergic effects in so-called inert diluents, *J. Inorg. Nucl. Chem.*, 1961, **19**(3), 328–339.
- 9 R. K. Jyothi, H.-R. Kim, J. S. Kim, K.-W. Chung and J.-Y. Lee, Diluents Role in Extraction and Possible Separation of Light Rare Earth Elements from Chloride Solutions by using Cyanex®272 used as an Extractant, *Korean J. Met. Mater.*, 2018, **56**(10), 763–771.
- 10 A. S. Kertes and F. Grauer, Thermodynamics of solvent extraction processes: Effect of diluent on the enthalpy of formation of tri-*n*-octylammonium chloride, *J. Inorg. Nucl. Chem.*, 1978, **40**(10), 1781–1782.
- 11 E. Löfström-Engdahl, E. Aneheim, C. Ekberg, M. Foreman, J. Halleröd and G. Skarnemark, Extraction thermodynamics of Am(III) and Eu(III) using CyMe4-BTBP in various organic diluents, *J. Chem. Thermodyn.*, 2014, **76**, 64–69.
- 12 E. Löfström-Engdahl, E. Aneheim, C. Ekberg and G. Skarnemark, A reinterpretation of C5-BTBP extraction data, performed in various alcohols, *J. Radioanal. Nucl. Chem.*, 2013, **296**(2), 733–737.
- 13 K. Rezaei and H. Nedjate, Diluent effect on the distribution ratio and separation factor of Ni(II) in the liquid–liquid extraction from aqueous acidic solutions using dibutylthiophosphoric acid, *Hydrometallurgy*, 2003, **68**(1), 11–21.
- 14 G. M. Ritcey, Solvent Extraction in Hydrometallurgy: Present and Future, *Tsinghua Sci. Technol.*, 2006, **11**(2), 137–152.
- 15 V. S. Shmidt and K. A. Rybakov, Predicting the effect of the nature of diluents on extraction equilibria, *Soviet At. Energy*, 1981, **50**(6), 365–371.



- 16 M. Taube, The influence of diluent polarity on the extraction of neptunium and uranium compounds to organic media, *J. Inorg. Nucl. Chem.*, 1960, **15**(1), 171–176.
- 17 J. H. Hildebrand, *Solubility*, American Chemical Society, New York, Monograph Series, 2nd edn, 1936.
- 18 J. H. Hildebrand, J. M. Prausnitz and R. L. Scott, *Regular and related solutions: the solubility of gases, liquids, and solids*, Van Nostrand Reinhold Co., 1970.
- 19 C. Hansen, *Hansen Solubility Parameters*, CRC Press, 2007.
- 20 T. Lécivain, A. Kimberlin, D. E. Dodd, S. Miller, I. Hobbs, E. Campbell, F. Heller, J. Lapka, M. Huber and K. L. Nash, The Effect of Organic Diluent on the Extraction of Eu(III) by HEH[EHP], *Solvent Extr. Ion Exch.*, 2019, **37**(3–4), 284–296.
- 21 M. Nilsson, S. Andersson, F. Drouet, C. Ekberg, M. Foreman, M. Hudson, J. O. Liljenzin, D. Magnusson and G. Skarnemark, Extraction Properties of 6,6'-Bis-(5,6-dipentyl-[1,2,4]triazin-3-yl)-[2,2']bipyridinyl (C5-BTBP), *Solvent Extr. Ion Exch.*, 2006, **24**(3), 299–318.
- 22 A. Wilden, P. M. Kowalski, L. Klawns, B. Kraus, F. Kreft, G. Modolo, Y. Li, J. Rothe, K. Dardenne, A. Geist, A. Leoncini, J. Huskens and W. Verboom, Unprecedented Inversion of Selectivity and Extraordinary Difference in the Complexation of Trivalent f Elements by Diastereomers of a Methylated Diglycolamide, *Chem.-Eur. J.*, 2019, **25**(21), 5507–5513.
- 23 A. Wilden, G. Modolo, S. Lange, F. Sadowski, B. B. Beele, A. Skerencak-Frech, P. J. Panak, M. Iqbal, W. Verboom, A. Geist and D. Bosbach, Modified Diglycolamides for the An(III) + Ln(III) Co-separation: Evaluation by Solvent Extraction and Time-Resolved Laser Fluorescence Spectroscopy, *Solvent Extr. Ion Exch.*, 2014, **32**(2), 119–137.
- 24 P. Zsabka, K. Van Hecke, L. Adriaensen, A. Wilden, G. Modolo, M. Verwerft, K. Binnemans and T. Cardinaels, Solvent Extraction of Am(III), Cm(III), and Ln(III) Ions from Simulated Highly Active Raffinate Solutions by TODGA Diluted in Aliquat-336 Nitrate Ionic Liquid, *Solvent Extr. Ion Exch.*, 2018, **36**(6), 519–541.
- 25 G. Modolo, A. Wilden, A. Geist, D. Magnusson and R. Malmbeck, A review of the demonstration of innovative solvent extraction processes for the recovery of trivalent minor actinides from PUREX raffinate, *Radiochim. Acta*, 2012, **715**.
- 26 V. Ostapenko, A. Vasiliev, E. Lapshina, S. Ermolaev, R. Aliev, Y. Totskiy, B. Zhuikov and S. Kalmykov, Extraction chromatographic behavior of actinium and REE on DGA, Ln and TRU resins in nitric acid solutions, *J. Radioanal. Nucl. Chem.*, 2015, **306**(3), 707–711.
- 27 V. Radchenko, T. Mastren, C. A. L. Meyer, A. S. Ivanov, V. S. Bryantsev, R. Copping, D. Denton, J. W. Engle, J. R. Griswold, K. Murphy, J. J. Wilson, A. Owens, L. Wyant, E. R. Birnbaum, J. Fitzsimmons, D. Medvedev, C. S. Cutler, L. F. Mausner, M. F. Nortier, K. D. John, S. Mirzadeh and M. E. Fassbender, Radiometric evaluation of diglycolamide resins for the chromatographic separation of actinium from fission product lanthanides, *Talanta*, 2017, **175**, 318–324.
- 28 A. K. H. Robertson, B. L. McNeil, H. Yang, D. Gendron, R. Perron, V. Radchenko, S. Zeisler, P. Causey and P. Schaffer,  $^{232}\text{Th}$ -Spallation-Produced  $^{225}\text{Ac}$  with Reduced  $^{227}\text{Ac}$  Content, *Inorg. Chem.*, 2020, **59**(17), 12156–12165.
- 29 B. Zielinska, C. Apostolidis, F. Bruchertseifer and A. Morgenstern, An Improved Method for the Production of Ac-225/Bi-213 from Th-229 for Targeted Alpha Therapy, *Solvent Extr. Ion Exch.*, 2007, **25**(3), 339–349.
- 30 Y. Sasaki, Y. Sugo, S. Suzuki and S. Tachimori, The novel extractants, diglycolamides, for the extraction of lanthanides and actinides in  $\text{HNO}_3$ -*n*-dodecane system, *Solvent Extr. Ion Exch.*, 2001, **19**(1), 91–103.
- 31 Z.-X. Zhu, Y. Sasaki, H. Suzuki, S. Suzuki and T. Kimura, Cumulative study on solvent extraction of elements by *N,N,N',N'*-tetraoctyl-3-oxapentanediamide (TODGA) from nitric acid into *n*-dodecane, *Anal. Chim. Acta*, 2004, **527**(2), 163–168.
- 32 S. A. Ansari, P. Pathak, P. K. Mohapatra and V. K. Manchanda, Chemistry of Diglycolamides: Promising Extractants for Actinide Partitioning, *Chem. Rev.*, 2012, **112**(3), 1751–1772.
- 33 K. Bell, A. Geist, F. McLachlan, G. Modolo, R. Taylor and A. Wilden, Nitric Acid Extraction into TODGA, *Procedia Chem.*, 2012, **7**, 152–159.
- 34 G. Modolo, H. Asp, H. Vijgen, R. Malmbeck, D. Magnusson and C. Sorel, Demonstration of a TODGA-Based Continuous Counter-Current Extraction Process for the Partitioning of Actinides from a Simulated PUREX Raffinate, Part II: Centrifugal Contactor Runs, *Solvent Extr. Ion Exch.*, 2008, **26**(1), 62–76.
- 35 A. Bhattacharyya, R. J. M. Egberink, P. K. Mohapatra, P. K. Verma, A. S. Kanekar, A. K. Yadav, S. N. Jha, D. Bhattacharyya, J. Huskens and W. Verboom, Remarkable Enhancement in Extraction of Trivalent f-Block Elements Using a Macrocyclic Ligand with Four Diglycolamide Arms: Synthesis, Extraction, and Spectroscopic and Density Functional Theory Studies, *Inorg. Chem.*, 2019, **58**(21), 14885–14899.
- 36 Y. Pan and C. L. Hussey, Electrochemical and Spectroscopic Investigation of  $\text{Ln}^{3+}$  ( $\text{Ln} = \text{Sm}, \text{Eu}, \text{and Yb}$ ) Solvation in Bis(trifluoromethylsulfonyl)imide-Based Ionic Liquids and Coordination by *N,N,N',N'*-Tetraoctyl-3-oxa-pentane Diamide (TODGA) and Chloride, *Inorg. Chem.*, 2013, **52**(6), 3241–3252.
- 37 A. N. Turanov, V. K. Karandashev, M. Boltoeva, C. Gaillard and V. Mazan, Synergistic extraction of uranium(VI) with TODGA and hydrophobic ionic liquid mixtures into molecular diluent, *Sep. Purif. Technol.*, 2016, **164**, 97–106.
- 38 P. Weßling, U. Müllich, E. Guerinoni, A. Geist and P. J. Panak, Solvent extraction of An(III) and Ln(III) using TODGA in aromatic diluents to suppress third phase formation, *Hydrometallurgy*, 2020, **192**, 105248.
- 39 E. L. Campbell, V. E. Holfeltz, G. B. Hall, K. L. Nash, G. J. Lumetta and T. G. Levitskaia, Nitric Acid and Water Extraction by T2EHDGA in *n*-Dodecane, *Solvent Extr. Ion Exch.*, 2017, **35**(7), 586–603.



- 40 D. Woodhead, F. McLachlan, R. Taylor, U. Müllich, A. Geist, A. Wilden and G. Modolo, Nitric Acid Extraction into a TODGA Solvent Modified with 1-Octanol, *Solvent Extr. Ion Exch.*, 2019, **37**(2), 173–190.
- 41 F. McLachlan, K. Greenough, A. Geist, B. McLuckie, G. Modolo, A. Wilden and R. Taylor, Nitric Acid Extraction into the TODGA/TBP Solvent, *Solvent Extr. Ion Exch.*, 2016, **34**(4), 334–346.
- 42 M. Sypula, A. Ouadi, C. Gaillard and I. Billard, Kinetics of metal extraction in ionic liquids:  $\text{Eu}^{3+}/\text{HNO}_3//\text{TODGA}/[\text{C1C4im}][\text{Tf}_2\text{N}]$  as a case study, *RSC Adv.*, 2013, **3**(27), 10736–10744.
- 43 Y. Sasaki, P. Rapold, M. Arisaka, M. Hirata, T. Kimura, C. Hill and G. Cote, An Additional Insight into the Correlation between the Distribution Ratios and the Aqueous Acidity of the TODGA System, *Solvent Extr. Ion Exch.*, 2007, **25**(2), 187–204.
- 44 S. A. Ansari, P. N. Pathak, M. Husain, A. K. Prasad, V. S. Parmar and V. K. Manchanda, Extraction of actinides using  $N,N,N',N'$ -tetraoctyl diglycolamide (TODGA): a thermodynamic study, *Radiochim. Acta*, 2006, 307.
- 45 P. N. Pathak, S. A. Ansari, S. V. Godbole, A. R. Dhobale and V. K. Manchanda, Interaction of  $\text{Eu}^{3+}$  with  $N,N,N',N'$ -tetraoctyl diglycolamide: A time resolved luminescence spectroscopy study, *Spectrochim. Acta, Part A*, 2009, **73**(2), 348–352.
- 46 M. Boltoeva, C. Gaillard, S. Georg, V. K. Karandashev and A. N. Turanov, Speciation of uranium(VI) extracted from acidic nitrate media by TODGA into molecular and ionic solvents, *Sep. Purif. Technol.*, 2018, **203**, 11–19.
- 47 S. Panja, P. K. Mohapatra, S. C. Tripathi, P. M. Gandhi and P. Janardan, A highly efficient solvent system containing TODGA in room temperature ionic liquids for actinide extraction, *Sep. Purif. Technol.*, 2012, **96**, 289–295.
- 48 Y. Sasaki, Y. Sugo, K. Morita and K. L. Nash, The Effect of Alkyl Substituents on Actinide and Lanthanide Extraction by Diglycolamide Compounds, *Solvent Extr. Ion Exch.*, 2015, **33**(7), 625–641.
- 49 S. A. Ansari, P. N. Pathak, V. K. Manchanda, M. Husain, A. K. Prasad and V. S. Parmar,  $N,N,N',N'$ -Tetraoctyl Diglycolamide (TODGA): A Promising Extractant for Actinide-Partitioning from High-Level Waste (HLW), *Solvent Extr. Ion Exch.*, 2005, **23**(4), 463–479.
- 50 M. Sypula, Innovative SANEX process for trivalent actinides separation from PUREX raffinate, in *Schriften des Forschungszentrums Jülich Reihe Energie & Umwelt/Energy & Environment*, RWTH Aachen, Jülich, 2014, p. 220.
- 51 T. Vidmar, EFFTRAN—A Monte Carlo efficiency transfer code for gamma-ray spectrometry, *Nucl. Instrum. Methods Phys. Res., Sect. A*, 2005, **550**(3), 603–608.
- 52 Y. Xu, Y. Gao, Y. Zhou, C. Fan, H. Hou and M. Zhang, Extraction behavior of strontium from nitric acid medium with  $N,N'$ -dimethyl- $N,N'$ -dioctyldiglycolamide, *Solvent Extr. Ion Exch.*, 2017, **35**(7), 507–518.
- 53 A. Geist, Extraction of Nitric Acid into Alcohol: Kerosene Mixtures, *Solvent Extr. Ion Exch.*, 2010, **28**(5), 596–607.
- 54 *Chemical thermodynamics of americium. Chemical thermodynamics*, ed. R. J. Silva, Amsterdam, Elsevier, 1995, vol. 2.
- 55 P. L. Brown and C. Ekberg, *Hydrolysis of Metal Ions*, Wiley, 2016, p. 952.
- 56 S. Hlushak, J. P. Simonin, S. De Sio, O. Bernard, A. Ruas, P. Pochon, S. Jan and P. Moisy, Speciation in aqueous solutions of nitric acid, *Dalton Trans.*, 2013, **42**(8), 2853–2860.
- 57 N. H. C. Lewis, J. A. Fournier, W. B. Carpenter and A. Tokmakoff, Direct Observation of Ion Pairing in Aqueous Nitric Acid Using 2D Infrared Spectroscopy, *J. Phys. Chem. B*, 2019, **123**(1), 225–238.
- 58 J. M. Anglada, M. T. C. Martins-Costa, J. S. Francisco and M. F. Ruiz-López, Reactivity of Undissociated Molecular Nitric Acid at the Air–Water Interface, *J. Am. Chem. Soc.*, 2021, **143**(1), 453–462.
- 59 T. Lewis, B. Winter, A. C. Stern, M. D. Baer, C. J. Mundy, D. J. Tobias and J. C. Hemminger, Does Nitric Acid Dissociate at the Aqueous Solution Surface?, *J. Phys. Chem. C*, 2011, **115**(43), 21183–21190.
- 60 T. Langner, A. Rietig and J. Acker, Raman spectroscopic determination of the degree of dissociation of nitric acid in binary and ternary mixtures with HF and  $\text{H}_2\text{SiF}_6$ , *J. Raman Spectrosc.*, 2020, **51**(2), 366–372.
- 61 S. Wang, R. Bianco and J. T. Hynes, Dissociation of nitric acid at an aqueous surface: Large amplitude motions in the contact ion pair to solvent-separated ion pair conversion, *Phys. Chem. Chem. Phys.*, 2010, **12**(29), 8241–8249.
- 62 A. V. Levanov, O. Y. Isaikina and V. V. Lunin, Dissociation constant of nitric acid, *Russ. J. Phys. Chem. A*, 2017, **91**(7), 1221–1228.
- 63 Y. Marcus and G. Hefter, Ion Pairing, *Chem. Rev.*, 2006, **106**(11), 4585–4621.
- 64 A. V. Matyskin, P. L. Brown and C. Ekberg, Weak barium and radium hydrolysis using an ion exchange method and its uncertainty assessment, *J. Chem. Thermodyn.*, 2019, **128**, 362–371.
- 65 L. Ciavatta, The specific interaction theory in equilibrium analysis: some empirical rules for estimating interaction coefficients of metal-ion complexes, *Ann. Chim.*, 1990, **80**, 255–263.
- 66 R. J. B. G. Silva, M. H. Rand, P. B. Robouch, H. Wanner and I. Puigdomenech, *Chemical Thermodynamics of Americium*, Nuclear Energy Agency, 1995.
- 67 M. Goral and B. Wisniewska-Gocłowska, IUPAC-NIST Solubility Data Series. 82. Alcohols with Water—Revised and Updated: Part 3. C6 Alcohols with Water, *J. Phys. Chem. Ref. Data*, 2007, **36**(2), 399–443.
- 68 A. Maczynski, D. G. Shaw, M. Goral, B. Wisniewska-Gocłowska, A. Skrzecz, Z. Maczynska, I. Owczarek, K. Blazej, M.-C. Haulait-Pirson, F. Kapuku, G. T. Hefter and A. Szafranski, IUPAC-NIST Solubility Data Series. 81. Hydrocarbons with Water and Seawater—Revised and Updated Part 1. C5 Hydrocarbons with Water, *J. Phys. Chem. Ref. Data*, 2005, **34**(2), 441–476.



- 69 M. Goral and B. Wisniewska-Gocłowska, IUPAC-NIST Solubility Data Series. 82: Alcohols with Water—Revised and Updated: Part 2. C5 Alcohols with Water, *J. Phys. Chem. Ref. Data*, 2007, **36**(1), 133–190.
- 70 M. Goral and B. Wisniewska-Gocłowska, IUPAC-NIST Solubility Data Series. 82: Alcohols with Water—Revised and Updated: Part 4. C7 Alcohols with Water, *J. Phys. Chem. Ref. Data*, 2007, **36**(2), 445–484.
- 71 M. Goral and B. Wisniewska-Gocłowska, IUPAC-NIST Solubility Data Series. 82: Alcohols with Water—Revised and Updated: Part 5. C8–C17 Alcohols with Water, *J. Phys. Chem. Ref. Data*, 2007, **36**(3), 685–731.
- 72 M. Góral and B. Wiśniewska-Gocłowska, IUPAC-NIST Solubility Data Series. 86: Ethers and Ketones with Water. Part 4. C4 and C5 Ketones with Water, *J. Phys. Chem. Ref. Data*, 2008, **37**(3), 1517–1574.
- 73 M. Góral and B. Wiśniewska-Gocłowska, IUPAC-NIST Solubility Data Series. 86: Ethers and Ketones with Water. Part 5. C6 Ketones with Water, *J. Phys. Chem. Ref. Data*, 2008, **37**(3), 1575–1609.
- 74 M. Góral and B. Wiśniewska-Gocłowska, IUPAC-NIST Solubility Data Series. 86: Ethers and Ketones with Water. Part 6. C7–C12 Ketones with Water, *J. Phys. Chem. Ref. Data*, 2008, **37**(3), 1611–1653.
- 75 M. Arisaka and T. Kimura, Thermodynamic and Spectroscopic Studies on Am(III) and Eu(III) in the Extraction System of *N,N,N',N'*-Tetraoctyl-3-Oxapentane-1,5-Diamide in *n*-Dodecane/Nitric Acid, *Solvent Extr. Ion Exch.*, 2011, **29**(1), 72–85.
- 76 E. A. Mowafy and H. F. Aly, Synthesis of some *N,N,N',N'*-Tetraalkyl-3-Oxa-Pentane-1,5-Diamide and their Applications in Solvent Extraction, *Solvent Extr. Ion Exch.*, 2007, **25**(2), 205–224.
- 77 P. N. Pathak, S. A. Ansari, S. Kumar, B. S. Tomar and V. K. Manchanda, Dynamic light scattering study on the aggregation behaviour of *N,N,N',N'*-tetraoctyl diglycolamide (TODGA) and its correlation with the extraction behaviour of metal ions, *J. Colloid Interface Sci.*, 2010, **342**(1), 114–118.
- 78 I. Herdzyk-Koniecko, C. Wagner, M. Trumm, U. Müllich, B. Schimmelpfennig, J. Narbutt, A. Geist and P. J. Panak, Do An(III) and Ln(III) ions form heteroleptic complexes with diglycolamide and hydrophilic BT(B)P ligands in solvent extraction systems? A spectroscopic and DFT study, *New J. Chem.*, 2019, **43**(16), 6314–6322.
- 79 H. Suzuki, Y. Sasaki, Y. Sugo, A. Apichaibukol and T. Kimura, Extraction and separation of Am(III) and Sr(II) by *N,N,N',N'*-tetraoctyl-3-oxapentanediamide (TODGA), *Radiochim. Acta*, 2004, **92**(8), 463–466.
- 80 M. R. Antonio, D. R. McAlister and E. P. Horwitz, An europium(III) diglycolamide complex: insights into the coordination chemistry of lanthanides in solvent extraction, *Dalton Trans.*, 2015, **44**(2), 515–521.
- 81 H. Narita, T. Yaita and S. Tachimori, Extraction behavior for trivalent lanthanides with amides and EXAFS study of their complexes, *Sol. Extr. Ind. Appl.*, ISEC, 2000, vol. 99(1), p. 693.
- 82 T. Yaita, A. W. Herlinger, P. Thiagarajan and M. P. Jensen, Influence of Extractant Aggregation on the Extraction of Trivalent f-Element Cations by a Tetraalkyldiglycolamide, *Solvent Extr. Ion Exch.*, 2004, **22**(4), 553–571.
- 83 S. A. Ansari, P. N. Pathak, M. Husain, A. K. Prasad, V. S. Parmar and V. K. Manchanda, Extraction of actinides using *N,N,N',N'*-tetraoctyl diglycolamide (TODGA): a thermodynamic study, *Radiochim. Acta*, 2006, **94**(6–7), 307–312.
- 84 Z. Chen, X. Yang, L. Song, X. Wang, Q. Xiao, H. Xu, Q. Feng and S. Ding, Extraction and complexation of trivalent rare earth elements with tetraalkyl diglycolamides, *Inorg. Chim. Acta*, 2020, **513**, 119928.

