



CHALMERS
UNIVERSITY OF TECHNOLOGY

Steel Converter Slag as an Oxygen Carrier-Interaction with Sulfur Dioxide

Downloaded from: <https://research.chalmers.se>, 2025-05-17 09:32 UTC

Citation for the original published paper (version of record):

Hildor, F., Leion, H., Mattisson, T. (2022). Steel Converter Slag as an Oxygen Carrier-Interaction with Sulfur Dioxide. *Energies*, 15(16). <http://dx.doi.org/10.3390/en15165922>

N.B. When citing this work, cite the original published paper.

Article

Steel Converter Slag as an Oxygen Carrier—Interaction with Sulfur Dioxide

Fredrik Hildor ¹, Henrik Leion ¹ and Tobias Mattisson ^{2,*}¹ Chemistry and Chemical Engineering, Chalmers University of Technology, 412 93 Göteborg, Sweden² Department of Space, Earth and Environment, Chalmers University of Technology, 412 93 Göteborg, Sweden

* Correspondence: tm@chalmers.se

Abstract: Steel converter slag, also called Linz-Donawitz (LD) slag, has been considered as an oxygen carrier for biofuel chemical looping applications due to its high availability. In addition to its content of iron which contributes to its oxygen-carrying capacity, LD slag also contains a significant amount of calcium. Calcium, however, is known to interact with sulfur, which may affect the usability of LD slag. To get a better understanding of the interaction between sulfur and LD slag, batch scale experiments have been performed using solid and gaseous fuel with or without sulfur dioxide, together with LD slag as an oxygen carrier. The reactivity and sulfur interaction were compared to the benchmark oxygen carrier ilmenite. Sulfur increases the gasification rate of biofuel char and the conversion of CO for both LD slag and ilmenite. However, no effect of sulfur could be seen on the conversion of the model tar species benzene. The increased gasification rate of char was suspected to originate from both surface-active sulfur and gaseous sulfur, increasing the reactivity and oxygen transfer of the oxygen carrier. Sulfur was partly absorbed into the LD slag particles with calcium, forming CaS and/or CaSO₄. This, in turn, blocks the catalytic effect of CaO towards the water gas shift reaction. When the SO₂ vapor pressure was decreased, the absorbed sulfur was released as SO₂. This indicates that sulfur may be released in loop-seals or in the air reactor in a continuous process.

Keywords: LD slag; oxygen carrier; steel converter slag; chemical looping; sulfur chemistry; biomass



Citation: Hildor, F.; Leion, H.; Mattisson, T. Steel Converter Slag as an Oxygen Carrier—Interaction with Sulfur Dioxide. *Energies* **2022**, *15*, 5922. <https://doi.org/10.3390/en15165922>

Academic Editors: Jaroslaw Krzywanski and Tomasz Czakiert

Received: 29 June 2022

Accepted: 11 August 2022

Published: 15 August 2022

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Low-cost oxygen carriers, such as ores or waste products, have been evaluated for thermochemical biomass conversion techniques such as chemical-looping combustion (CLC), chemical-looping gasification (CLG), and oxygen carrier aided combustion (OCAC) [1–3]. These techniques can be used to decrease emissions, but also, in the case of CLC, can be used to separate CO₂ from the flue gases. Figure 1 presents the layout of these processes. If biomass is used and the separated CO₂ is stored, the overall carbon flow to the atmosphere will be negative, i.e., bio-energy with carbon capture and storage (BECCS) [4,5]. However, for this process to be efficient, the oxygen carrier needs to be both efficient and have the chemical and physical strength to enable a lifetime of hundreds of hours of operation [6,7].

Low-cost oxygen carriers are expected to be needed for biomass conversion in these processes, but biomass contains ash that will be mixed with the oxygen carrier and could be hard to separate. Iron-based oxygen carriers are to be preferred since these are nonhazardous to handle and are more environmentally friendly [8]. Among the most promising iron-based low-cost oxygen carriers are ilmenite, an iron-titanium ore that is available in large quantities. Ilmenite has sufficient fuel conversion, as well as good chemical and physical properties, thus currently making ilmenite the benchmark oxygen carrier [2,9–13]. However, since ilmenite is about 6–8 times more expensive than sand, which is used today for fluidized bed boilers, other oxygen carriers with lower costs are of interest [3,14].

Steel converter slag, also called Linz-Donawitz (LD) slag, is a byproduct of the steel manufacturing industry that has been investigated as an oxygen carrier [15]. Since the

demand is low, the price of this material is also expected to be low and more similar to sand [14]. LD slag has been investigated as an oxygen carrier and has been suggested to have sufficient chemical and physical properties in addition to having similar fuel reactivity as ilmenite [15–17].

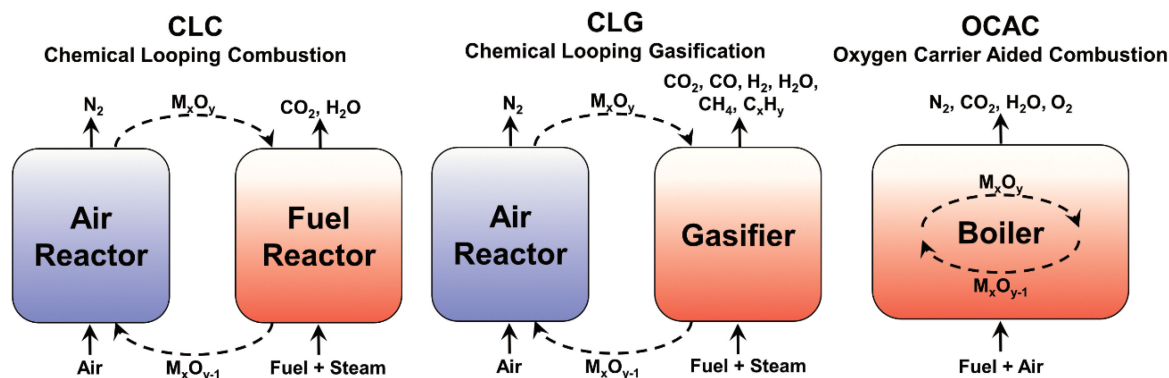


Figure 1. Simplified sketches of three different technologies utilizing metal oxide oxygen carriers (MO in the figure) to produce either separated CO_2 simultaneous with power generation (CLC), raw gasification gas with CO_2 separated into the raw gas (CLG), or oxygen carriers in a conventional boiler for oxygen buffering (OCAC).

During OCAC operation with LD slag, relatively high CO emissions were generated. It was suggested that this unconverted CO was a result of the alkali interaction with the slag. It was suspected that higher amounts of alkali, in the form of KOH and KCl in the boiler, resulted in a lower burnout [14,15]. Sulfur is known to influence alkali chemistry and boiler operation during combustion. If sulfur is present, alkali will react and form sulfates resulting in, e.g., decreased superheater corrosion. Therefore, co-combustion with sulfur-rich fuel, or the addition of sulfur, is commonly used to decrease corrosion [18–20]. When LD slag was used as bed material in the Chalmers CFB boiler, sulfur was added with two different methods: (I) ammonium sulfate was added to the cyclone resulting in decreased CO emission, as expected; (II) elementary sulfur was added directly to the bed together with the fuel. However, elementary sulfur only had a temporary effect on decreasing CO emissions [14]. Thus, it is expected that co-combustion with sulfur-rich fuels will not be as efficient to decrease CO emission or corrosion for longer periods when using LD slag as an oxygen carrier. Lime in the LD slag supposedly reacted with the sulfur and formed $CaSO_4$. From SEM-EDX analysis, it was also indicated that sulfur was accumulated not only on the surface of the particles, but also inside the bed particles [15]. Projecting this observed interaction and the knowledge that $CaSO_4$ has a larger crystal structure than CaO and $CaCO_3$, the formation of $CaSO_4$ might also result in decreased surface area of the particles since pores can be plugged. This could result in decreased reactivity of the oxygen carrier since gas transport through the particle is decreased [21].


Previous studies with oxygen carriers and sulfur interaction have concluded that oxygen access via the oxygen carrier is essential for the forms of sulfur which are generated in a chemical-looping process. From both thermodynamic calculations [22,23] and experiments [23–26], it has been observed that mostly H_2S is formed if the oxygen access is under-stoichiometric, as in the fuel reactor of a CLG process. When lower fuel to oxygen carrier ratios are used, the larger oxygen access will result in mostly SO_2 being formed. From these studies, it has been concluded that most sulfur is released in the fuel reactor. However, none of these investigated oxygen carriers contained calcium, which is known to react with sulfur at combustion boiler temperatures. In one study, Arjmand et al. investigated calcium manganite with methane and SO_2 , and here it was found that calcium played a significant role in binding the sulfur to different compounds [27]. Ilmenite that had been used under OCAC conditions has also been evaluated regarding sulfur interaction,

finding that the calcium from ash has a significant role in the sulfur chemistry also for other oxygen carriers [28].

This study aims to investigate how sulfur affects the properties of the calcium-rich oxygen carrier LD slag under conditions relevant for CLC and CLG. It is expected that sulfur affects the gasification rate of the char, conversion of gaseous species, and composition of the outgoing gases, hence it is significant for understanding the process.

Theoretical Background

The formation of CaSO_4 from limestone in boilers for high-temperature sulfur capturing processes was studied intensely during the 1960s and 1970s. These studies were mostly directed toward the combustion of sulfur-containing coal [29,30]. Additionally, more recently there have been investigations of utilizing lime together with iron ore oxygen carriers to remove sulfur from coal in a laboratory fluidized bed [31]. Thermodynamically, the optimal sulfur capture temperature for limestone is around 880 °C, at which temperature CaCO_3 calcines to CaO according to Reaction (R1) [32]. CaO , in turn, reacts with SO_2 under oxidizing conditions, forming CaSO_4 according to Reaction (R2).






However, due to the shifting reducing and oxidizing conditions in fluidized bed boilers, part of the CaSO_4 is reduced, forming CaS or CaO , as well as gaseous species such as H_2S , COS , and SO_2 [21,29,33]. In comparison to conventional boilers, the fuel reactor in CLG and CLC are moderate-to-very reducing, and will most likely generate sulfur in only the more reduced forms, such as H_2S [23,34]. When using materials such as ilmenite in CLC operation with sulfur-containing fuel, it has been observed that most of the sulfur exits from the fuel reactor as SO_2 and H_2S [23]. These are the most thermodynamic stable gaseous compounds of sulfur under reducing conditions. For materials with oxygen uncoupling properties, it is instead expected that sulfur is emitted as mainly SO_2 from the fuel reactor [23–25].

LD slag contains plenty of calcium in different phases. The slag used in this study contains roughly 30 wt.% of calcium, whereof 2–4 wt.% is in the form of lime (CaO or free calcium). This means that the overwhelming majority of the calcium is bound as calcium silicates or in metal-containing structures [15]. Even though the amount of free calcium is low, the catalytic properties of CaO towards the water gas shift reaction (Reaction (R3)) are important for gasification processes using lime-containing beds, such as LD slag [35,36]. If CaO is sulfated in a gasifier using LD slag as an oxygen carrier, this may affect both the gasification process, as well as the catalytic properties of the bed material.



If CaSO_4 is formed, Reaction (R4) or (R5) can occur to generate CaO or CaS . The CaO can, in turn, react under reducing conditions, forming CaS according to Reaction (R6). In both CLG and CLC with solid fuel, steam will most likely be used in the gasifier/fuel reactor to increase the gasification rate of the solid fuel. CaS can react in these cases with steam according to Reaction (R7), forming H_2S [21]. During oxidation, it can form CaSO_4 or SO_2 according to Reactions (R8) and (R9). CaS might also react with CaSO_4 at temperatures relevant for boilers according to Reaction (R10) [37]. In addition, sulfur has been found to deposit as elementary sulfur inside chemical-looping reactors as a result of the equilibrium Reaction (R11), called the Claus reaction [23].





According to thermodynamic calculations, it has been shown in an oxidative environment that CaSO_4 - CaS - CaO is dependent on temperature, as well as the SO_2 and O_2 partial pressure [21]. During reducing conditions, as with H_2 , a similar phase diagram of the stable solid phases at different temperatures can be calculated (see Figure 2).

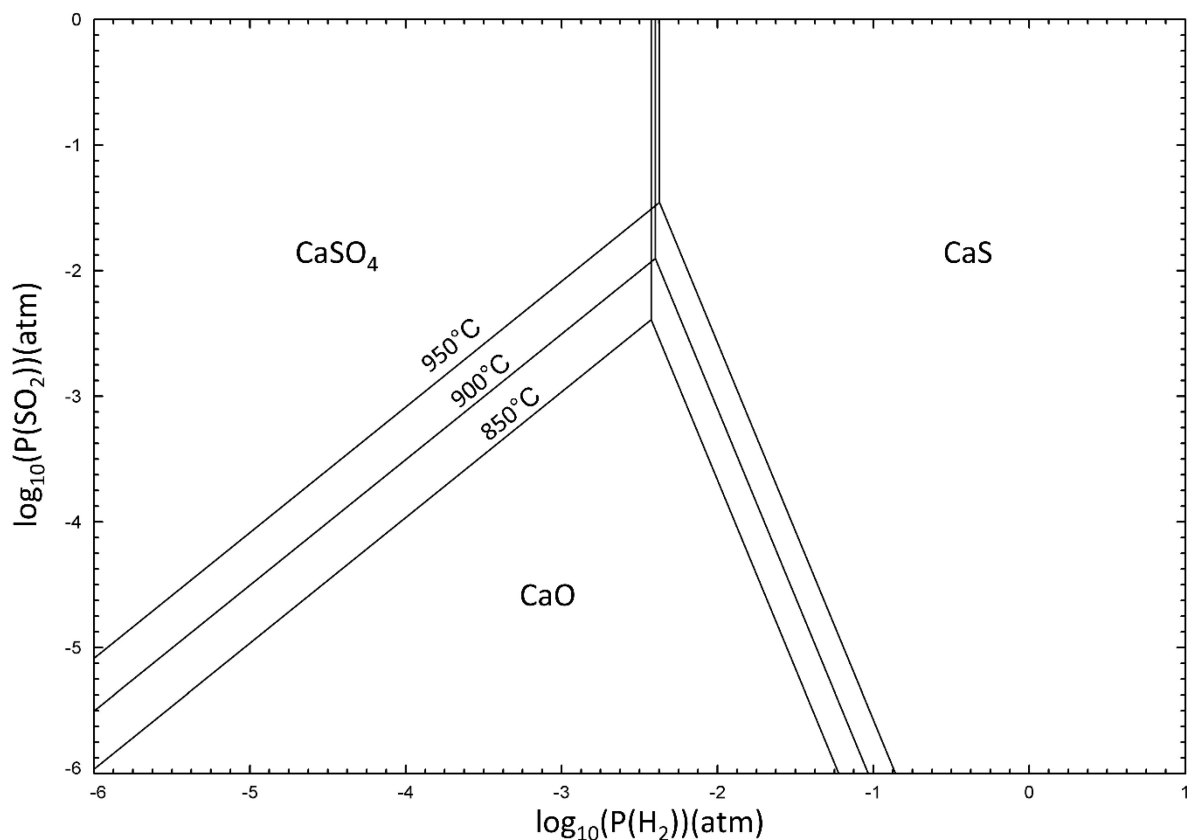



Figure 2. Ca-S-O-H diagram of stable solid phases at different H_2 and SO_2 partial pressure at different temperatures with a constant partial pressure of steam of 50%.

The partial pressure of steam is important for the oxidizing potential in the gasifier/fuel reactor. This is particularly interesting for LD slag since this material generates high hydrogen concentrations via the water-splitting reaction (Reaction (R12)). “A” in the reaction is Mn and Mg that are present in the oxygen carrying phase of LD slag [36]. How steam partial pressure affects the sulfonation of calcium can be seen in Figure 3.



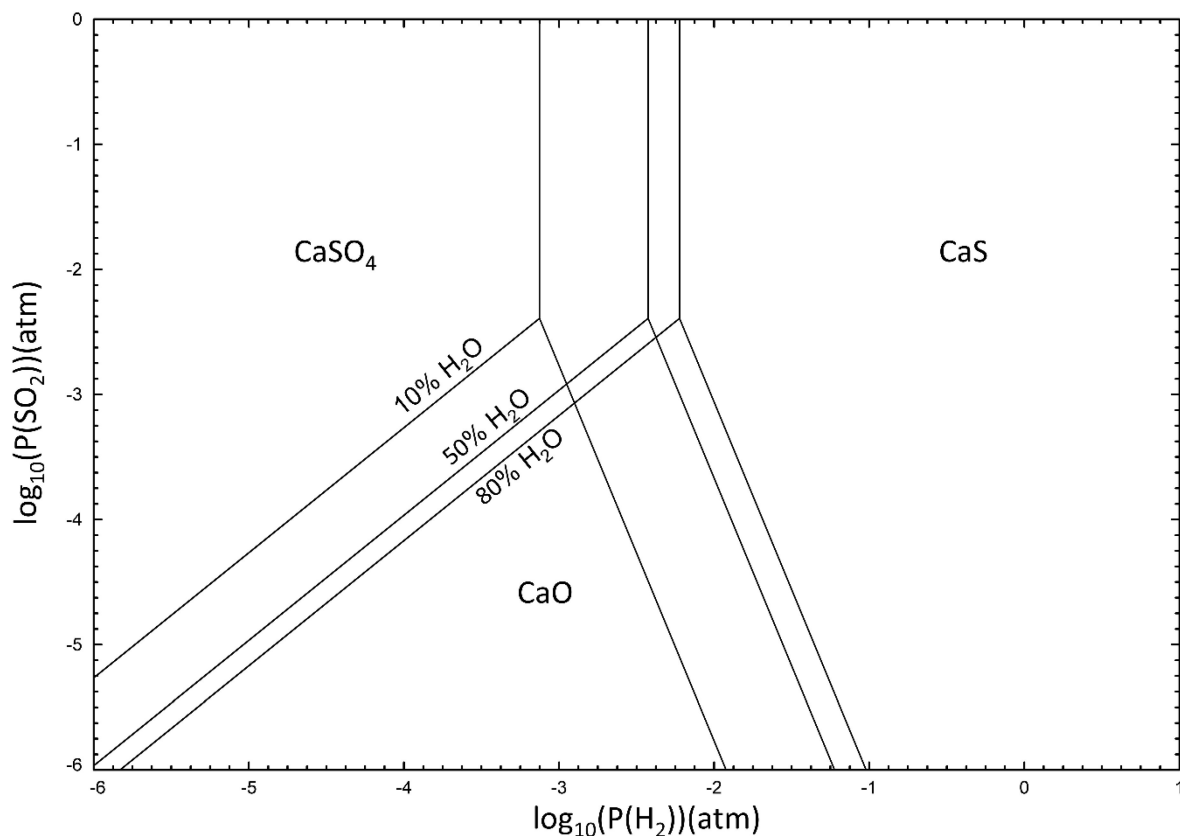


Figure 3. Ca-S-O-H diagram of stable solid phases at different H₂ and SO₂ partial pressure at 850 °C with three different partial pressures of steam.

From Figures 2 and 3, it can be concluded that even with a small partial pressure of sulfur and hydrogen, the most stable phase will be CaS. This means that in CLG and CLC, the phase of free calcium in presence of sulfur is most likely CaS, due to the reducing conditions, especially since significant fractions of hydrogen are expected to be present when using LD slag as an oxygen carrier for gasification [36]. It is important to note that these reactions mentioned above are only related to CaO. The CaO content in LD slag is around 1%; the majority of Ca in LD slag is found in phases like (CaO)_xSiO₂ and CaFe_{2-x}A_xO₅ [15]. However, CaS and CaSO₄ can also be formed from these phases at a low partial pressure of SO₂ at 850 °C and reducing conditions (see Supplementary Materials for calculated equilibriums).

Although LD slag was the main focus of this work, the benchmark oxygen carrier ilmenite was also used for comparison. It has been observed for ilmenite that the reaction rate towards methane [23] and coal pyrolysis gas [38] increases in the presence of sulfur dioxide. This was not only during the experiments with sulfur dioxide added in the gas phase, but there also seemed to be a lasting effect on the oxygen carrier. Even afterward, when sulfur was not added with the fuel, continued experiments showed an increased reactivity due to bound sulfur in the particles.

The scope of this study is to investigate how sulfur interacts with LD slag during reducing conditions. The fate of sulfur will be investigated and the potential formation of CaS and CaSO₄ explored. The effect of sulfur on the gasification properties and whether sulfur will be released during oxidizing or reducing conditions are other aspects that will be explored. The conversion behavior of benzene, an important tar precursor, together with sulfur, was also investigated in this work.

2. Experiments

The experiments in this work were performed in a batch laboratory fluidized bed reactor (see Figure 4 for a schematic overview of the unit). Here, gases were selected and inserted from the bottom of the reactor. The reactor, with an inner diameter of 22 mm, was constructed of quartz glass and mounted inside a furnace. In the quartz reactor, a porous plate was fixed where particles were placed for exposure. Temperature was measured both underneath the bed and inside the bed of particles. Pressure fluctuations over the bed were measured using a Honeywell pressure transducer with a frequency of 20 Hz for observation of bed fluidization behavior or interruptions in the fluidization.

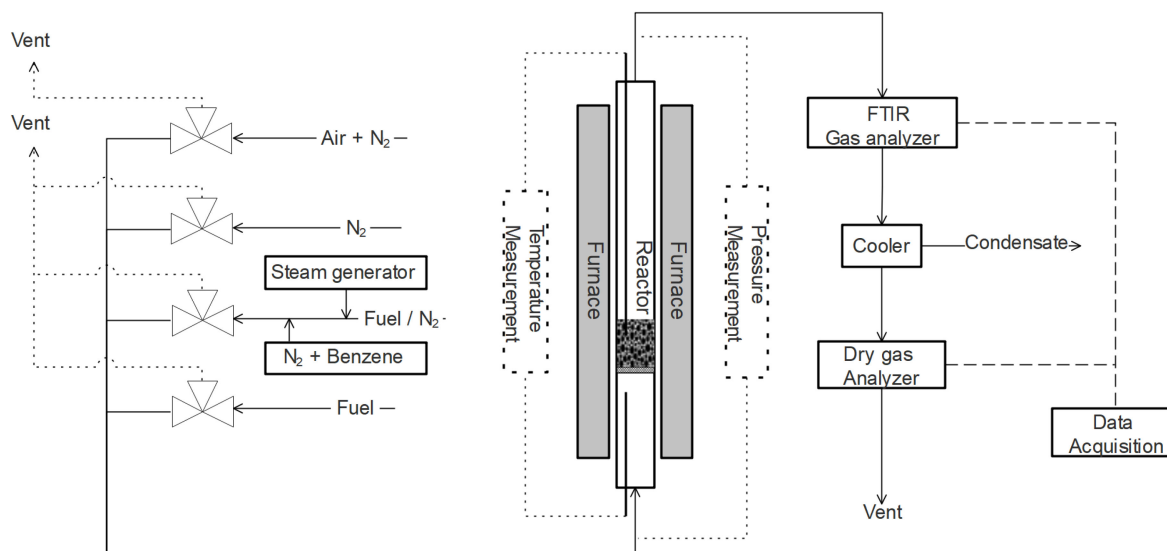


Figure 4. Schematic overview of the batch fluidized bed reactor system.

The wet outgoing gases were analyzed using an FTIR during gaseous fuel experiments to measure benzene. After a cooler and a condensation trap, one of two five-channel Rosemount NGA 2000 instruments analyzed the gases. The first four channels of both analyzers were equipped with NDIR (nondispersive infrared) sensors for CO₂, CO, and CH₄, and a paramagnetic sensor for O₂ measurement. The two analyzers differed on the fifth channel where either an SO₂ NDIR detector or a thermal conductivity detector for H₂ was installed. Dräger tubes for H₂S detection and SO₂ were also used to estimate the H₂S/SO₂ formation. Gases for Dräger tubes were collected after the dry gas analyzer in air-tight 1 L aluminum bags and measured afterward. It is important to note that SO₂ dissolves in water and was partly dissolved in the condensation trap, identified by both the smell and the increased acidity of the water. For experiments with solid fuel, the FTIR was bypassed, in order to protect the FTIR instrument from tars. For these experiments, the components in the outgoing gas were only analyzed with one of the Rosemount analyzers at the time. More details regarding the system can be found elsewhere [39].

The oxygen carrier material used in these experiments was LD slag received from SSAB, sieved to 150–400 µm. The same batch of slag has been used in other studies [14,15,40,41]. The ilmenite used was a Norwegian rock ilmenite received from Titania, sieved between 100–300 µm. This batch has also been used in other studies [2,15,42]. Both oxygen carriers were heat-treated in air at 950 °C for 24 h. The sand was extra pure sea sand received from Merck, sieved between 180–250 µm. The elemental composition of these bed materials can be seen in Table 1. Elemental composition was determined using ICP-SFMS according to SS EN ISO 17294-2: 2016 on LD slag and sand, and XRF according to the SP method 4343 on ilmenite.

Table 1. Elemental composition is given in wt.% of the studied bed materials excluding oxygen.

Element	Fe	Ti	Ca	Si	Mg	Mn	V	Al	Cr	Ni
LD slag	17	0.78	32	5.6	5.9	2.6	1.5	0.76	0.33	0.002
Ilmenite	36	28	0.22	0.67	2	0.21	0.12	0.17	0.06	0.03
Sand	0.36	0.04	0.05	45	0.24	0.01	0	0.22	0	0

The solid fuel used in the laboratory fluidized bed reactor was produced by inert heat treatment of wood pellets. Wood pellets were devolatilized in a fluidized silica bed at 820 °C under an N₂ atmosphere for more than 20 min. After devolatilization and cooling down, the sand was sieved. The devolatilized wood pellets were then crushed and sieved to obtain the desired size range of 180–300 µm. The volatile mass fraction of the original pellets was calculated to be 82 wt.%. The elemental composition of the wood pellets and the devolatilized fuel can be seen in Table 2.

Table 2. Fuel analysis of the pellets and devolatilized pellets used in the experiments. Samples were converted into ash at 550 °C according to SS-EN-ISO 18122. Values are given in wt.%.

	Dry Basis					on Ash Samples							
	Ash	S	C	H	O	Fe	Ca	Mg	Mn	Al	K	P	Si
Wood Pellets Sample	0.4	< 0.02	50.3	6.2	43	0.89	22	3.6	2.7	1.1	9.6	1.4	4.0
Devolatilized Wood Pellets Sample	3.5	0.02	93.5	< 0.5	3	3.9	21	4.8	2.9	1.5	5.8	1.3	6.6
German wood char	7.2	0.02	85.3	2.6	4.4	1	12	0.97	0.37	1	4.4	0.35	12

In addition to the wood pellets, another reference fuel was used called German wood char. This was delivered already as char and was only crushed and sieved to obtain the desired size range of 180–300 µm.

Prior to experiments in the batch fluidized bed reactor, the bed was activated using syngas (50% CO in H₂). These activation cycles were performed with 900 mL/min syngas for 20 s in every cycle, followed by oxidization with 5% O₂. The oxidation was performed until the sample was fully oxidized and the outgoing gases reached 5% O₂ again. Between these reducing and oxidizing atmospheres, inert N₂ with a flow of 1000 mL/min was used to purge the reactor for 180 s. These activation cycles were performed until a constant conversion of syngas could be observed for the sample, normally 7–20 cycles depending on the mass of the oxygen carrier. This activation was performed since there is a known increase in reactivity for these oxygen carriers, and after activation, the conversion of fuels is rather stable [12]. These types of cycles were also used before every experiment as a reference.

2.1. Solid Fuel Experiments

For the solid fuel experiments, a sample of 40 g of oxygen carrier bed material was used. First, the oxygen carriers were activated using syngas. After the activation cycles, the solid fuel experiments were performed. Here, devolatilized and crushed wood char pellets were inserted from the top of the reactor together with a stream of 500 mL/min N₂. A sample of 0.2 g of devolatilized char in the size range of 180–300 µm was used. During solid fuel cycles without sulfur addition, the bed material was fluidized using 50% steam in N₂ with a total flow of 1000 Nml/min. For experiments with SO₂, a total flow of 1000 Nml/min was used with a concentration of 50% steam, and was mixed with SO₂ in N₂, meaning that the inlet concentration of SO₂ was 0.2 or 0.4% of the total inlet flow.

A summary of all the experiments can be seen in Table 3. The experiment matrix was performed with both fuels, the devolatilized wood pellets and German wood char. There were differences in the setup with the analyzers detecting either H₂ or SO₂. Dräger tubes

for SO₂ and H₂S were mainly used for 0.4% SO₂ experiments with German wood char. For experiments with German wood char, complementary reference experiments were performed after all SO₂ experiments to detect releases of sulfur from the used material using Dräger tubes.

Table 3. Summary of experiments with solid fuel.

	Gas Composition during Reduction	Reduction Length [s]	Temp [°C]	Number of Cycles	Measurements
Activation cycles	900 mL/min 50% CO 50% H ₂	20	850	3–15	CO, CO ₂ , CH ₄ , O ₂ , and H ₂
Reference experiment	1000 mL/min 50% H ₂ O N ₂ Balance 0.2 g Fuel	900–3000	870, 920, and 970	3	CO, CO ₂ , CH ₄ , O ₂ , and H ₂ /SO ₂ + Dräger tubes SO ₂ , H ₂ S for German wood char final
0.2% SO ₂	1000 mL/min 50% H ₂ O 0.2% SO ₂ N ₂ Balance 0.2 g Fuel	900–3000	870, 920, and 970	3	CO, CO ₂ , CH ₄ , O ₂ , and H ₂ /SO ₂
0.4% SO ₂	1000 mL/min 50% H ₂ O 0.4% SO ₂ N ₂ Balance 0.2 g Fuel	900–3000	870, 920, and 970	3	CO, CO ₂ , CH ₄ , O ₂ , and H ₂ /SO ₂ + Dräger tubes SO ₂ , H ₂ S for German wood char

This oxidation–inert–reducing–inert series, or cycle, was repeated three times at each experimental condition. The results were averaged over these cycles. Experiments were performed at 870 °C and 970 °C. The same sample (LD slag, ilmenite or sand) was used for all experiments, first for all experiments without sulfur, and then for the experiments with sulfur. Figure 5 shows one typical cycle of solid fuel gasification with LD slag at 870 °C. When the 5% oxygen in nitrogen is replaced with inert gas at time = 0 s, the oxygen concentration rapidly drops as the oxygen is flushed from the system. The solid fuel, fluidization gas containing steam, N₂, and for the specific experiment 0.4% SO₂, was introduced at 180 s. The gasification of the fuel proceeds, as indicated by the rising concentrations of CO₂, CO, and H₂. After 900–3000 s when all carbon in the bed has been converted, another inert period of 180 s was performed before reoxidation of the oxygen carriers. During the oxidation period, 5% oxygen in nitrogen was first fully reacting with the particles, clearly seen as no gas-phase O₂ exits from the reactor initially. At about 2500 s in the figure, the oxygen increases as the oxygen carriers become saturated with oxygen. At the same time as gas-phase O₂ was observed, a small amount of CO₂ was generated. This CO₂ originates from the combustion of unconverted char and char that may be trapped on the walls of the upper part of the reactor tube [43]. In the figure, the concentration of SO₂ is multiplied by a factor of 10 to improve readability. Two things should be noted regarding the concentration of SO₂: (i) SO₂ does not decrease to zero when SO₂ was removed from the fluidizing gas during the inert period after the fuel cycle; and (ii) SO₂ never reaches the ingoing concentration since some sulfur is absorbed in the cooler and bed material.

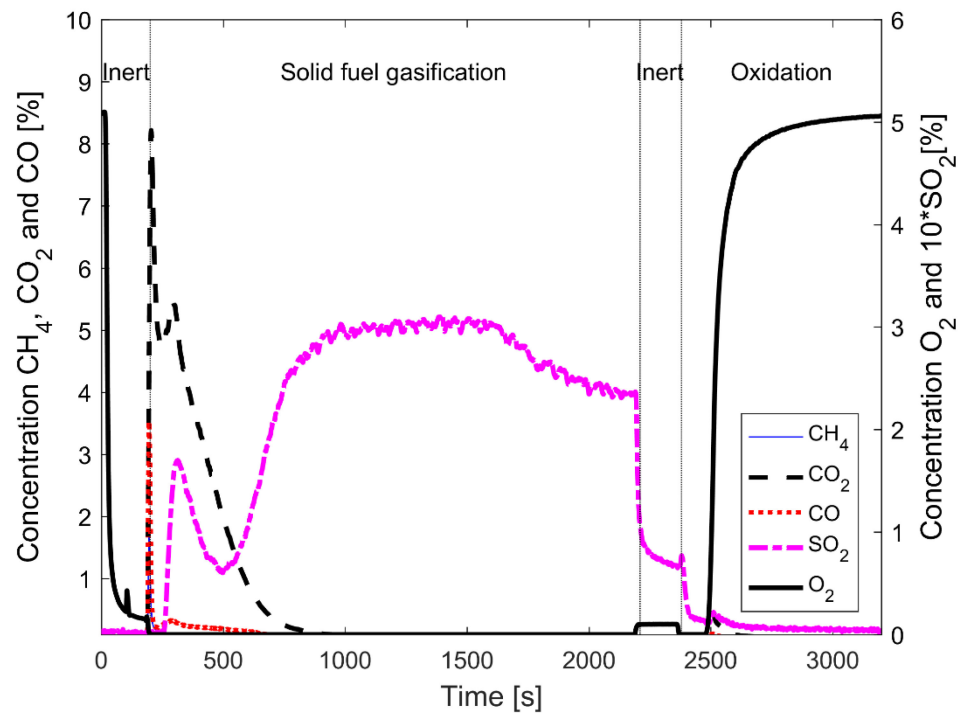


Figure 5. One cycle at 870 °C of char gasification using LD slag as bed material in the laboratory scale fluidized bed with 0.4% SO₂ present in the fluidization gas.

Data Evaluation

For the solid fuel experiments, the total molar gas yield for each component from the gasification of the char was calculated with Equation (1) between time t_1 to time t_2 . This was done for either a full cycle or for a part of a cycle. The total molar flow was calculated assuming ideal gas using Equation (2), P —pressure (Pa), R —gas constant, T —temperature (K), V —volume (m³) and x_A —concentration. This was done with the assumption that the only outgoing gases of significant volume in the non-condensed gas were CO₂, CO, H₂, and CH₄. SO₂ was excluded due to the limited concentration and since SO₂ could not be measured at the same time as H₂.

$$n_{i,t} = \int_{t_1}^{t_2} x_{i,out} * \dot{n}_{out} dt \quad (1)$$

$$\dot{n}_{out} = \frac{P}{RT} * \frac{\dot{V}_{N_2,in}}{1 - (x_{CO_2} + x_{CO} + x_{H_2} + x_{CH_4})} \quad (2)$$

The fraction of char converted, X_c , is defined as the cumulative carbon released at a certain time divided by the total carbon emitted from the converted char during the reduction period. These are defined in Equations (3) and (4). The integral in Equation (4) is evaluated from the time of char insertion ($t_1 = t_{red, start}$) to the end of the reduction when the atmosphere in the reactor is changed to inert ($t_2 = t_{red, end}$).

$$X_c(t) = \frac{m_c(t)}{m_{c,tot}} \quad (3)$$

$$m_c(t) = M_c \int_{t_1}^{t_2} \dot{n}_{out}(t) (x_{CO}(t) + x_{CO_2}(t) + x_{CH_4}(t)) dt \quad (4)$$

The gasification rate (r_w) was calculated using Equation (5) where \dot{m}_c was the mass-based rate of conversion of carbon. The gasification rate was then normalized using Equation (6). In this work, a mean value for the gasification rate was normally extracted

from the gasification rate between a char conversion of $0.3 < X_c < 0.7$. The reason for this conversion span is that the gasification rate is more stable in this region and easier to compare to other experiments [44].

$$r_w = \frac{dX_c}{dt} = \frac{\dot{m}_c}{m_{c,tot}} \quad (5)$$

$$r = \frac{r_w}{1 - X_c} \quad (6)$$

In addition to the char conversion, the gas phase conversion is also very important. Two parameters have been used in this work to evaluate the gas conversion: (i) the conversion of carbon species to CO, and (ii) the H₂/CO molar ratio. The former is defined as Equation (7). Here the molar yield of each component is calculated using Equation (1), averaged over $0.3 < X_c < 0.7$.

$$\frac{CO}{C_t} = \frac{n_{CO}}{n_{CO} + n_{CO_2} + n_{CH_4}} \quad (7)$$

Re-oxidation after the reduction cycle, correlated to the omega value at the end of the cycle, was calculated using Equation (8). A reference O₂ curve using inert sand in the same experimental conditions was used to determine the point of transition between inert and oxidizing conditions. The difference between the actual uptake using an oxygen carrier and the reference cycle with inert sand was then judged to be a result of O₂ uptake of the oxygen carrier.

$$O_{2,re-oxidation} = \int_{t_{ox}=0}^{t_{ox}=end} (x_{O_2,ref} - x_{O_2,sample}) * \dot{n}_{out} \quad (8)$$

Since there are both traces of soot and some remaining char, the final O₂ consumed by the oxygen carrier is calculated by subtracting the molar CO₂ generated during oxidation from the total O₂ uptake during the same period.

The equilibrium constant K_{eq} for the WGS Reaction (R6) is defined as in Equation (9) when gases are at equilibrium. The temperature dependence of the equilibrium at atmospheric pressure is shown in the same equation [45,46]. The reaction quotient Q_i is defined similarly as the equilibrium, and calculated for the measured outgoing gases from the reactor at the time i (see Equation (10)). Q_i is used to estimate how far the concentrations of the gases are from the equilibrium. If $Q_i = K_{eq}$, the gases are at equilibrium with respect to Reaction (R6).

$$K_{eq} = \frac{x_{CO_2} * x_{H_2}}{x_{CO} * x_{H_2O}} = \exp\left(-4.33 + \frac{4577.8}{T}\right) \quad (9)$$

$$Q_i = \frac{x_{CO_2,i} * x_{H_2,i}}{x_{CO,i} * x_{H_2O,i}} \quad (10)$$

2.2. Gaseous Fuel Experiments

Two different setups for gaseous fuel experiments were conducted for this study: (I) benzene experiments to evaluate how and if sulfur affects the conversion of the tar component benzene, and (II) the effects of SO₂ on the conversion of syngas (CO + H₂). Here, it is important to study possible interactions with sulfur with the bed material with lasting effects on the conversion of the fuel.

2.2.1. Effect of SO₂ on Benzene Conversion

Benzene tests were executed with 5 g oxygen carrier (ilmenite or LD slag) diluted with 10 g silica sand at 850 °C. This dilution was necessary to avoid full conversion of the gaseous fuel species. The samples were activated as described in Section 2.1. After activation, the same cyclic schedule was used, oxidation–inert–reduction–inert, with the

same flow during inert and oxidation as described in Section 2.1. For benzene tests, a flow of 500 mL/min steam and 300 mL/min N₂/benzene mixture was introduced during the reduction phase in the cycles. The N₂/benzene mixture was N₂ saturated with benzene at 6 °C, resulting in a benzene concentration of 1.46% in the ingoing flow. The sulfur content was regulated to obtain a total content of 0%, 0.2%, and 0.4% SO₂ in the fluidization gas according to Table 4. Reducing gas was inserted for 60 s every cycle. Experiments were performed at 850 °C to be more comparable to previous results [15,47].

Table 4. Summary of gaseous fuel experiments containing benzene.

	Gas Composition during Reduction	Reduction Length [s]
0% SO ₂	1000 mL/min 50% Steam 1.46% Benzene N ₂ Balance	
0.2% SO ₂	1000 mL/min 50% Steam 1.46% Benzene 0.2% SO ₂ N ₂ Balance	60
0.4% SO ₂	1000 mL/min 50% Steam 1.46% Benzene 0.4% SO ₂ N ₂ Balance	

2.2.2. Effect of SO₂ on CO Conversion and Structure

To investigate if and how SO₂ binds into or onto the LD slag, a sequence of separate reduction cycles was performed with subsequent analysis. The experiments were conducted with CO so the SO₂ effect on the reactivity towards CO could be observed at the same time. Here, 15 g of oxygen carrier was used, without any sand. After activation at 850 °C (described in Section 2.1), the same cyclic oxidation–inert–reduction–inert was used also for the experiments, but at 870 °C instead. Oxidation using 1000 mL/min 5% O₂ in N₂ and inert for 180 s using 1000 mL/min N₂. First, reference experiments with reduction using 900 mL/min 25% CO and 25% H₂ in N₂ for 40 s were committed. After this, samples were reduced for 40 s with a flow of 25% CO, 25% H₂, and 1% SO₂ in N₂. This was done for six cycles at 870 °C. After the final reduction, the sample was oxidized using 5% O₂ and 1.5% SO₂ in N₂ instead of only diluted air, and this was done for over 90 min. This was to investigate how SO₂ was absorbed in the structure of the particles. After this loading of sulfur, the samples were again reduced, this time as the first reference experiments using a flow of 900 mL/min 25% CO and 25% H₂ in N₂ for 40 s. This was also done 6 times. A summary of these experiments can be seen in Table 5.

2.2.3. Data Evaluation

Equation (1) was used to determine the cumulative molar flow of the outgoing gas species, and the conversion over the entire cycle was calculated by dividing the amount of outgoing gas species by the amount of ingoing. The molar flow was assumed to be unchanged for benzene and CO experiments. For benzene, the expected gas expansion is small compared to the total flow considering the low concentration of ingoing benzene.

2.3. Material Characterization

SEM-EDX (scanning electron microscopy equipped with energy dispersive X-ray spectroscopy) analysis was done with an FEI Quanta 200 FEG ESEM. Bed material was mounted in epoxy and polished, exposing a cross-section of the particles, thus making it possible to investigate the inside of the particles with SEM-EDX. The crystalline phases

in the bed material were determined by powder X-ray diffraction (XRD). The XRD was a Bruker D8 ADVANCE equipped with a Cu K α radiation source. BET surface area was measured using a TriStar 3000. The 0.5 g samples were degassed for 1 h at 90 °C, followed by 18 h at 250 °C. The surface area was measured using nitrogen and was cooled using liquid nitrogen.

Table 5. Summary of gaseous fuel experiments with syngas for CO conversion evaluation in the same order as execution.

	Gas Composition during the Experiment	Reduction Length [s]	Number of Cycles
<i>Reference experiment</i>	900 mL/min 25% CO 25% H ₂ N ₂ Balance	40	3
<i>SO₂ Reduction</i>	900 mL/min 25% CO 25% H ₂ 1% SO ₂ N ₂ Balance	40	6
<i>SO₂ Load (OX)</i>	1000 mL/min 5% O ₂ 1.5% SO ₂ N ₂ Balance	90 min	1
<i>CO Reduction</i>	900 mL/min 25% CO 25% H ₂ N ₂ Balance	40	6

3. Results

3.1. Effect of SO₂ on the Gasification of Solid Fuel

As expected, SO₂ contributes to an increased gasification rate of solid biomass fuel [43]. This can be seen in Figure 6 for both LD slag and ilmenite. The gasification rate for ilmenite with SO₂ is stable and higher than for ilmenite without SO₂ more or less over the entire conversion. However, in comparison to ilmenite, LD slag shows both a higher variance and a smaller increase in mean gasification rate. A significant increase of gasification rate formed as a peak at $X_c \approx 0.25$ characterizes the char conversion for LD slag in the presence of sulfur at 870 °C. It is of note that this peak of increased gasification rate was not observed for gasification cycles at 970 °C.

The mean gasification rate is defined as the average gasification rate between the fuel conversion degree of $0.3 < X_c < 0.7$. The effect on the mean gasification rate of different concentrations of SO₂ in the ingoing gas can be observed in Figure 7. With no SO₂ present in the fluidization gas, LD slag and ilmenite have a very similar mean gasification rate. However, in the presence of SO₂, a clear difference between the oxygen carriers can be observed. The gasification rate for ilmenite increased more with higher SO₂ levels compared to LD slag. At 870 °C, the increase in gasification rate is proportional to the amount of SO₂ added to the fluidization gas for both oxygen carriers. This is in contrast to 970 °C, where the difference in rate between 0.2% and 0.4% SO₂ for LD slag is minimal.

Gasification with sand was used as a reference case. The gasification of fuel should primarily depend on the surrounding gas and not on the oxygen-carrying properties. Hence, one can expect that gasification in a sand bed is enhanced with SO₂. However, the addition of SO₂ in the sand experiments did not affect the gasification rate. This was somewhat surprising, so these experiments were executed again with a different solid char fuel, but with the same result. It was also observed that no SO₂ was present in the outgoing gas during the sand experiments; in bag samples only H₂S was detected at low X_c . However, when most of the char was converted, SO₂ was detected in the outgoing gas.

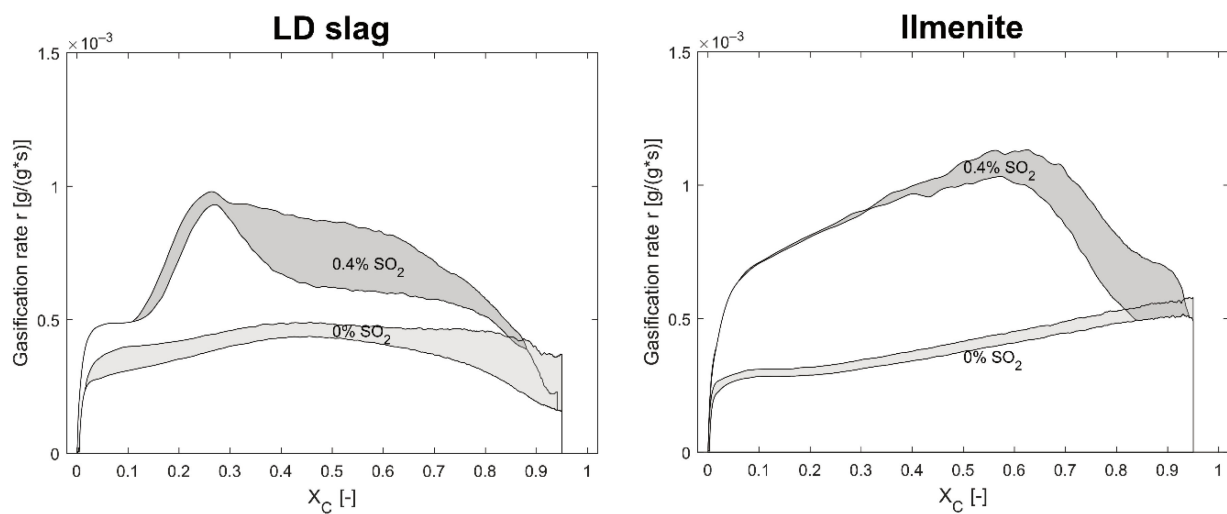


Figure 6. Gasification rate “ r ” as a function of the char conversion X_c for LD slag and ilmenite with SO_2 and without SO_2 in the ingoing gas at 870°C using devolatilized wood pellets. The gray area indicates the reproducibility and is bordered by the highest and lowest gasification rate for the repeated experiments.

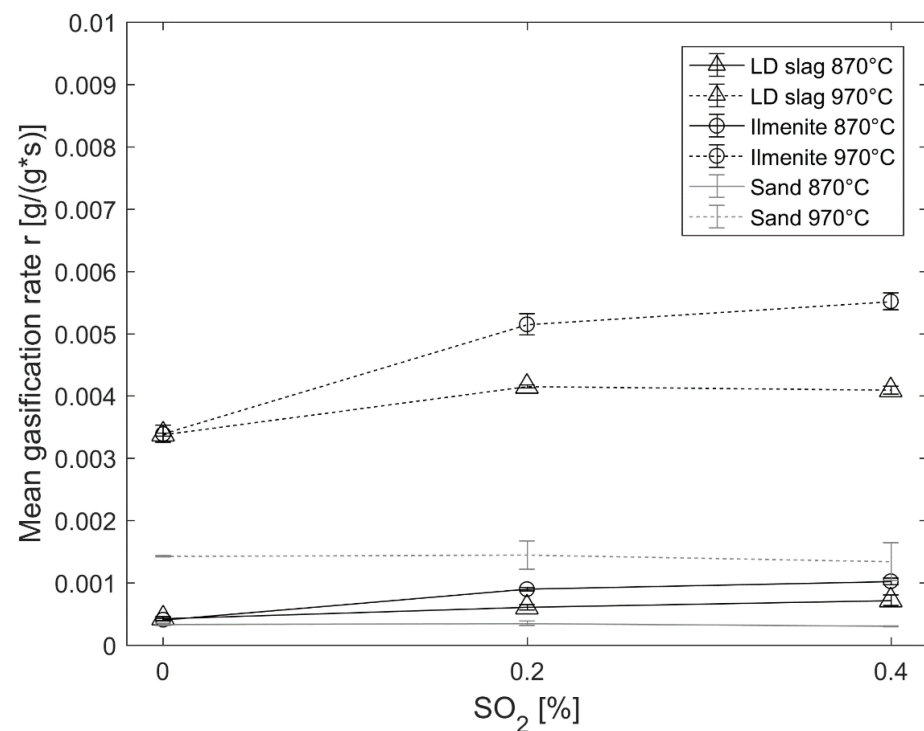


Figure 7. Mean gasification rate “ r ” between $0.3 < X_c < 0.7$ for LD slag, ilmenite, and sand at different temperatures and concentrations of SO_2 .

A closer investigation of the outlet gas concentrations in relation to the gasification rate for a cycle for LD slag and ilmenite, respectively, in the presence of SO_2 as well as without is seen in Figure 8. For the ilmenite, it can be observed that until $X_c = 0.7$, the general shape is the same with and without SO_2 in the inlet gas. The gasification rate with ilmenite increases as the H_2 concentration drops, when $X_c > 0.7$, and more H_2 was generated contributing to the decreased gasification rate, likely due to hydrogen inhibition.

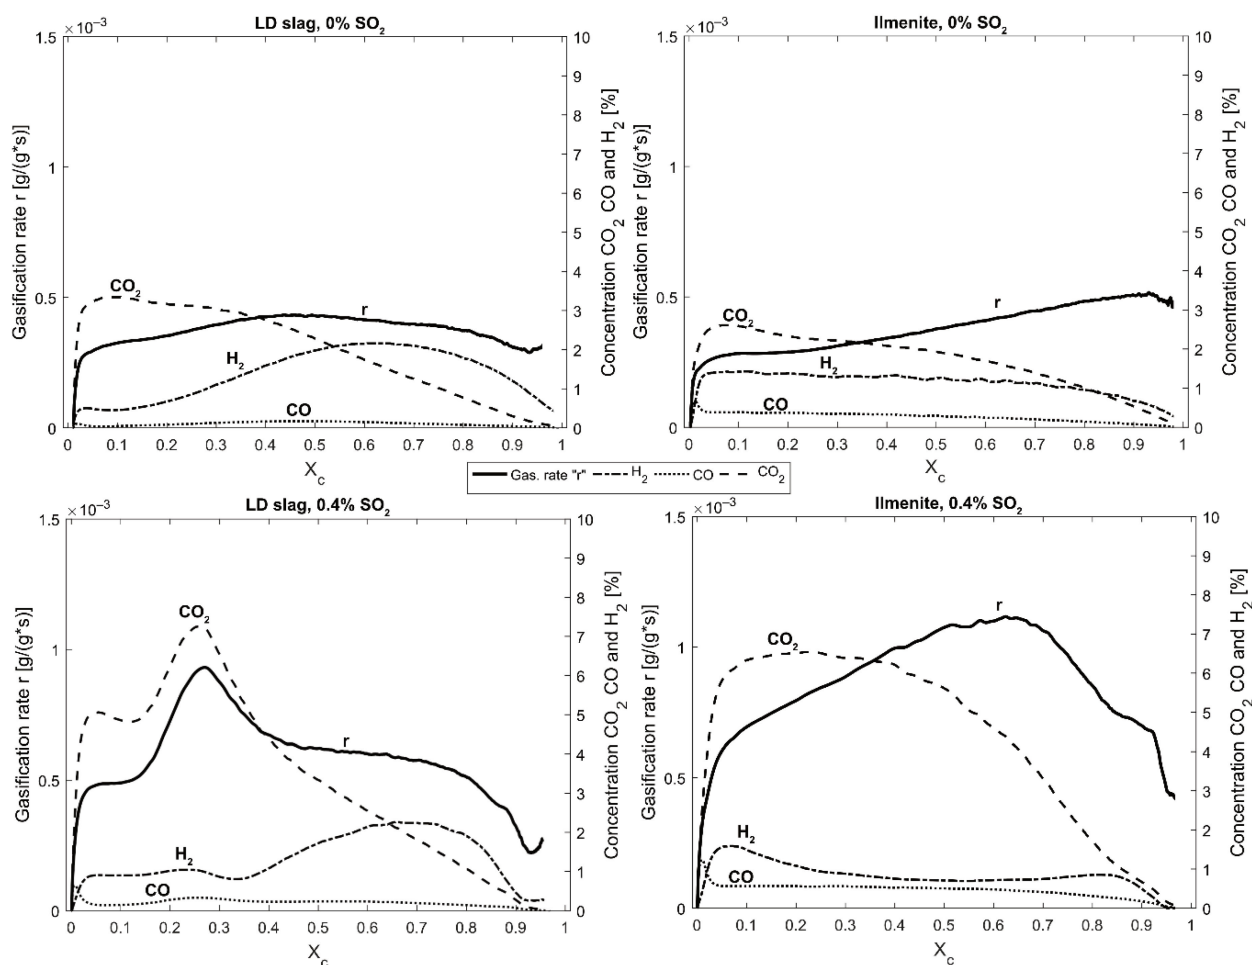


Figure 8. Gasification rate “ r ” and concentration of outgoing gases as a function of X_c for LD slag and ilmenite at 870 °C. The two upper figures are without the presence of SO₂, and the two lower figures are for experiments using 0.4% SO₂. Curves are selected as the middle curve within the max and minimum gasification rate “ r ” displayed as gray areas in Figure 6. Devolatilized wood pellets were used as fuel for these experiments.

For LD slag, there is a significant peak in gasification rate and subsequent CO₂ concentration at around $X_c \approx 0.25$ (see, e.g., Figure 6). This peak was present in all repetitions at 870 °C, but was gradually smoothed out on the right side of the peak. This can be seen in more detail by comparing the lower 0.4% SO₂ curve in Figure 6 with the highest measured gasification rate where the “peak” is a step rather than a peak. At the higher temperature, 970 °C, this peak could not be observed and the general shape of the curves with and without sulfur was closer to each other.

The conversion of the carbon in the fuel to CO can be seen in Figure 9 presented as the CO/ C_t ratio. Here, LD slag is compared to ilmenite and sand at both 870 °C and 970 °C. For LD slag, no significant effect of the SO₂ concentration on the CO/ C_t ratio can be observed. However, for both ilmenite and sand, a minor decrease in CO/ C_t ratio can be observed with increased SO₂. This means that more CO₂ was produced over the cycle when the SO₂ concentration increased.

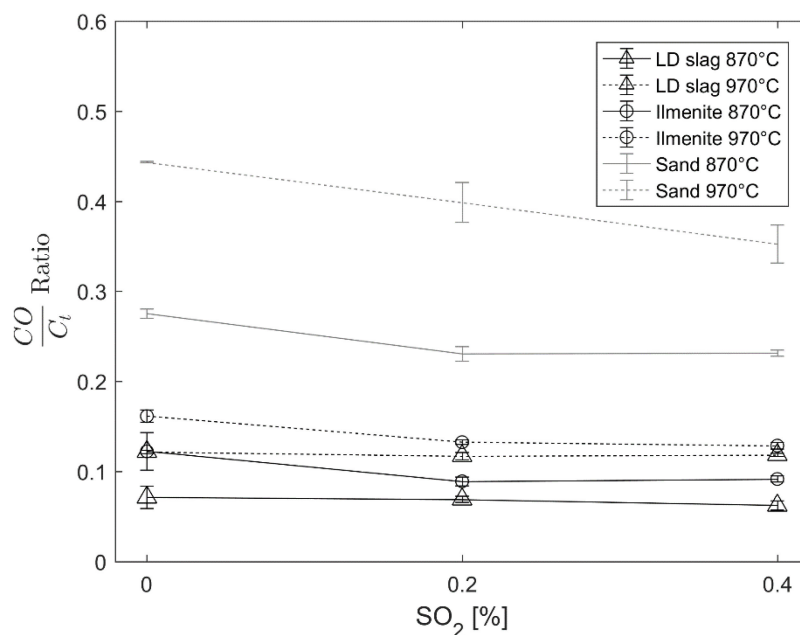


Figure 9. Molar CO ratio over total outgoing carbon for the gasification experiments, taken between $0.3 < X_c < 0.7$ for LD slag, ilmenite, and sand at 870 °C and 970 °C using devolatilized wood pellets as fuel.

The H_2/CO ratio is displayed in Figure 10 for LD slag, ilmenite, and sand at 870 °C and 970 °C. Here, a significant decrease in the H_2/CO ratio could be observed for LD slag at 870 °C with increased SO_2 concentration in the fluidization gas. Similar behavior can be observed for ilmenite at 870 °C. At the higher temperature, 970 °C, no significant changes can be observed regarding the H_2/CO ratio when SO_2 is present with the oxygen carriers.

3.2. Water Gas Shift Reaction

From previous studies, it was observed that the CaO content in LD slag catalyzes the WGS reaction [36]. This means that the outgoing gases from a CLG or CLC process using LD slag will most likely be closer to the equilibrium of the WGS reaction compared to other non-catalytic materials. Comparing the gasification experiments performed with or without the presence of SO_2 (see Figure 11), LD slag showed a changed and decreased reaction quotient Q compared to the experiment performed without SO_2 . In comparison, with ilmenite, which is an oxygen carrier that has a limited catalytic influence on the WGS reaction, the effect of SO_2 on the reaction quotient was only small. The reference experiment with sand also did not show any significant difference for the reaction quotient Q in the presence of SO_2 .

For experiments at the higher temperature of 970 °C (see Supplementary Materials), no clear effect of sulfur could be detected for LD slag or sand towards the WGS reaction. This could indicate that the catalyzing CaO is not affected by sulfur at the higher temperature, meaning that no CaS or $CaSO_4$ was formed at this partial pressure of SO_2 .

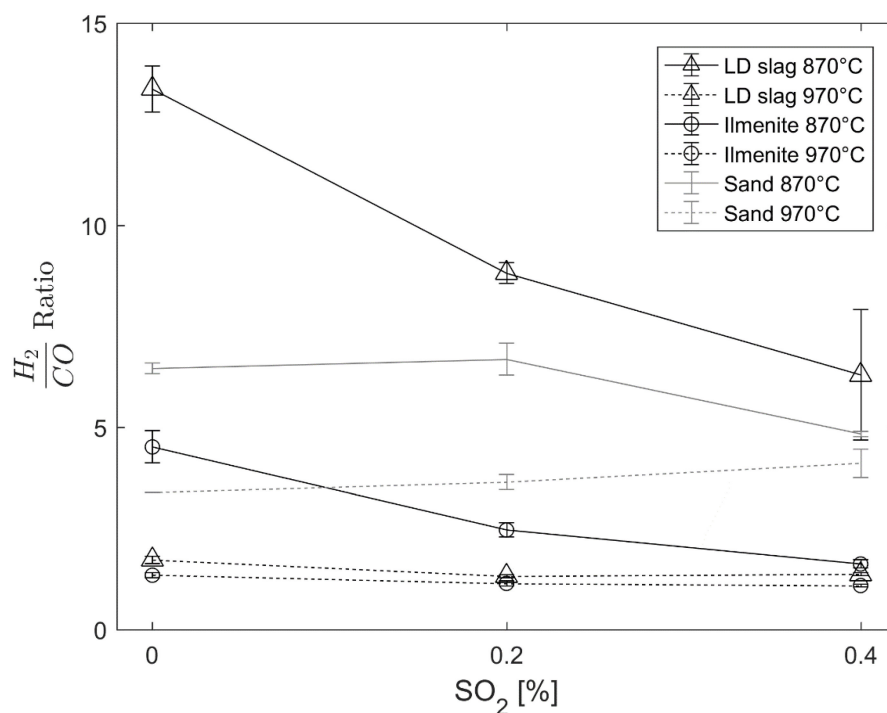


Figure 10. Molar H_2/CO ratio for the gasification experiments was evaluated between $0.3 < X_c < 0.7$ for LD slag, ilmenite, and sand at $870\text{ }^\circ\text{C}$ and $970\text{ }^\circ\text{C}$ using devolatilized wood pellets as fuel.

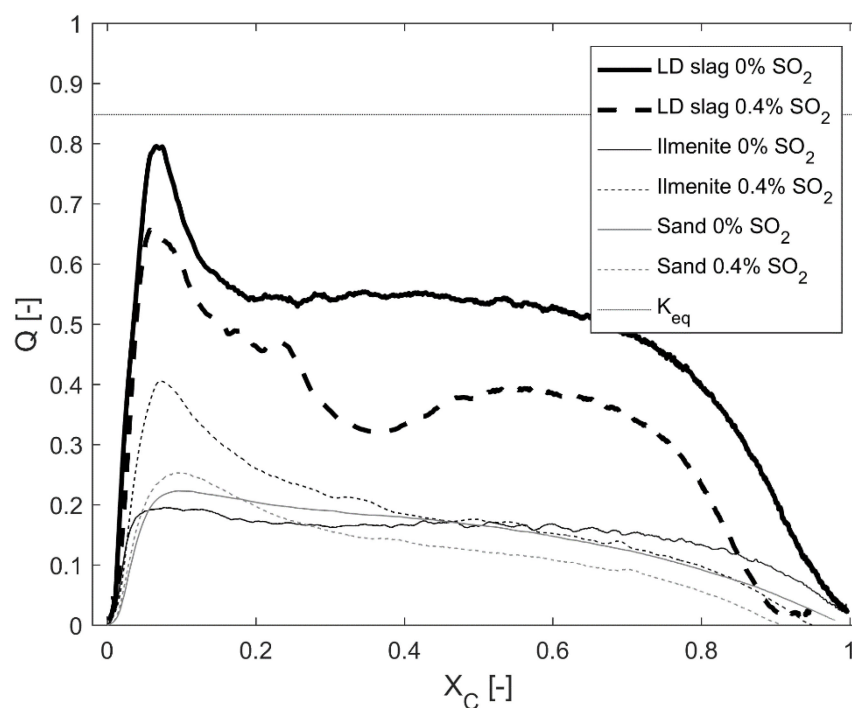


Figure 11. The reaction quotient Q for LD slag, ilmenite, and sand with and without the presence of SO_2 in the fluidization gas plotted against the conversion of the ingoing carbon, X_c . Experiments were performed at $870\text{ }^\circ\text{C}$ using 0.2 g fuel. The dotted horizontal line in the figure is the equilibrium constant K_{eq} for the WGS reaction at $870\text{ }^\circ\text{C}$.

3.3. Benzene Conversion

Conversion of benzene in the presence of SO_2 was investigated for LD slag and ilmenite. The gas composition for the experiments is displayed in Table 4. Benzene was

used in these experiments as a precursor for tars, and it is well known that benzene is one of the most difficult aromatics to convert in thermochemical conversion of biomass. The overall conversion of benzene over the entire cycle can be seen in Figure 12. Here, it should be noticed that the scale of conversion is only zoomed in to 40–60%. The difference with and without SO_2 present is within the error margin for ilmenite. As such, for ilmenite, SO_2 does not affect benzene conversion. For LD slag, a small decrease in reactivity towards benzene in the presence of more SO_2 is observed. However, the experimental results are within the error margins for the experiments. The benzene conversion for LD slag and ilmenite was 50% and 56%, respectively.

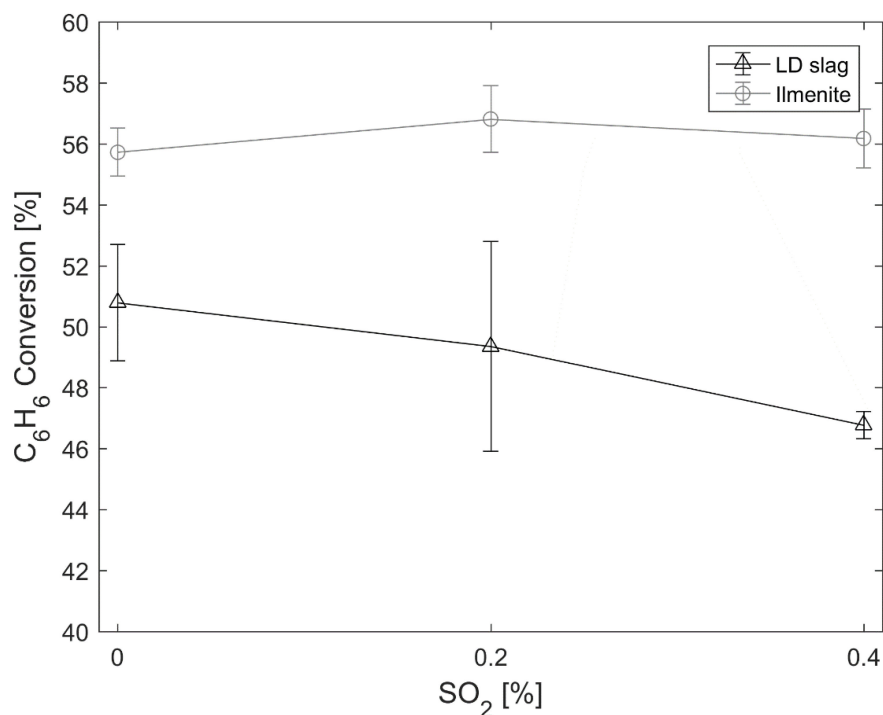


Figure 12. Benzene conversion at 850 °C using LD slag and ilmenite in the presence of SO_2 . Note that the scale of conversion is only between 40% and 60%. See Table 4 for experimental conditions during the reducing phase.

3.4. Sulfur Interaction with LD Slag—Influence of Solid Fuel

Gasification experiments were performed again using the analyzer with a SO_2 detector and the second solid fuel, German wood char. Figure 13 shows the outgoing gases from the char conversion experiments described in Section 2.1 where gasification rate and concentrations are plotted against the conversion of char. However, in comparison to experiments shown in Figure 8, the wood char fuel used contained more volatiles. In addition to this, the curves indicate similar trends for both LD slag and ilmenite with the different fuels. Further comparison of the two different solid biofuels can be seen in the Supplementary Materials with experiments performed with sand.

In the figure, it is clear that SO_2 is interacting differently with LD slag compared to ilmenite. Common to the two materials is that both LD slag and ilmenite have almost no SO_2 released at the beginning of the cycle ($0 < X_c < 0.1$) as the volatiles from the fuel are released. A clear CO peak in Figure 13 indicates the presence and release of volatiles. After the effect of volatiles, ilmenite has a relatively even outgoing concentration of SO_2 during the gasification between $0.1 < X_c < 0.8$, which at the end of the cycle reaches the ingoing concentration of roughly 0.4%. For LD slag, the outgoing SO_2 is much more shifting in relation to char conversion X_c . The SO_2 concentration peaks, together with the peak of the increased gasification rate. The same peak could be observed in Figure 8 with 0.4% SO_2 and LD slag. After this, the SO_2 concentration decreases at $X_c \approx 0.5$, as seen in Figure 13.

This is directly after the peak with CO_2 and the increased gasification rate, and the same time as H_2 starts to increase in Figure 8.

When using Dräger tubes for bag samples of the gas to analyze the H_2S and SO_2 concentration, it was observed that the sulfur balance is not complete when only considering these two sulfur components in the outgoing gases (see Table 6). H_2S concentration was increasing as a function of X_c to reach about 2000 ppm in the outgoing gases around $X_c = 0.5$ for both LD slag and ilmenite. Then, the H_2S concentration decreased while SO_2 was increased.

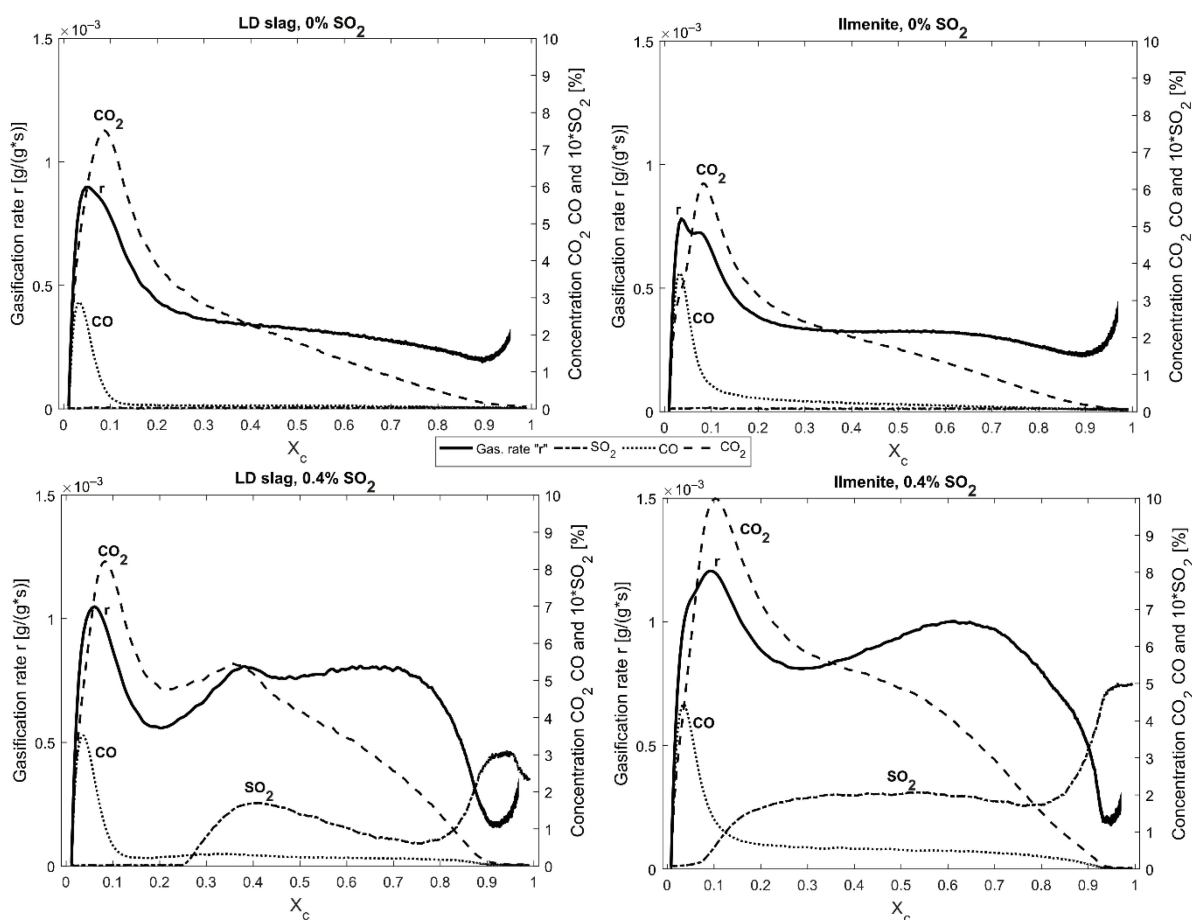


Figure 13. Gasification rate " r " and concentration of outgoing gases and SO_2 in relation to char conversion X_c for LD slag and ilmenite. The two upper figures are without the presence of SO_2 , and the two lower figures are in the presence of 0.4% SO_2 . Note that these experiments are performed with another wood char, German wood char, instead of devolatilized wood pellets, with more volatiles compared to the experiments evaluated in Section 3.1.

It should, however, be noted that the bag sampling method has a very low time resolution. It takes 1 min to fill a bag sample; during this time, X_c increased from 0.08 to 0.29 for the first sampling point of, e.g., LD slag. Then, it took another minute to prepare another bag sample, so the next bag starts at $X_c = 0.44$. Nevertheless, even with the low resolution, it was clear that the sulfur balance is not covered by only H_2S and SO_2 , neither for the oxygen carriers LD slag or ilmenite, nor for sand. In addition to solid interaction, the highly soluble SO_2 is also captured in the condensed water, which has been observed to be slightly acidic and has a sulfurous smell. COS is also known to be a common gasification product [23,48] that could not be measured here. It is also possible and expected from thermodynamic calculations that elementary sulfur is formed via Reaction (R11). Elementary sulfur will condense on the reactor walls that are located at low-temperature areas and in tubes downstream of the main reactor.

Table 6. Result of H₂S and SO₂ concentrations from bag samples extracted during one cycle of gasification of German wood char in the presence of 0.4% SO₂ at 870 °C. Roughly one liter of gas was extracted over 50–60 s, and the average X_c was taken as the mean of the calculated X_c for every bag sample during the extraction period.

LD Slag, 0.4% SO ₂			Ilmenite, 0.4% SO ₂		
Avg. X _c	H ₂ S [ppm]	SO ₂ [ppm]	Avg. X _c	H ₂ S [ppm]	SO ₂ [ppm]
0.15	350	0	0.20	750	500
0.47	2000	400	0.50	2100	400
0.89	1800	1200	0.86	1700	1200
0.92	1000	2200	0.91	750	2800

For LD slag, sulfur was released as SO₂ after the experiments. This was released during the inert purging, after the reducing gasification phase with char and SO₂. This can be seen in Figure 5, where SO₂ can be observed during the inert phase between reduction and oxidation. This was also similar to the gaseous fuel experiments with syngas where SO₂ was released during inert conditions after sulfur was loaded into the structure (see Section 3.5). This sulfur release during the inert phase was only observed for LD slag, not for ilmenite or sand. This suggests that sulfur binds to the Ca in the LD slag, and is then released as SO₂ under inert conditions when the partial pressure of SO₂ is decreased, e.g., via Reaction (R10) if CaS is formed.

When oxidation starts, the concentration of SO₂ is decreased compared to inert conditions. This could indicate that CaS is oxidized partly forming SO₂ (via Reaction (R9)) in addition to CaSO₄ (via Reaction (R8)). Finally, when oxygen passes through the bed, and the oxygen carrier captures most of the oxygen, there is again a small peak of SO₂. This could be from S deposited on the reactor walls above the bed which is oxidized during oxidation. Elemental sulfur is formed via the Claus Reaction (R11) and has been observed as yellow dust on reactor walls in these experiments and previous experiments using other equipment [23].

After gasification experiments with SO₂, an additional reference gasification experiment was executed without SO₂ in the ingoing gases. Here, it was observed that sulfur in the form of SO₂ and H₂S, detected with Dräger tubes, was released with similar concentrations as in previous experiments with SO₂. This suggests that sulfur is bound into the structure. Adding to this, the gasification rate was as high for this cycle as it was when SO₂ was present in the fluidization gas. However, this was not a lasting effect; it only lasted for one cycle. In the next cycle, the rate decreased and returned closer to the experiments without SO₂. This is in correlation with the increased conversion of CO observed in gaseous fuel experiments after sulfur is accumulated in the oxygen carrier presented in Figure 14. Similarly, a lasting increased conversion effect of sulfur has been observed in previous studies with ilmenite [23].

3.5. Sulfur Interaction with LD Slag—Gaseous Fuel

In this section, gaseous experiments were performed, as described in Table 5 in Section 2.2. After activation cycles, 1% SO₂ and syngas (H₂/CO, 50/50) were used to reduce the bed of LD slag at 870 °C. It was observed that the conversion of CO increased in the presence of SO₂. In addition, it was observed that the conversion increased as sulfur accumulated in the sample. This can be seen in Figure 14 for 1% SO₂ compared to no SO₂ mixed with the syngas. It was also observed that a peak of SO₂ was formed when oxygen was introduced to the reactor after the reduction. These peaks further suggest that some sulfur was both accumulated into the structure during the reduction, and also that some of it was released during oxidation or depositions of elementary sulfur. The potential reaction could most likely be SO₂ forming from CaS, according to Reaction (R9).

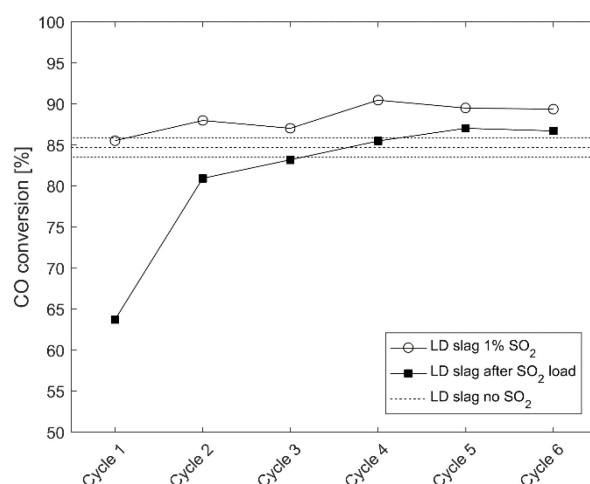


Figure 14. CO conversion for cycles using LD slag as bed material at 870 °C. The horizontal dotted line is the reference with the mean and variance of cycles reduced with 50% syngas (50% CO in H₂) diluted with N₂. Firstly, -○- shows the CO conversion for six cycles reduced with 1% SO₂ and 50% syngas with N₂ as a balance. Here, a slight increase in CO conversion can be observed for every cycle. The sample was then loaded with a high amount of sulfur using 1.5% SO₂ during the oxidation for 90 min. Thereafter, -■- shows the CO conversion rate for the sample reduced using 50% syngas diluted with N₂ for six cycles, the same as the reference experiments. Here, it was observed that the conversion of the first reduction was much lower than in the following cycles where the conversion was similar to the reference or slightly higher.

After the first cycles with sulfur in the reducing gas, sulfur was instead inserted during the oxidation. The particles were “loaded” with SO₂ during 90 min oxidation with an ingoing SO₂ concentration of 1.5%. After 90 min, the outgoing sulfur concentration was just above 1% and still increasing. After this, the particles were again reduced with syngas with no SO₂ in the ingoing gases. A decreased reactivity was observed compared to before the sulfur loading, especially in the first cycles. The reactivity was then increased with every cycle, as can be observed in Figure 14. This decreased reactivity could be associated with the decreased surface area that was measured with BET. In Table 7, the surface area for the particles is displayed under different conditions. Here, it is clear that sulfation decreases the surface area of the particles, indicating blocked pores. However, already after the first reduction, the surface area is increased to almost the same as after activation. Additional reduction cycles did not increase the surface area to a greater extent, as can be seen after a total of seven cycles where the surface area is almost the same as after the first reduction.

Table 7. BET surface area of LD slag particles before and after sulfur loading. It is clear that there is a drop in surface area after SO₂ loading and that the surface area is increased again after reduction cycles.

Sample	BET Surface Area [m ² /g]
LD slag heat treated	1.00 ± 0.004
LD slag after activation	0.83 ± 0.007
LD slag after SO ₂ loading	0.41 ± 0.005
LD slag after SO ₂ loading and reduced once	0.70 ± 0.002
LD slag after SO ₂ loading and 7 reduction cycles	0.72 ± 0.007

After the loading of sulfur, sulfur was detected as SO₂ during the reduction, but also during the inert phase after the reduction (see Figure 15). The amount of outgoing SO₂ decreased as a function of cycles, as is clarified with an arrow in the figure. Moreover, when

oxygen was introduced, a small extra peak of SO_2 was followed by a fast decline in SO_2 concentration. This can be seen in the inert oxidation shift at around 400 s in Figure 15. It was noted that O_2 was detected after SO_2 had declined to zero. This is in alignment with previous studies where CaS has been formed during the reduction and then reacted with CaSO_4 during the inert period of the experiments, according to Reaction (R10) [27], and formed SO_2 and CaO . Unfortunately, in XRD, only CaSO_4 could be identified as a sulfur-containing phase for the reduced sample, which is the same as for the oxidized sample. This could indicate that CaS is under the detection limit for XRD. The reduced sample was quenched directly after the reduction during inert conditions; nevertheless, no CaS could be observed. Moreover, with SEM-EDX, it could be observed that sulfur was located together with calcium (see Figure 16). Sulfur was not present in the areas containing Si and Ca, nor Ca and Fe. This suggests that known structures in LD slag such as calcium silicates ($(\text{CaO})_x\text{SiO}_2$) and Srebrodolskite ($\text{Ca}_2\text{Fe}_{2-x}\text{B}_x\text{O}_5$ — $B = \text{Mg, Mn, Si}$) do not bind sulfur into the structure. Therefore, it is most likely that lime (CaO) present in the structure at a few percentage [15] was interacting with the sulfur. Sulfur, together with Ca, was mainly at the surface of the particles, but also throughout the entire cross-section.

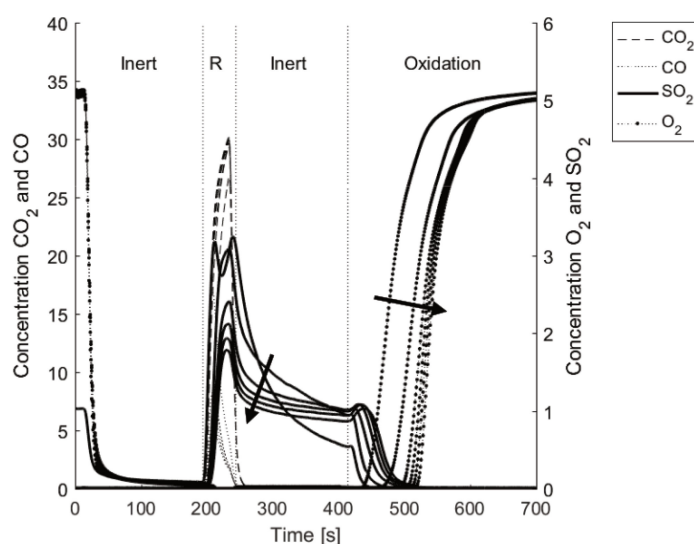


Figure 15. The concentration of outgoing gases for reduction cycles after LD slag has been loaded with SO_2 during oxidation. Arrows show development after every cycle; decreased SO_2 out from every cycle and increased time for oxygen breakthrough. Dotted vertical lines indicate the atmospheric conditions in every cycle; “R” is reduction using syngas.

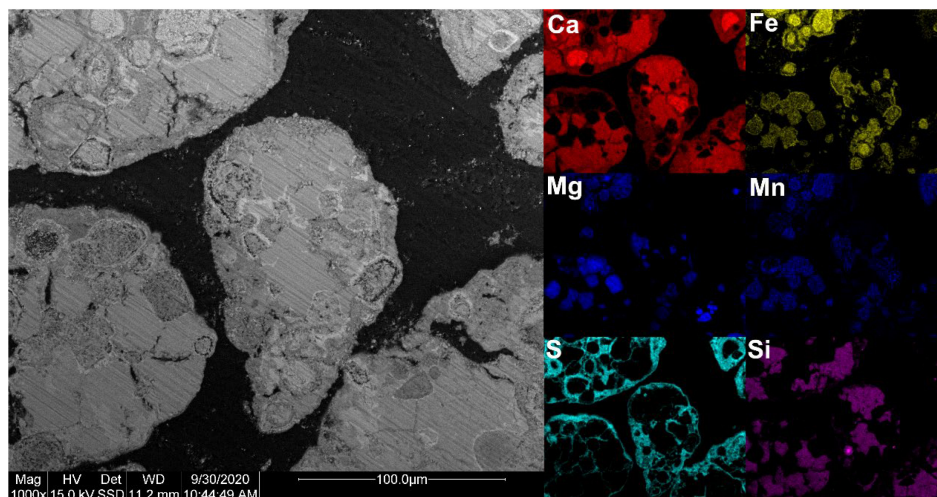


Figure 16. SEM-EDX image of LD slag that has been loaded with SO_2 and reduced once at 870°C .

4. Discussion

It is clear from these experiments that the possible reaction paths for sulfur are many and complex. In addition to gaseous species that are not measured, such as COS and SO_3 , some sulfur species are lost in the condensed water in the gas treatment system, and most likely elemental sulfur is deposited in the colder areas after the reactor. Additionally, the interaction with calcium in LD slag adds more complexity. Therefore, a total sulfur balance over the system is in this work not possible.

A summary of the reaction paths and effects of sulfur on LD slag can be seen in Figure 17. There are three important reactions path that are emphasized in the figure, from the left: (i) formation of CaSO_4/CaS ; (ii) surface-active sulfur increasing the reaction rate towards, e.g., CO; and (iii) increased gasification rate of char due to oxygen transfer via SO_2 from OC to char.

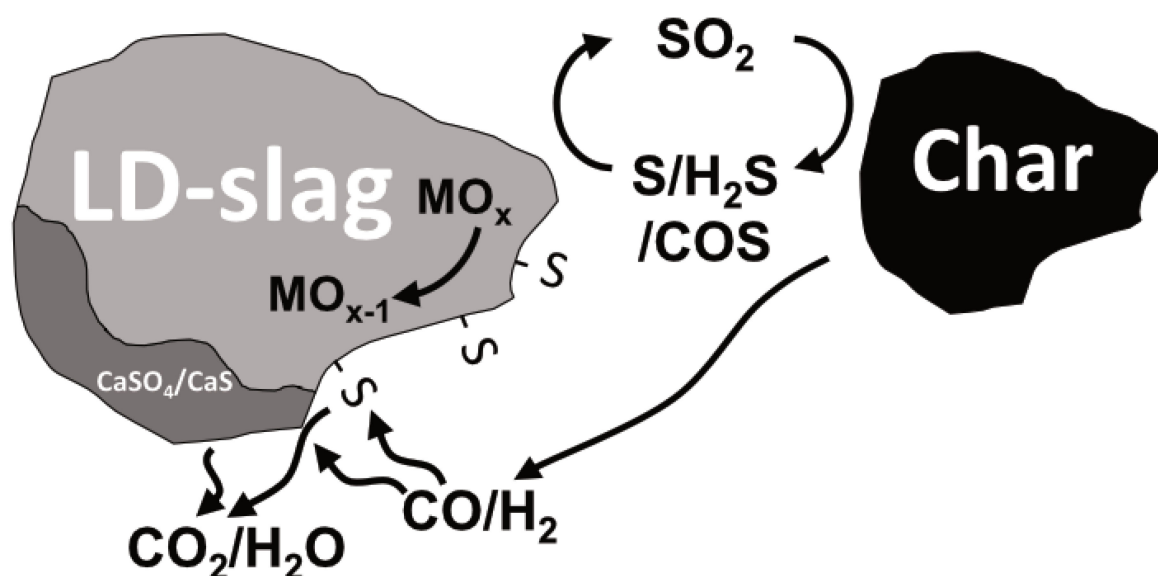


Figure 17. A graphical summary of reaction paths involving sulfur suggested in the discussion section.

For LD slag, one of the significant interactions of CaO with SO_2 is the formation of CaS and CaSO_4 . This was expected from the thermodynamic calculations presented in Figures 2 and 3. CaO is a known catalyst and can explain why LD slag has a reaction quotient Q closer to the equilibrium compared to the other tested materials in Figure 11 [35,36,49]. Forming CaS or CaSO_4 , less CaO in the bed can catalyse the WGS reaction. As could be observed in Figure 11, the sulfur content in the ingoing gas decreased the reaction quotient Q for LD slag. The same effect of sulfur could not be observed for the other tested materials. However, this effect could only be detected at 870 °C. At 970 °C, no significant effect of sulfur regarding the reaction quotient Q could be observed. This suggests that neither CaS nor CaSO_4 was formed at this partial pressure of SO_2 , as compared with Figure 2 to see the effect of temperature on equilibrium for the CaS/ CaSO_4 /CaO system.

SO_2 and H_2S in the outgoing gas are highly affected by the bed material used. This can be observed in Figure 13 and Table 6. For both ilmenite and LD slag, the initial part of the char conversion ($0 < X_c < 0.1$) was characterized by high amounts of mostly H_2S that were detected with Dräger tubes. Almost no SO_2 was present in this initial phase. This is most likely due to the high amount of H_2 that was released with the volatiles from the char. Likely, H_2 reacts with SO_2 , forming H_2S that is more thermodynamic stable with high amounts of H_2 . It is after this initial char conversion ($X_c > 0.1$) where LD slag and ilmenite perform differently. For ilmenite, the outgoing concentration of H_2 is stable, as well as the SO_2 , until the solid fuel is fully converted. However, when LD slag is reduced, more H_2 is formed due to water splitting [36]. This was observed as a simultaneous increase in H_2 concentration in Figure 8, and as a decrease in SO_2 in Figure 13. Thermodynamic

calculations using the concentrations in these figures also suggest the formation of H_2S . The presence of H_2S and SO_2 in the same gas mixture enables elemental sulfur to be formed according to the Claus reaction (Reaction (R11)). Elemental sulfur can stick to the walls of the reactor cooler areas. When oxidation of the oxygen carrier starts, all oxygen is absorbed into the bed. When oxygen breaks through, it might react with the sulfur that is stuck to the walls. This could be the reason for the SO_2 peak that occurs in Figure 14 just before the oxygen breakthrough.

Sulfur was observed to absorb into the LD slag. Loading a large amount of sulfur over a long period of time under oxidative conditions resulted in a clear decrease in surface area and reactivity (see Table 5 and Figure 14). Parts of the sulfur that were loaded into the LD slag particle were then observed to be released during the following reduction cycles without SO_2 in the ingoing gas. This could mean that CaS forms during the reduction and then reacts with the $CaSO_4$, according to Reaction (R10). This reaction path is also strengthened from the observation of the SO_2 concentration profile over the cycle, seen in Figure 15. SO_2 concentration in the outgoing gases peaks during the reduction and starts to decrease when the inert phase starts. However, the SO_2 concentration drops first to zero, then oxidation starts and all remaining CaS is oxidized to $CaSO_4$. Even after seven reduction cycles, the SO_2 release during reduction was significant, and sulfur-containing phases were detected in the cross-section of the particles using SEM-EDX. Only $CaSO_4$, and no CaS, could be detected in these samples using XRD. If CaS was formed, the amounts were very small and could be expected to react fast with $CaSO_4$ that is likely closely located in the same calcium-containing phases in the LD slag. Further, the SO_2 peak that was observed directly when oxygen was introduced indicates that CaS was formed and partly oxidized to SO_2 , according to Reaction (R9). This occurred in gaseous fuel experiments after and before the loading of sulfur in the sample. Additionally, in gasification experiments, sulfur interacted accordingly with sulfur release during inert phases and a small release when oxygen was introduced (see, e.g., Figure 5). In similar experiments with ilmenite, this behavior was not observed. Interpolating this behavior to an industrial scale indicates that SO_2 could be released in loop seals and in the air reactor in a CLC or CLG plant using LD slag as an oxygen carrier. However, when using biofuel as fuel, calcium is known to be deposited on ash layers of ilmenite and inside the structure as well [11,50]. For ilmenite, these ash layers have been observed to be important for the sulfur interaction [28], since calcium is identified as the main component for this interaction path that might transport sulfur to the loop seal or air reactor. Further studies including calcium from the fuel are required to estimate the importance of the ingoing calcium in LD slag compared to ilmenite in a full-scale application.

In comparison to previous studies where LD slag has been used in a boiler [15], it can be observed that the sulfur from the fuel was located on the surface of the particles. In this study, it was observed that sulfur was present throughout the entire sample (see Figure 16). This could be due to the lack of available calcium from the fuel ash that can form on the surface, or because the amount of sulfur introduced to the sample was high, resulting in saturation on the surface. From the SEM-EDX analysis, no migration limitation/border of sulfur could be observed, indicating an inward-going migration of sulfur in the cross-section. However, since LD slag is so heterogeneous, a clear migration trend is hard to detect. From previous studies, it has been found that sulfur penetration can increase significantly under alternating oxidizing and reducing conditions [21].

The effect of sulfur towards reactions of larger hydrocarbons was tested using benzene. For the conversion of benzene, the investigated concentrations of SO_2 have minimal or no effect on the conversion. It is important to note that the particles were oxidized prior to the benzene experiments. Therefore, the extra oxygen provided by the small amount of SO_2 should have minimal effect. This suggests that the oxidation reaction towards benzene is unaffected by sulfur or the reactions with LD slag forming CaS or $CaSO_4$. However, the minor decrease in reactivity that can be seen comparing 0% to 0.4% SO_2 could be due to the decreased surface area of the particles. This means that the same mechanism

observed to increase the conversion of methane in the presence of sulfur observed in previous studies [23] might not be applicable for benzene. Since no change is observed, SO_2 does not seem to affect the rate-limiting step of activating benzene, i.e., destabilizing the benzene ring [51].

The increased reactivity of LD slag with SO_2 could be partly be a result of the oxygen transport from CaSO_4 forming CaS ; i.e., a new oxygen-carrying phase in LD slag is formed [52]. However, since ilmenite does not contain Ca, this is not contributing to the changed reactivity of ilmenite; rather, this occurs by the direct effect of oxygen transfer from SO_2 reduced to H_2S . However, the direct addition of SO_2 as a source of oxygen can only have a limited effect due to the low concentrations. This is obvious from the experiments with sand where only H_2S could be detected during the main part of gasification and the oxygen provided by SO_2 is consumed during the gasification with limited effect on the overall gasification rate. This indicates that sulfur does not interact with the char directly to increase the reaction rate, in the same manner as sulfur does not interact with the destabilization of the benzene ring. Therefore, another mechanism is expected to be the origin of the observed reaction rate for both the investigated oxygen carriers.

Hydrogen inhibition of char during gasification is a well-known effect that decreases the gasification rate [53–55]. This has also been observed to be important for LD slag, since H_2 is generated from water-splitting of steam when LD slag is reduced and this affects the gasification rate [36]. One hypothesis of the increased gasification rate observed in this study could be that SO_2 reacts with H_2 , forming H_2S , and that this decreases the H_2 concentration, and ultimately, the hydrogen inhibition. It is unlikely, however, that this effect is dominant. In the sand samples, there is a small effect on the H_2 concentration and the H_2/CO ratio (see Figure 10 and Supplementary Materials figures). However, the effect of the gasification rate is negligible for sand. Moreover, for LD slag and ilmenite, there is an effect on the H_2/CO ratio at 870 °C but not at 970 °C; still, the gasification rate is increased in the presence of SO_2 at both temperatures. Further, the increased CO conversion observed in this study for LD slag and the increased methane conversion for ilmenite with sulfur [23] could not be related to hydrogen inhibition since no char is present.

More likely is that sulfur interacts as an intermediate to transport oxygen from the oxygen carrier to the char. SO_2 reacts with char forming H_2S , COS , or S , that then, in turn, is oxidized to SO_2 by the oxygen carrier. Thermodynamic calculations regarding the conversion of char from SO_2 compared to H_2S can be seen in the Supplementary Materials. Similar reaction schemas have been suggested previously for the observed increased reaction rate towards petroleum coke of iron-based oxygen carriers [43]. This could also explain why the experiments with sand did not show any significant gasification rate change. In sand, the oxygen from SO_2 can only be transferred once to the char and then is not oxidized again. This would explain the mixture of H_2S and SO_2 in the outgoing gases during the char conversion for LD slag and ilmenite (Figure 13 and Table 6) compared to sand (see Supplementary Materials). The oxygen transport also increases with the amount of SO_2 added, which the increased gasification rate seen in Figure 7 at both 870 °C and 970 °C indicates. Furthermore, the absorbed sulfur that was released in the following experiments without SO_2 addition also increased the gasification rate. This also suggests that it is the gas phase sulfur transporting the oxygen.

The characteristic peak at $X_c \approx 0.25$ with the increased gasification rate during the solid fuel experiments with LD slag is seen in Figures 6, 8 and 13. This type of peak was not observed at 970 °C, suggesting that this correlated to the sulfur interaction with calcium in the LD slag. In Figures 8 and 13, it can be observed that the peak is correlated to low H_2 and high SO_2 . High SO_2 could be correlated to a phase change that increases the amount of sulfur in the gas phase. Compared with the phase diagram in Figure 2, at a lower partial pressure of SO_2 , changing the partial pressure of H_2 converts CaS to CaSO_4 via the formation of CaO . Before the peak, it can be observed in Table 6 that the first bag sample for LD slag contained much less $\text{H}_2\text{S} + \text{SO}_2$ than ilmenite. This could suggest that sulfur is first absorbed into the structure, and then at one point partly released when the LD slag

is reduced to a specific degree. This release causes an increased gasification rate and an observed high SO_2 concentration.

Another hypothesis for the increased reaction rate towards CO and char could be that sulfur is surface-active. It is known that sulfur affects catalysts both as poison and promoters [56]. In addition, reactions including iron and iron oxide are known to be promoted by low amounts of sulfur [57,58]. Since the effect of sulfur seems to be lasting (at least for a few cycles) both for ilmenite [23] and LD slag, it could be suspected that surface reactions are promoted by low amounts of sulfur. Small amounts of sulfur have also been observed to be absorbed on the surface of iron oxygen carriers [59] and in other studies to increase reactivity towards coal pyrolysis gas [38]. This could explain the increased reactivity towards gaseous species, and also suggest that the catalytic cracking of benzene is not active with the same reaction mechanism affected by sulfur. However, the solid-solid reaction between oxygen carrier and char has been expected to be low in fluidized beds [9,60]. Nevertheless, studies of iron oxygen carriers in non-fluidized beds have indicated that the solid-solid interaction might be of significance due to the low reactivity towards reducing gasses for iron compared to, e.g., Ni [61–63]. Sulfur attached to the surface iron of LD slag and ilmenite might therefore increase the gasification rate of the char. This could also explain the lack of effect that sulfur has on sand, since sand cannot transport oxygen via a solid-solid reaction with the char. Moreover, since ilmenite has more iron at the surface after activation [12], more sulfur can interact with the surface iron. This could be contributing to the relatively higher gasification rate increase observed for ilmenite compared to LD slag in the presence of sulfur. In the experiments for this study, the fluidization velocity is relatively low, roughly four times the minimum fluidization velocity at 870 °C. Even so, this low fluidization velocity should make the solid-solid interactions less pronounced.

5. Conclusions

This study is based on the experiments performed in a fluidized batch reactor using LD slag and ilmenite as a bed material compared to sand. Both solid fuel experiments utilizing wood char and gaseous fuels such as CO and benzene were used. Sulfur was inserted as SO_2 with concentrations up to 0.4% in the fluidization gas. It was found that even low amounts of SO_2 have a significant effect on how these oxygen carriers convert solid fuels. It was concluded that:

- SO_2 is partly interacting with LD slag by reacting with the calcium phases in the particle, forming CaSO_4 and most likely CaS;
- The calcium interaction of SO_2 had a negative effect on the catalytic properties of LD slag on the WGS reaction at a lower operating temperature of around 870 °C;
- The interaction between SO_2 and calcium can result in a decreased surface area on the particles. However, this is not a permanent effect. If the sulfur partial pressure is decreased, the surface area is again increased after a few reduction cycles.
- Even small amounts of sulfur can increase the reactivity towards CO. Even if no SO_2 is introduced with the fuel, sulfur that was previously bound in the LD slag results in a higher reaction rate compared to only activated bed material;
- The formation of CaS can result in sulfur being released as SO_2 in loop seals and air reactors in a CLC or CLG boiler;
- The gasification rate of wood char increased for both LD slag and ilmenite, however less for LD slag, when adding SO_2 . This increased gasification rate was not related to the extra oxygen provided by the SO_2 ;
- SO_2 could partly affect the inhibiting effects of hydrogen for the oxygen carriers;
- Sulfur is expected to act as an intermediate transporting oxygen from the oxygen carrier to char, and then back to the oxygen carrier to be oxidized again.

Supplementary Materials: The following supporting information can be downloaded at: <https://www.mdpi.com/article/10.3390/en15165922/s1>, Figure S1. Gasification experiments with sand and devolatilized wood char at 870 °C. Figure S2. Gasification experiments with sand and german wood char at 870 °C. Here a significant volatiles peak can be seen comparing Figure S1 and Figure S2 besides that the reactivity of the devolatilized wood char is slightly higher. Figure S3. Gasification experiments with sand and german wood char at 870 °C using the gas analyzer measuring SO₂ in the outgoing gases. Figure S4. Gasification rate "r" and concentration of outgoing gases as a function of X_c for LD slag and Ilmenite at 970 °C. The two upper figures are without the presence of SO₂ and the two lower figures are for experiments using 0.4% SO₂. Curves are selected as the middle curve within the max and minimum gasification rate "r" displayed as gray areas in Figure 6. Devolatilized wood pellets were used as fuel for these experiments. Figure S5. The reaction quotient Q for LD slag, ilmenite and sand with and without the presence of SO₂ in the fluidization gas plotted against the conversion of the ingoing carbon, X_c. Experiments were performed at 970 °C using 0.2 g fuel. The dotted horizontal line in the figure is the equilibrium constant K_{eq} for the WGS reaction at 970 °C. Figure S6. Equilibrium of sulphur species as a function of ingoing amount of H₂. Equilibrium is based on an 0.05 mole SO₂ and 0.5 mole H₂O. It is very simplified to just show the effect of H₂ on the conversion of SO₂ to H₂S at 850 °C. If including CO and CO₂ WGS will generate H₂ and this will form H₂S even with no ingoing H₂. Figure S7. Equilibrium of 0.5 mole Ca₂Fe₂O₅ with 0.05 mole SO₂ + 0.5 mole H₂O as a function of mole H₂ at 850 °C. This indicates that CaSO₄ and CaS can be formed to some extent from Ca₂Fe₂O₅ in presence of sulphur. Figure S8. Equilibrium of 0.5 mole Ca₂SiO₄ with 0.05 mole SO₂ + 0.5 mole H₂O as a function of mole H₂ at 850 °C. This indicates that CaSO₄ and CaS can be formed to some extent from calcium silicates in presence of sulphur. Figure S9. Thermodynamic calculations regarding formation of elementary sulfur that are formed from the Claus reaction when H₂S and SO₂ are present in a gas. Figure S10. Thermodynamic calculations regarding reactions of SO₂ and C as a function of SO₂ at 850 °C. SO₂ are expected to increase the conversion of carbon to both CO and sulfur containing carbon species like CS₂ and COS. Figure S11. Thermodynamic calculations regarding reactions of H₂S and C as a function of H₂S at 850 °C. No conversion of the carbon is expected to occur.

Author Contributions: Conceptualization, All authors.; methodology, F.H. and H.L.; software, F.H.; validation, All authors.; formal analysis, F.H.; investigation, F.H.; resources, H.L.; data curation, F.H.; writing—original draft preparation, F.H.; writing—review and editing, All authors; visualization, F.H.; supervision, T.M. and H.L.; project administration, H.L.; funding acquisition, H.L. All authors have read and agreed to the published version of the manuscript.

Funding: This research is funded by ÅForsk (20-269).

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Acknowledgments: This work was financed by ÅForsk (20-269). The LD slag bed material was provided by SSAB.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Adanez, J.; Abad, A.; Garcia-Labiano, F.; Gayan, P.; De Diego, L.F. Progress in Chemical-Looping Combustion and Reforming Technologies. *Prog. Energy Combust. Sci.* **2012**, *38*, 215–282. [[CrossRef](#)]
2. Thunman, H.; Lind, F.; Breitholtz, C.; Berguerand, N.; Seemann, M. Using an Oxygen-Carrier as Bed Material for Combustion of Biomass in a 12-MWth Circulating Fluidized-Bed Boiler. *Fuel* **2013**, *113*, 300–309. [[CrossRef](#)]
3. Matzen, M.; Pinkerton, J.; Wang, X.; Demirel, Y. Use of Natural Ores as Oxygen Carriers in Chemical Looping Combustion: A Review. *Int. J. Greenh. Gas Control* **2017**, *65*, 1–14. [[CrossRef](#)]
4. Mendiara, T.; Gayán, P.; García-Labiano, F.; De Diego, L.F.; Pérez-Astray, A.; Izquierdo, M.T.; Abad, A.; Adánez, J. Chemical Looping Combustion of Biomass: An Approach to BECCS. *Energy Procedia* **2017**, *114*, 6021–6029. [[CrossRef](#)]
5. Rydén, M.; Lyngfelt, A.; Langørgen, O.; Larring, Y.; Brink, A.; Teir, S.; Havåg, H.; Karmhagen, P. Negative CO₂ Emissions with Chemical-Looping Combustion of Biomass—A Nordic Energy Research Flagship Project. *Energy Procedia* **2017**, *114*, 6074–6082. [[CrossRef](#)]
6. Adánez, J.; De Diego, L.F.; García-Labiano, F.; Gayán, P.; Abad, A.; Palacios, J.M. Selection of Oxygen Carriers for Chemical-Looping Combustion. *Energy Fuels* **2004**, *18*, 371–377. [[CrossRef](#)]

7. Hossain, M.M.; de Lasa, H.I. Chemical-Looping Combustion (CLC) for Inherent CO₂ Separations—A Review. *Chem. Eng. Sci.* **2008**, *63*, 4433–4451. [[CrossRef](#)]
8. Idziak, K.; Czakiert, T.; Krzywanski, J.; Zylka, A.; Kozłowska, M.; Nowak, W. Safety and Environmental Reasons for the Use of Ni-, Co-, Cu-, Mn- and Fe-Based Oxygen Carriers in CLC/CLOU Applications: An Overview. *Fuel* **2020**, *268*, 117245. [[CrossRef](#)]
9. Leion, H.; Mattisson, T.; Lyngfelt, A. Solid Fuels in Chemical-Looping Combustion. *Int. J. Greenh. Gas Control* **2008**, *2*, 180–193. [[CrossRef](#)]
10. Pröll, T.; Mayer, K.; Bolhàr-Nordenkamp, J.; Kolbitsch, P.; Mattisson, T.; Lyngfelt, A.; Hofbauer, H. Natural Minerals as Oxygen Carriers for Chemical Looping Combustion in a Dual Circulating Fluidized Bed System. *Energy Procedia* **2009**, *1*, 27–34. [[CrossRef](#)]
11. Corcoran, A.; Marinkovic, J.; Lind, F.; Thunman, H.; Knutsson, P.; Seemann, M. Ash Properties of Ilmenite Used as Bed Material for Combustion of Biomass in a Circulating Fluidized Bed Boiler. *Energy Fuels* **2014**, *28*, 7672–7679. [[CrossRef](#)]
12. Adánez, J.; Cuadrat, A.; Abad, A.; Gayán, P.; Diego, L.F.D.; García-Labiano, F. Ilmenite Activation during Consecutive Redox Cycles in Chemical-Looping Combustion. *Energy Fuels* **2010**, *24*, 1402–1413. [[CrossRef](#)]
13. Jerndal, E.; Leion, H.; Axelsson, L.; Ekvall, T.; Hedberg, M.; Johansson, K.; Källén, M.; Svensson, R.; Mattisson, T.; Lyngfelt, A. Using Low-Cost Iron-Based Materials as Oxygen Carriers for Chemical Looping Combustion Chemical Looping—An Alternative Concept for Efficient and Clean Use of Fossil Resources La Boucle Chimique-Un Concept Alternatif Pour Un Usage Propre et Efficace Des. *Oil Gas Sci. Technol. Rev. IFP Energ. Nouv.* **2011**, *66*, 235–248. [[CrossRef](#)]
14. Rydén, M.; Hanning, M.; Lind, F. Oxygen Carrier Aided Combustion (OCAC) of Wood Chips in a 12 MWth Circulating Fluidized Bed Boiler Using Steel Converter Slag as Bed Material. *Appl. Sci.* **2018**, *8*, 2657. [[CrossRef](#)]
15. Hildor, F.; Mattisson, T.; Leion, H.; Linderholm, C.; Rydén, M. Steel Converter Slag as an Oxygen Carrier in a 12 MWth CFB Boiler—Ash Interaction and Material Evolution. *Int. J. Greenh. Gas Control* **2019**, *88*, 321–331. [[CrossRef](#)]
16. Mattisson, T.; Hildor, F.; Li, Y.; Linderholm, C. Negative Emissions of Carbon Dioxide through Chemical-Looping Combustion (CLC) and Gasification (CLG) Using Oxygen Carriers Based on Manganese and Iron. *Mitig. Adapt. Strateg. Glob. Chang.* **2019**, *25*, 497–517. [[CrossRef](#)]
17. Moldenhauer, P.; Linderholm, C.; Rydén, M.; Lyngfelt, A. Avoiding CO₂ Capture Effort and Cost for Negative CO₂ Emissions Using Industrial Waste in Chemical-Looping Combustion/Gasification of Biomass. *Mitig. Adapt. Strateg. Glob. Chang.* **2019**, *25*, 1–24. [[CrossRef](#)]
18. Zevenhoven, M.; Yrjas, P.; Hupa, M. 14 Ash-forming matter and ash-related problems. In *Handbook of Combustion Volume 4: Solid Fuels*; Lackner, M., Winter, F., Agarwal, A.K., Eds.; WILEY-VCH Verlag GmbH & Co. KgaA: Weinheim, Germany, 2010; pp. 493–531; ISBN 978-3-527-32449-1.
19. Kassman, H.; Bäfver, L.; Åmand, L.E. The Importance of SO₂ and SO₃ for Sulphation of Gaseous KCl—An Experimental Investigation in a Biomass Fired CFB Boiler. *Combust. Flame* **2010**, *157*, 1649–1657. [[CrossRef](#)]
20. Kassman, H.; Normann, F.; Åmand, L.-E. The Effect of Oxygen and Volatile Combustibles on the Sulphation of Gaseous KCl. *Combust. Flame* **2013**, *160*, 2231–2241. [[CrossRef](#)]
21. Mattisson, T.; Lyngfelt, A. Reaction between Sulfur Dioxide and Limestone under Periodically Changing Oxidizing and Reducing Conditions—Effect of Cycle Time. *Energy Fuels* **1998**, *12*, 905–912. [[CrossRef](#)]
22. Wang, B.; Yan, R.; Lee, D.H.; Liang, D.T.; Zheng, Y.; Zhao, H.; Zheng, C. Thermodynamic Investigation of Carbon Deposition and Sulfur Evolution in Chemical Looping Combustion with Syngas. *Energy Fuels* **2008**, *22*, 1012–1020. [[CrossRef](#)]
23. Moldenhauer, P.; Rydén, M.; Mattisson, T.; Younes, M.; Lyngfelt, A. The Use of Ilmenite as Oxygen Carrier with Kerosene in a 300W CLC Laboratory Reactor with Continuous Circulation. *Appl. Energy* **2013**, *113*, 1846–1854. [[CrossRef](#)]
24. Forero, C.R.; Gayán, P.; García-Labiano, F.; de Diego, L.F.; Abad, A.; Adánez, J. Effect of Gas Composition in Chemical-Looping Combustion with Copper-Based Oxygen Carriers: Fate of Sulphur. *Int. J. Greenh. Gas Control* **2010**, *4*, 762–770. [[CrossRef](#)]
25. Adánez-Rubio, I.; Abad, A.; Gayán, P.; García-Labiano, F.; De Diego, L.F.; Adánez, J. The Fate of Sulphur in the Cu-Based Chemical Looping with Oxygen Uncoupling (CLOU) Process. *Appl. Energy* **2013**, *113*, 1855–1862. [[CrossRef](#)]
26. Ma, J.; Mei, D.; Wang, C.; Tian, X.; Liu, Z.; Zhao, H. Sulfur Fate during In-Situ Gasification Chemical Looping Combustion (IG-CLC) of Coal. *Chem. Eng. J.* **2021**, *406*, 126773. [[CrossRef](#)]
27. Arjmand, M.; Kooiman, R.F.; Rydén, M.; Leion, H.; Mattisson, T.; Lyngfelt, A. Sulfur Tolerance of Ca_xMn_{1-x}YMyO_{3-δ} (M = Mg, Ti) Perovskite-Type Oxygen Carriers in Chemical-Looping with Oxygen Uncoupling (CLOU). *Energy Fuels* **2014**, *28*, 1312–1324. [[CrossRef](#)]
28. Vigoureux, M.; Leffler, T.; Knutsson, P.; Lind, F. Sulfur Capture and Release by Ilmenite Used as Oxygen Carrier in Biomass Combustor. *Fuel* **2022**, *309*, 121978. [[CrossRef](#)]
29. Montagna, J.C.; Lenc, J.F.; Vogel, G.J.; Jonke, A.A. Regeneration of Sulfated Dolomite from a Coal-Fired FBC Process by Reductive Decomposition of Calcium Sulfate in a Fluidized Bed. *Ind. Eng. Chem. Process Des. Dev.* **1977**, *16*, 230–236. [[CrossRef](#)]
30. Jamil, R.; Ming, L.; Jamil, I.; Rizwan, J. Application and Development Trend of Flue Gas Desulfurization (FGD) Process: A Review. *Int. J. Innov. Appl. Stud.* **2013**, *4*, 286–297.
31. Luo, M.; Zhou, L.; Wang, C.; Kuang, C. The evolution and desulfurization of sulfur in chemical looping combustion of coal. In *Energy Sources, Part A: Recovery, Utilization, and Environmental Effects*; Taylor & Francis: Abingdon, UK, 2021; pp. 1–12. [[CrossRef](#)]
32. Westmoreland, P.R.; Harrison, D.P. Evaluation of Candidate Solids for High-Temperature Desulfurization of Low-Btu Gases. *Environ. Sci. Technol.* **1976**, *10*, 659–661. [[CrossRef](#)]

33. Lyngfelt, A.; Leckner, B. SO₂ Capture Fluidised-Bed Boilers: Re-Emission of SO₂ Due to Reduction of CaSO₄. *Chem. Eng. Sci.* **1988**, *44*, 207–213. [[CrossRef](#)]
34. Wang, P.; Means, N.; Shekhawat, D.; Berry, D.; Massoudi, M. Chemical-Looping Combustion and Gasification of Coals and Oxygen Carrier Development: A Brief Review. *Energies* **2015**, *8*, 10605–10635. [[CrossRef](#)]
35. Teyssié, G.; Leion, H.; Schwebel, G.L.; Lyngfelt, A.; Mattisson, T. Influence of Lime Addition to Ilmenite in Chemical-Looping Combustion (CLC) with Solid Fuels. *Energy Fuels* **2011**, *25*, 3843–3853. [[CrossRef](#)]
36. Hildor, F.; Leion, H.; Linderholm, C.J.; Mattisson, T. Steel Converter Slag as an Oxygen Carrier for Chemical-Looping Gasification. *Fuel Process. Technol.* **2020**, *210*, 106576. [[CrossRef](#)]
37. Fernández, M.J.; Lyngfelt, A.; Steenari, B.M. Reaction between Limestone and SO₂ under Conditions Alternating between Oxidizing and Reducing. The Effect of Short Cycle Times. *Energy Fuels* **2000**, *14*, 654–662. [[CrossRef](#)]
38. Tsedenbal, B.; Kannari, N.; Sato, K.; Shirai, H.; Takarada, T. Effect of Hydrogen Sulfide on the Combustion Reactivity of Ilmenite Ores with Coal Volatiles under Steam Reforming. *Energy Fuels* **2020**, *34*, 9862–9871. [[CrossRef](#)]
39. Leion, H.; Frick, V.; Hildor, F. Experimental Method and Setup for Laboratory Fluidized Bed Reactor Testing. *Energies* **2018**, *11*, 2505. [[CrossRef](#)]
40. Störner, F.; Hildor, F.; Leion, H.; Zevenhoven, M.; Hupa, L.; Rydén, M.; Eliasson Störner, F.; Hildor, F.; Leion, H.; Zevenhoven, M.; et al. Potassium Ash Interactions with Oxygen Carriers Steel Converter Slag and Iron Mill Scale in Chemical-Looping Combustion of Biomass—Experimental Evaluation Using Model Compounds. *Energy Fuels* **2020**, *34*, 2304–2314. [[CrossRef](#)]
41. Monshi, A.; Asgarani, M.K. Producing Portland Cement from Iron and Steel Slags and Limestone. *Cem. Concr. Res.* **1999**, *29*, 1373–1377. [[CrossRef](#)]
42. Corcoran, A.; Knutsson, P.; Lind, F.; Thunman, H. Comparing the Structural Development of Sand and Rock Ilmenite during Long-Term Exposure in a Biomass Fired 12 MWth CFB-Boiler. *Fuel Process. Technol.* **2018**, *171*, 39–44. [[CrossRef](#)]
43. Leion, H.; Mattisson, T.; Lyngfelt, A. The Use of Petroleum Coke as Fuel in Chemical-Looping Combustion. *Fuel* **2007**, *86*, 1947–1958. [[CrossRef](#)]
44. Azimi, G.; Keller, M.; Mehdipoor, A.; Leion, H. Experimental Evaluation and Modeling of Steam Gasification and Hydrogen Inhibition in Chemical-Looping Combustion with Solid Fuel. *Int. J. Greenh. Gas Control* **2012**, *11*, 1–10. [[CrossRef](#)]
45. Moe, J.M. Design of Water-Gas Shift Reactors. *Chem. Eng. Prog.* **1962**, *58*, 33–36.
46. Bustamante, F.; Enick, R.M.; Cugini, A.V.; Killmeyer, R.P.; Howard, B.H.; Rothenberger, K.S.; Ciocco, M.V.; Morreale, B.D.; Chattopadhyay, S.; Shi, S. High-Temperature Kinetics of the Homogeneous Reverse Water-Gas Shift Reaction. *AIChE J.* **2004**, *50*, 1028–1041. [[CrossRef](#)]
47. Keller, M.; Leion, H.; Mattisson, T.; Thunman, H. Investigation of Natural and Synthetic Bed Materials for Their Utilization in Chemical Looping Reforming for Tar Elimination in Biomass-Derived Gasification Gas. *Energy Fuels* **2014**, *28*, 3833–3840. [[CrossRef](#)]
48. Larsson, A.; Gunnarsson, I.; Tengberg, F. *The GoBiGas Project—Demonstration of the Production of Biomethane from Biomass via Gasification*; Göteborg Energi AB Project Report; Göteborg Energi AB: Gothenburg, Sweden, 2018. [[CrossRef](#)]
49. Schwebel, G.L.; Leion, H.; Krumm, W. Comparison of Natural Ilmenites as Oxygen Carriers in Chemical-Looping Combustion and Influence of Water Gas Shift Reaction on Gas Composition. *Chem. Eng. Res. Des.* **2012**, *90*, 1351–1360. [[CrossRef](#)]
50. Vigoureaux, M.; Knutsson, P.; Lind, F. Sulfur Uptake during Oxygen-Carrier-Aided Combustion with Ilmenite. *Energy Fuels* **2020**, *34*, 7735–7742. [[CrossRef](#)]
51. Tamhankar, S.S.; Tsuchiya, K.; Riggs, J.B. Catalytic Cracking of Benzene on Iron Oxide-Silica: Catalyst Activity and Reaction Mechanism. *Appl. Catal.* **1985**, *16*, 103–121. [[CrossRef](#)]
52. Shen, L.; Zheng, M.; Xiao, J.; Xiao, R. A Mechanistic Investigation of a Calcium-Based Oxygen Carrier for Chemical Looping Combustion. *Combust. Flame* **2008**, *154*, 489–506. [[CrossRef](#)]
53. Hüttinger, K.J.; Merdes, W.F. The Carbon-Steam Reaction at Elevated Pressure: Formations of Product Gases and Hydrogen Inhibitions. *Carbon* **1992**, *30*, 883–894. [[CrossRef](#)]
54. Keller, M.; Leion, H.; Mattisson, T.; Lyngfelt, A. Gasification Inhibition in Chemical-Looping Combustion with Solid Fuels. *Combust. Flame* **2011**, *158*, 393–400. [[CrossRef](#)]
55. Lussier, M.G.; Zhang, Z.; Miller, D.J. Characterizing Rate Inhibition in H₂O/H₂ Gasification via Measurement of Adsorbed Hydrogen Concentration. *ACS Div. Fuel Chem. Prepr.* **1996**, *41*, 206–208. [[CrossRef](#)]
56. Kiskinova, M.P. *Poisoning and Promotion in Catalysis Based on Surface Science Concepts and Experiments*; Elsevier: Amsterdam, The Netherlands, 1991; ISBN 0080887406.
57. Torres Galvis, H.M.; Koeken, A.C.J.; Bitter, J.H.; Davidian, T.; Ruitenbeek, M.; Dugulan, A.I.; De Jong, K.P. Effects of Sodium and Sulfur on Catalytic Performance of Supported Iron Catalysts for the Fischer-Tropsch Synthesis of Lower Olefins. *J. Catal.* **2013**, *303*, 22–30. [[CrossRef](#)]
58. Yamaguchi, T.; Jin, T.; Tanabe, K. Structure of Acid Sites on Sulfur-Promoted Iron Oxide. *J. Phys. Chem.* **1986**, *90*, 3148–3152. [[CrossRef](#)]
59. Luo, M.; Zhou, L.; Kuang, C.; Wang, C.; Zhang, H. Release and Fate of Pyritic Sulfur in Chemical Looping Combustion. *Fuel* **2021**, *285*, 119213. [[CrossRef](#)]

60. Berguerand, N.; Lyngfelt, A. The Use of Petroleum Coke as Fuel in a 10 KWth Chemical-Looping Combustor. *Int. J. Greenh. Gas Control* **2008**, *2*, 169–179. [[CrossRef](#)]
61. Siriwardane, R.V.; Ksepko, E.; Tian, H.; Poston, J.; Simonyi, T.; Sciazko, M. Interaction of Iron-Copper Mixed Metal Oxide Oxygen Carriers with Simulated Synthesis Gas Derived from Steam Gasification of Coal. *Appl. Energy* **2013**, *107*, 111–123. [[CrossRef](#)]
62. Riley, J.; Siriwardane, R.; Tian, H.; Benincosa, W.; Poston, J. Kinetic Analysis of the Interactions between Calcium Ferrite and Coal Char for Chemical Looping Gasification Applications: Identifying Reduction Routes and Modes of Oxygen Transfer. *Appl. Energy* **2017**, *201*, 94–110. [[CrossRef](#)]
63. Kun, Z.; He, D.; Guan, J.; Wang, Q.; Li, X.; Shang, J.; Zhang, Q. Interaction between Bimetallic Composite Oxygen Carriers and Coal and Its Contribution to Coal Direct Chemical Looping Gasification. *Int. J. Hydrogen Energy* **2020**, *45*, 19052–19066. [[CrossRef](#)]