




Epitaxial growth and characterization of (001) [NiFe/M]20 (M = Cu, CuPt and Pt) superlattices

Downloaded from: <https://research.chalmers.se>, 2025-12-05 04:40 UTC

Citation for the original published paper (version of record):

Kateb, M., Gudmundsson, J., Ingvarsson, S. (2023). Epitaxial growth and characterization of (001) [NiFe/M]20 (M = Cu, CuPt and Pt) superlattices. *Surfaces and Interfaces*, 38.
<http://dx.doi.org/10.1016/j.surfin.2023.102783>

N.B. When citing this work, cite the original published paper.



Epitaxial growth and characterization of (001) [NiFe/M]₂₀ (M = Cu, CuPt and Pt) superlattices

Movaffaq Kateb^{a,b,*}, Jon Tomas Gudmundsson^{a,c}, Snorri Ingvarsson^a

^a Science Institute, University of Iceland, Dunhaga 3, IS-107 Reykjavik, Iceland

^b Condensed Matter and Materials Theory Division, Department of Physics, Chalmers University of Technology, SE-412 96, Gothenburg, Sweden

^c Division of Space and Plasma Physics, School of Electrical Engineering and Computer Science, KTH Royal Institute of Technology, SE-100 44, Stockholm, Sweden

ARTICLE INFO

Keywords:

NiFe
Superlattice
Magnetic anisotropy
Microstructure
Substrate temperature

ABSTRACT

We present optimization of [(15 Å) Ni₈₀Fe₂₀/(5 Å) M]₂₀ single crystal multilayers on (001) MgO substrates, with M being Cu, Cu₅₀Pt₅₀ and Pt. These superlattices were characterized by high resolution X-ray reflectivity (XRR) and diffraction (XRD) as well as polar mapping of important crystal planes. It is shown that cube on cube epitaxial relationship can be obtained when depositing at substrate temperature of 100 °C regardless of the lattice mismatch (5% and 14% for Cu and Pt, respectively). At lower substrate temperatures poly-crystalline multilayers were obtained while at higher substrate temperatures {111} planes appear at ~10° off normal to the film plane. It is also shown that as the epitaxial strain increases, the easy magnetization axis rotates towards the direction that previously was assumed to be harder, i.e. from [110] to [100], and eventually further increase in the strain makes the magnetic hysteresis loops isotropic in the film plane. Higher epitaxial strain is also accompanied with increased coercivity values. Thus, the effect of epitaxial strain on the magnetocrystalline anisotropy is much larger than what was observed previously in similar, but polycrystalline samples with uniaxial anisotropy (Kateb et al. 2021).

1. Introduction

Since the discovery of the giant magneto-resistance (GMR) effect by Fert [1] and Grünberg [2] in the late 1980s, magnetic multilayers have been widely studied. In many cases they present unique features that cannot be achieved within the bulk state namely inter-layer exchange coupling [3], magnetic damping due to the interface [4,5] rather than alloying [6], and perpendicular magnetic anisotropy [7].

The GMR discovery, without a doubt, was an outcome of the advances in preparation methods such as molecular beam epitaxy (MBE), that enabled deposition of multilayer films with nanoscale thicknesses [8]. Thus, a great deal of effort has been devoted to enhancing the preparation methods over the years using both simulations [9–12] and experiments (cf. Ref. [13] and references therein). Permalloy (Ni₈₀Fe₂₀=Py) multilayers with non-magnetic (NM) Pt [13–15] or Cu [12,16–19] as spacers have been studied extensively in recent years. Various deposition methods have been utilized for preparing magnetic multilayers such as MBE [16], pulsed laser deposition (PLD) [20], ion beam deposition [12,21], dc magnetron sputtering (dcMS) [3,14,17,18], and more recently, high power impulse magnetron sputtering (HiPIMS) [13].

Py is a unique material with regards to studying magnetic anisotropy, which has been shown to depend strongly on the preparation method [22]. For instance, uniaxial anisotropy can be induced in polycrystalline Py by several means [23]. However, it has been thought that the cubic symmetry of single crystal Py encourages magneto-crystalline anisotropy, while uniaxial anisotropy cannot be achieved. We have recently shown, using HiPIMS deposition, that one can decrease the Ni₃Fe (L₁₂) order, but maintain the single crystal form, to achieve uniaxial anisotropy. We attributed this to the high instantaneous deposition rate during the HiPIMS pulse [24], which limits ordering, compared to dcMS that present cubic (biaxial) anisotropy. Regarding Py multilayers there has been a lot of focus on magneto-dynamic properties recently while the effects of interface strain on magnetic anisotropy has not received much attention. Rook et al. [16] prepared polycrystalline Py/Cu multilayers by MBE and reported a weak anisotropy, i.e. hysteresis loops along both the hard and easy axes with complete saturation at higher fields. They compared the coercivity values (H_c) and the saturation fields of their samples to the coercivity (H_c) and anisotropy field (H_k) of sputter deposited multilayers, showing uniaxial anisotropy, and concluded that the latter gives more than twice harder

* Corresponding author at: Condensed Matter and Materials Theory Division, Department of Physics, Chalmers University of Technology, SE-412 96, Gothenburg, Sweden.

E-mail address: movaffaq.kateb@chalmers.se (M. Kateb).

<https://doi.org/10.1016/j.surfin.2023.102783>

Received 22 November 2022; Received in revised form 9 February 2023; Accepted 27 February 2023

Available online 5 March 2023

2468-0230/© 2023 The Author(s). Published by Elsevier B.V. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

properties. They also reported an increase in H_c with increased Py thickness and attributed this to the interface strain that relaxes with increased thickness. Corrêa et al. [14] prepared nanocrystalline Py/Pt multilayers on rigid and flexible substrates and in both cases obtained weak anisotropy but two orders of magnitude larger H_c . Unfortunately, they did not mention any change in magnetic anisotropy upon straining the flexible substrate.

Recently we showed that utilizing increased power to the dcMS process, and in particular, by using HiPIMS deposition that the interface sharpness in polycrystalline [Py/Pt]₂₀ multilayers can be improved, due to increased ionization of the sputtered species [13]. Briefly, in dcMS deposition the film forming material is composed mostly of neutral atoms [25], while in HiPIMS deposition a significant fraction of the film forming material consists of ions [26,27]. In fact we have shown, using molecular dynamics simulations, that higher ionization of the film-forming material leads to smoother film surfaces and sharper interfaces [28,29]. We also showed that by changing the non-magnetic spacer material one can increase interface strain, that is accompanied with higher H_c and H_k , and limited deterioration of uniaxial anisotropy [13].

Another aspect of preparation is that deposition chambers for multilayers mostly benefit from oblique deposition geometry, which encourage uniaxial anisotropy in Py. The origin of uniaxial anisotropy induced by oblique deposition has been proposed to be self-shadowing, but this has not been systematically verified. We demonstrated uniaxial anisotropy, even in atomically smooth films with normal texture, which indicates absence of self-shadowing [30,31]. We also showed that oblique deposition is more decisive in the definition of the anisotropy direction than application of an *in-situ* magnetic field for inducing uniaxial magnetic anisotropy. Also for polycrystalline Py films oblique deposition by HiPIMS presents a lower coercivity and anisotropy field than when dcMS deposition is applied [32–34]. While none of the above mentioned results verify self-shadowing they are consistent with our interpretation of the order i.e. oblique deposition induces more disorder than *in-situ* magnetic field and HiPIMS produce more disorder than dcMS. Note that the level of order in polycrystals cannot be easily observed by X-ray diffraction. In this regard we proposed a method for mapping the resistivity tensor that is very sensitive to level of order in Py [23,35]. We reported much higher coercivity and deterioration of uniaxial anisotropy in (111)Py/Pt multilayers obtained by HiPIMS deposition of the Py layers [13]. We attributed the latter effect to the interface sharpness and higher epitaxial strain when HiPIMS is utilized for Py deposition.

Here, we study the properties of Py superlattices deposited by dcMS with Pt, Cu and CuPt as non-magnetic spacers. Pt and Cu were chosen as spacer because they have lattice parameters of 3.9 and 3.5 Å, respectively, and therefore provide varying strain to the Py film which has lattice constant of 3.54 Å. In this regard, calibration of the substrate temperature during deposition with respect to the desired thickness is of prime importance [36]. It is worth mentioning that dcMS deposition is expected to give more ordered single crystal (001) Py layers in which crystalline anisotropy is dominant [22]. This enables understanding to what extent interface strain will affect magnetocrystalline anisotropy of Py which we will show is much larger than the changes in uniaxial anisotropy in our latest study [13]. Section 2 discusses the deposition method and process parameters for the fabrication of the superlattices and the characterization methods applied. In Section 3 the effects of substrate temperature on the properties of the Py/Cu system are studied followed by exploring the influence of varying the lattice parameter of the non-magnetic layer on the structural and magnetic properties of the superlattice. The findings are summarized in Section 4.

2. Experimental apparatus and methods

The substrates were one side polished single crystal (001)MgO (Crystal GmbH) with surface roughness <5 Å and of dimensions

10 mm × 10 mm × 0.5 mm. The MgO substrates were used as received without any cleaning but were baked for an hour at 600 °C in vacuum for dehydration, cooled down for about an hour, and then maintained at the desired temperature ±0.4 °C during the deposition. The superlattices were deposited in a custom built UHV magnetron sputter chamber with a base pressure below 5×10^{-7} Pa. The chamber is designed to support 5 magnetron assemblies and targets, which are all located 22 cm away from substrate holder with a 35° angle with respect to substrate normal. The shutters were controlled by a LabVIEW program (National Instruments). The deposition was made with argon of 99.999% purity as the working gas using a Ni₈₀Fe₂₀ at.% and Cu targets both of 75 mm diameter and a Pt target of 50 mm in diameter.

The Py depositions were performed at 150 W dc power (MDX 500 power supply from Advanced Energy) at argon working gas pressure of 0.25 Pa which gives deposition rate of 1.5 Å/s. Both pure Cu and Pt buffer layers were deposited at dc power of 20 W. For the deposition of CuPt alloy we calibrated Cu₅₀Pt₅₀ at.% at dc power at 10 and 13 W for Cu and Pt, respectively. This selection of powers provide a similar deposition rate of 0.45 Å/s in all cases. In order to ensure that the film thickness is as uniform as possible, we rotate the sample at ~12.8 rpm. These deposition processes were repeated to fabricate superlattices consisting of 20 repetitions of 15 Å Py and 5 Å Pt, Cu or Cu₅₀Pt₅₀ at.% (CuPt).

X-ray diffraction measurements (XRD) were carried out using a X'pert PRO PANalytical diffractometer (Cu K_{α1} and K_{α2} lines, wavelength 0.15406 and 0.15444 nm, respectively) mounted with a hybrid monochromator/mirror on the incident side and a 0.27° collimator on the diffracted side. We would like to remark that, K_{α2} separation at $2\theta = 55^\circ$ is only 0.2° and much less at the smaller angles i.e. where our multilayer peaks are located. This is an order of magnitude smaller than the full width half maximum (FWHM) of our multilayer and satellite peaks. A line focus was used with a beam width of approximately 1 mm. The film thickness, mass density, and surface roughness, was determined by low-angle X-ray reflectivity (XRR) measurements with an angular resolution of 0.005°, obtained by fitting the XRR data using the commercial X'pert reflectivity program, that is based on the Parrat formalism [37] for reflectivity.

The magnetic hysteresis was recorded using a home-made high sensitivity magneto-optic Kerr effect (MOKE) loop. We use a linearly polarized He–Ne laser of wavelength 632.8 nm as a light source, with Glan-Thompson polarizers to further polarize and to analyze the light after Kerr rotation upon reflection off the sample surface. The Glan-Thompson polarizers linearly polarize the light with a high extinction ratio. They are cross polarized near extinction, i.e. their polarization states are near perpendicular and any change in polarization caused by the Kerr rotation at a sample's surface is detected as a change in power of light passing through the analyzer. The coercivity was read directly from the easy axis loops. The anisotropy field is obtained by extrapolating the linear low field trace along the hard axis direction to the saturation magnetization level, a method commonly used when dealing with effective easy axis anisotropy.

3. Results and discussion

3.1. Effect of substrate temperature on structural and magnetic properties

Fig. 1 shows the XRR results from Py/Cu superlattices deposited at different substrate temperatures. The Λ and δ indicated in the figure are inversely proportional to the superlattice period and the total thickness, respectively. It can be clearly seen that the fringes decay faster for a Py/Cu superlattice deposited at substrate temperature of 21 °C and 200 °C than when deposited at 100 °C. This indicates lower surface roughness obtained in the Py/Cu superlattice deposited at 100 °C. When deposited at room temperature, the large lattice mismatch between MgO and Py/Cu does not allow depositing a high quality superlattice. For substrate temperature of 200 °C, however, it is

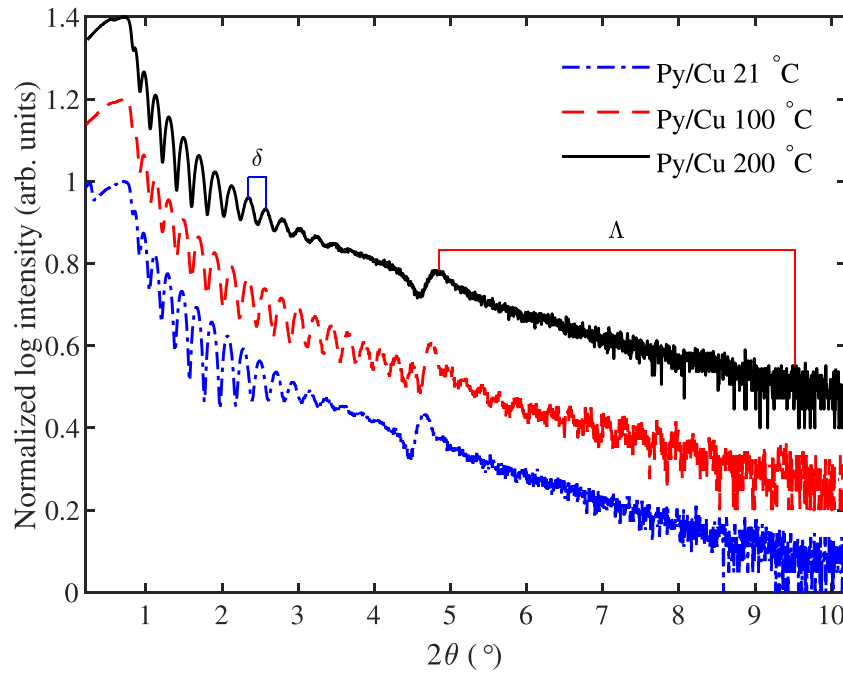


Fig. 1. Comparison of the XRR pattern from $[\text{Py}/\text{Cu}]_{20}$ superlattices deposited on (001)MgO at different substrate temperatures. The Λ and δ are inversely proportional to the Py/Cu period and total thickness, respectively.

difficult to grow a continuous Cu layer with such a low thickness (5 Å). This is due to the dewetting phenomenon which causes the minimum Cu thickness that is required to maintain its continuity to be 12 Å. Earlier, it has been shown that for substrate temperature up to 100 °C Py/(1 Å) Cu showed a limited intermixing upon annealing [17]. The optimum substrate temperature for deposition obtained here is very close to 156 °C which has earlier been reported for the deposition of (001) Fe/MgO [38] and (001) $\text{Fe}_{84}\text{Cu}_{16}$ /MgO [39] superlattices. We would like to remark that in our previous study we deposited 5 nm Ta underlayer to reduce the substrate surface roughness [13]. However, Ta on MgO is non-trivial due to the large lattice mismatch (22%). Besides, Ta underlayer encourages polycrystalline $\langle 111 \rangle$ texture normal to substrate surface that does not serve our purpose here.

Fig. 2 shows the result of symmetric ($\theta - 2\theta$) XRD scan normal to the film for Py/Cu superlattices deposited at different substrate temperatures. It can be seen that no Cu and Py peak were detected in the superlattice deposited at room temperature. Thus, epitaxial growth of Py and Cu were suppressed by the low substrate temperature. Furthermore, we studied room temperature deposited Py/Cu using grazing incidence XRD which indicated a polycrystalline structure (not shown here). For substrate temperature of 100 – 200 °C there are clear (002) Py/Cu peaks indicating an epitaxial relationship in the (001)Py \parallel (001)Cu \parallel (001)MgO stack. However, there is no sign of satellite peaks due to the Λ (Py/Cu) period. We explain this further when comparing the Py/Cu, Py/Pt, and Py/CuPt superlattices in Section 3.2.

Fig. 3 shows the pole figures from the {200} and {111} planes for Py/Cu superlattices deposited at different substrate temperatures. For the Py/Cu superlattice deposited at 21 °C, there is only a peak in the middle of the {111} pole figure that indicates a weak $\langle 111 \rangle$ contribution normal to the film plane. For a superlattice deposited with substrate temperature of 100 °C the {200} pole figure indicates an intense spot at $\psi = 0$ that is corresponding to (002)Py/Cu planes parallel to the substrate. There is also a weaker four-fold spot at $\psi = 90^\circ$ and $\phi = 0, 90, 180$ and 270° from the {200} planes parallel to the substrate edges. In the {111} pole figure only four-fold points appear at $\psi = 54.7^\circ$ and with 45° shifts in ϕ with respect to substrate edges. These are the characteristics of the so-called cube on cube epitaxy achieved at 100 °C.

For deposition with substrate temperature of 200 °C, however, there is a weak {111} ring at $\psi = 7.5^\circ$. Note that these {111} planes were not detected by normal XRD because the (111)Py/Cu peak appears at $2\theta \approx 42^\circ$ which is masked by the strong (002)MgO peak normal to the film plane.

Fig. 4 compares the MOKE response of Py/Cu superlattices deposited at different substrate temperatures. For a superlattice deposited at room temperature, uniaxial anisotropy along the [100] direction is evident. This is expected since the oblique deposition in a co-deposition chamber tends to induce uniaxial anisotropy in Py films [22,30–32]. However, the oblique deposition cannot overcome magnetocrystalline anisotropy due to symmetry in an ordered single crystal Py [22]. Thus, the low substrate temperature must be accounted for the limiting order in the Py layer and presence of uniaxial anisotropy.

For deposition at higher substrate temperatures, however, biaxial anisotropy was obtained with the easy axes along the [110] directions in plane. It is worth mentioning that the bulk crystal symmetry gives the easy axis along the [111] direction which is forced into the film plane along the [110] direction due to shape anisotropy [22]. In the Py/Cu superlattice grown at 100 °C (Fig. 4(b)), $\langle 1\bar{1}0 \rangle$ is clearly an easy direction, with a very low H_c of 0.7 Oe and double-hysteresis loops along the $\langle 110 \rangle$ direction that saturates at 1.2 Oe. For the Py/Cu superlattice deposited at 200 °C (Fig. 4(c)), it seems the double-hysteresis loops overlap and the other easy axis gives a step that in total present increased coercivity. With increasing substrate temperature not only do the coercivities vary but also the shapes of the hysteresis curves are different. When the substrate temperature during deposition is 21 °C the magnetization, shown in Fig. 4(a), is much like we obtain for polycrystalline single layer films. When the substrate temperature is higher, as shown in Figs. 4 (b) and (c), however, the anisotropy has rotated by 45 degrees and the hysteresis loops have changed. The intermediate steps in the hysteresis curves are caused by antiferromagnetic alignment of the magnetic layers, that minimizes the exchange and dipolar magnetic interactions. In some cases this results in perfectly zero magnetic remanence, while in other cases the cancellation is not perfect. The non-magnetic Cu spacer layer is only 5 Å thick in our case, just at the onset of the first antiferromagnetic exchange coupling peak observed by Parkin [40]. Double hysteresis curves have been observed

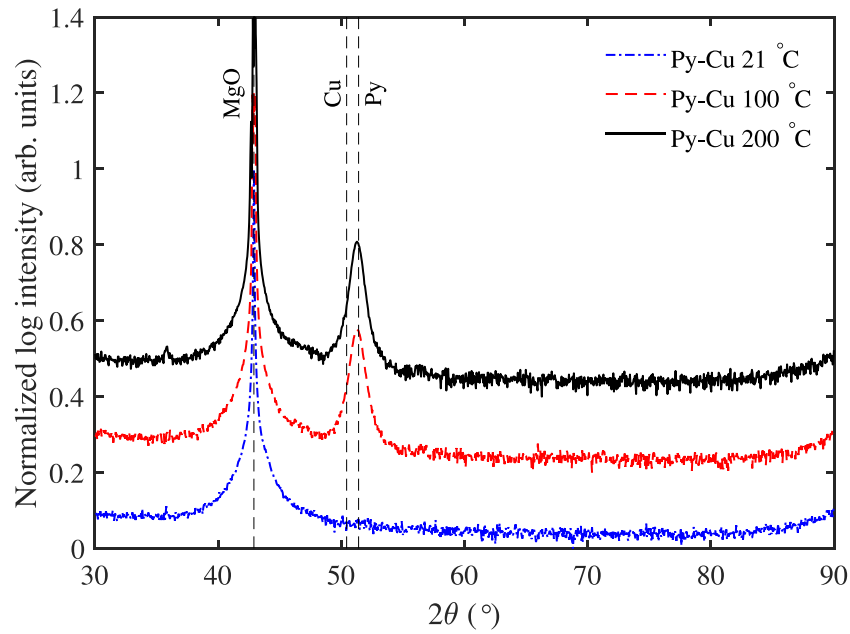


Fig. 2. Comparison of the XRD pattern from [Py/Cu]₂₀ superlattices deposited on (001)MgO at different substrate temperatures. The intense peak belongs to (002) planes of MgO and the other peak is due to (002) planes of Py/Cu multilayer.

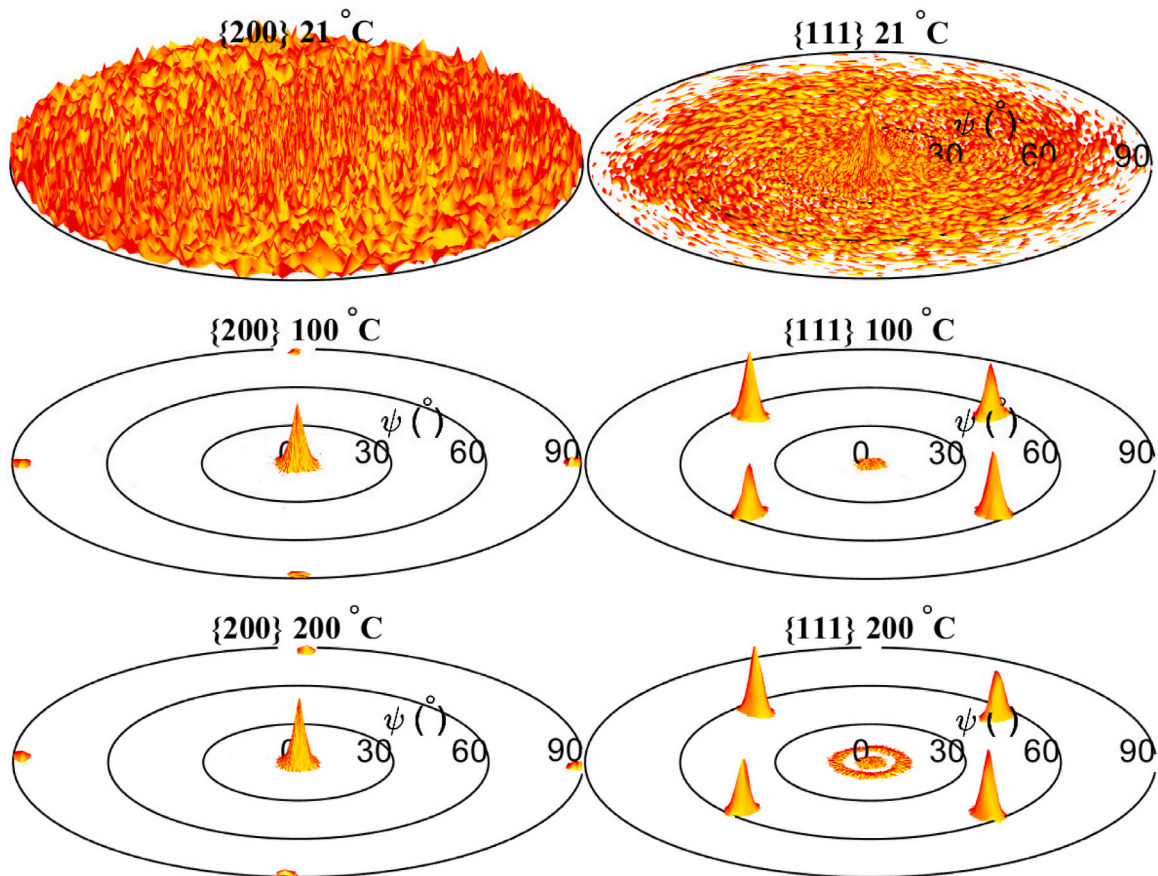


Fig. 3. Comparison of the {200} and {111} pole figures from [Py/Cu]₂₀ superlattices deposited on (001)MgO at substrate temperatures of 21, 100, and 200 °C. The background is removed for better illustration.

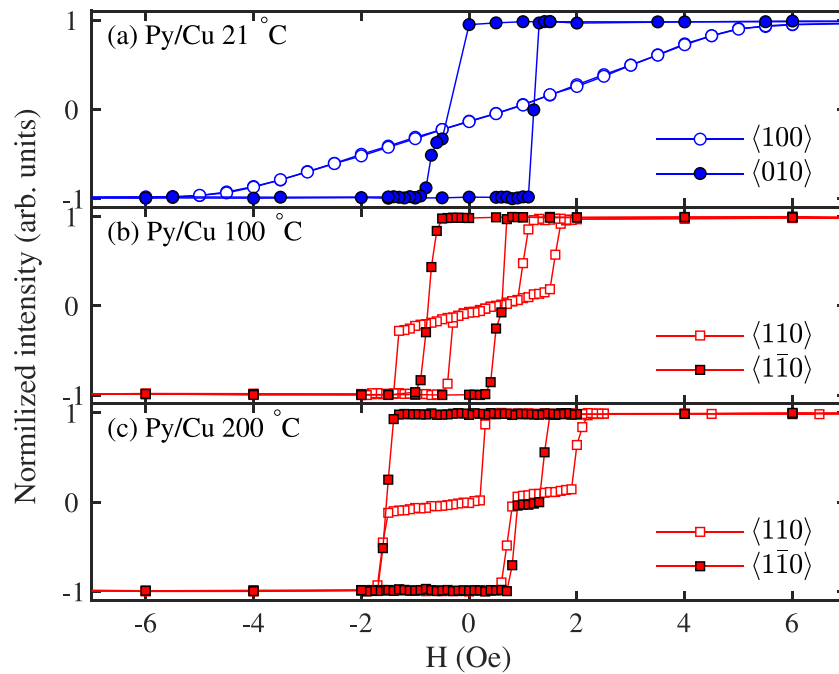


Fig. 4. MOKE response of different $[\text{Py/Cu}]_{20}$ superlattices deposited on (001)MgO at substrate temperatures (a) 21, (b) 100 and (c) 200 °C. Each legend indicates probing orientation in the substrate plane.

Table 1

The Py and NM layer thicknesses (t), roughness (R_a) and density (ρ) extracted by fitting the XRR results of different superlattices deposited on (001)MgO at 100 °C substrate temperature.

Sample	t (Å)			R_a (Å)		ρ (g/cm ³)	
	Py	NM	Λ	Py	NM	Py	NM
Py/Cu	15.8	3.46	19.3	7.62	6.25	8.74	9.8
Py/Pt	15.9	2.97	18.9	5.92	3.24	8.55	27.2
Py/CuPt	15.9	3.43	19.3	2.25	4.94	7.45	26.8

in the Py/Cu system [18]. Note that Ni is miscible in Cu and during annealing a mixing of Ni and Cu is possible. Such intermixing causes a decrease of magnetic homogeneity and a reduction in the GMR [17,18].

3.2. Effect of strain on structural and magnetic properties

In order to explore the influence of strain on the magnetic properties we deposited NM layers of Pt and $\text{Cu}_{50}\text{Pt}_{50}$ at % alloy in addition to Cu discussed in Section 3.1. Pt has lattice constant of 3.9 Å which is larger than of Py, which has lattice constant of 3.54 Å. Therefore, by going from Cu to $\text{Cu}_{50}\text{Pt}_{50}$ and then to Pt the strain is gradually increased. Fig. 5 shows XRR results from different superlattices deposited on (001)MgO at 100 °C. Note that the Λ peak is suppressed in the Py/Cu superlattice. One may think this arises from a diffused Py/Cu interface that leads to smooth density variation at the interface. This is not the case here and the Λ peaks intensity decreases due the similar density of Py and Cu. The latter has been shown to reduce the resolution of the XRR measurement in Si/SiO₂ by a few orders of magnitude [41].

The layers thickness and their mass density as well as surface and interface roughness obtained by fitting XRR results for deposition at substrate temperature of 100 °C are summarized in Table 1. The period Λ is in all cases about 19 Å with $t_{\text{Py}} \sim 16$ Å and $t_{\text{NM}} \sim 3$ Å. The film mass density of the Py layers is the highest (8.74 g/cm³) in the Py/Cu stack but is lowest (7.45 g/cm³) in the Py/CuPt stack.

Fig. 6 shows the XRD results from Py/NM superlattices deposited on (001)MgO at substrate temperature of 100 °C. The most intense peak, indicated by the vertical dashed line, belongs to the (002) planes of the

MgO substrate. Rather than exhibiting separate peaks for Py and NM, a single main (002) Py/NM peak is evident from all the superlattices and indicated by 0 in the figure. This peak is closer to the Py side due to the higher thickness of Py layers compared to the NM layers. The other peaks, indicated by \pm are satellite peaks. The asymmetric intensity of the satellite peaks is associated with the strain in direction normal to the substrate. It is also clear that the main (002) Py/CuPt peak is located between the Py/Cu and Py/Pt peaks. Due to the lack of any other peaks, we conclude that these superlattices are single crystalline with their (001) orientation normal to the substrate surface. The satellite peaks suggest the period Λ to be of 18.8 and 19.2 Å for Py/Pt and Py/CuPt, respectively, which is slightly off compared to the values given in Table 1.

Fig. 7 shows the {002} and {111} pole figures from different superlattices deposited on (001) MgO at substrate temperature of 100 °C. Since the Py/Pt and Py/CuPt superlattices exhibit multiple (002) peaks the pole figure were obtained for the main peak (indicated by 0 in Fig. 6). It can be seen that all the pole figures are very similar. All these pole figures indicate a cube on cube epitaxial relationship.

Fig. 8 depicts the MOKE response from Py/Pt and Py/CuPt superlattices prepared at 100 °C. For the Py/Pt superlattice we did not detect any clear easy direction in the film plane, the film appeared almost isotropic in the film plane with H_c in the range 60 – 75 Oe. The hysteresis in the [100] and [110] directions are displayed in Fig. 8(a). Aside from H_c of 3 Oe, the Py/CuPt superlattice presents biaxial anisotropy similar to Py/Cu, cf. Fig. 4(b) and (c). However, a Py/Cu superlattice exhibits an easy axis along the [110] directions, while an easy axis appears along the [100] orientations for a Py/CuPt superlattice. Note that the [100] directions are harder than both the [110] and [111] directions. However, forcing easy axes along the [100] direction in the single crystal Py on (001)MgO has been reported previously [42].

For the polycrystalline, but highly (111) textured Py/M multilayers, we observed limited change in coercivity and opening in hard axis with interface strain due to the choice of M [13]. Here, for Py/Pt the coercivity increases by an order of magnitude and the cubic anisotropy is almost destroyed.

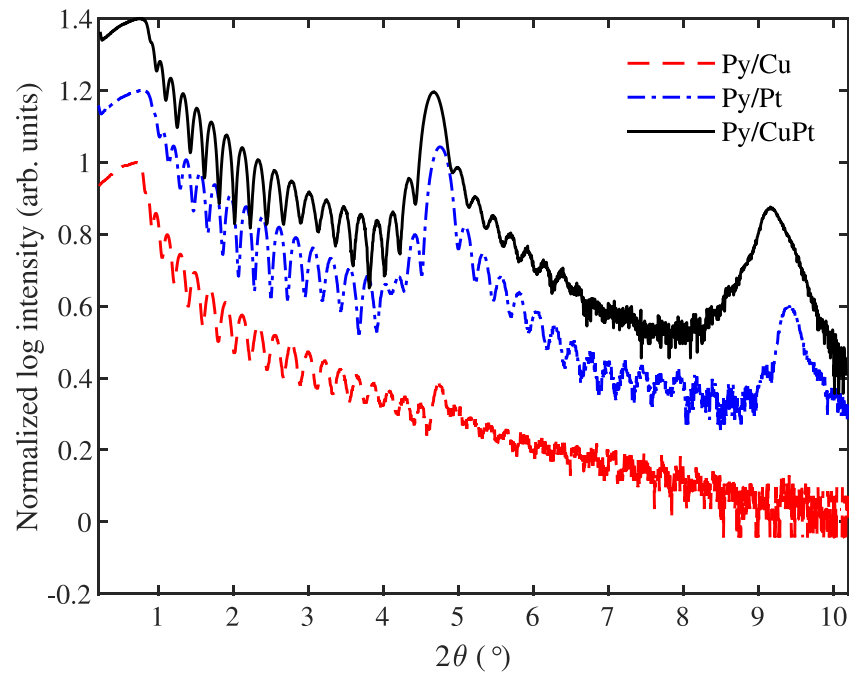


Fig. 5. XRR measurements from the various superlattices, $[\text{Py}/\text{Cu}]_{20}$, $[\text{Py}/\text{Pt}]_{20}$, and $[\text{Py}/\text{CuPt}]_{20}$, deposited on (001)MgO at substrate temperature of 100 °C.

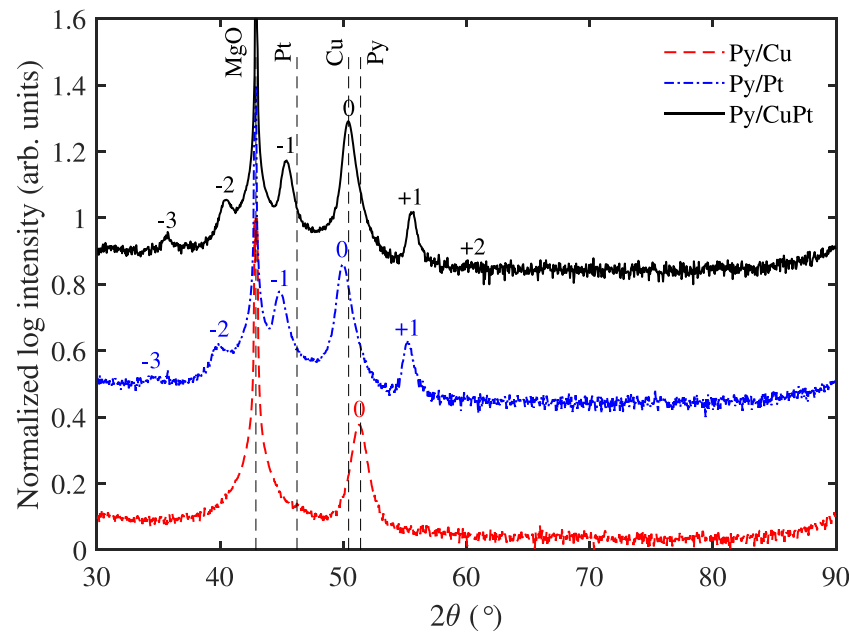


Fig. 6. Comparison of the XRD results from the various superlattices, $[\text{Py}/\text{Cu}]_{20}$, $[\text{Py}/\text{Pt}]_{20}$ and $[\text{Py}/\text{CuPt}]_{20}$, deposited at substrate temperature of 100 °C. All the peaks are due to the (002) plane and the vertical dashed line indicate the (002) peak position for the bulk state.

4. Summary

In summary, it is shown that Py superlattices can be successfully deposited on (001)MgO within a narrow substrate temperature window around 100 °C. For a small lattice mismatch of 5% in the superlattice the easy axes are detected along the $[110]$ directions, similar to the single crystal Py. It is also shown that for a moderate lattice mismatch

(7%) the easy axes rotates towards the $[100]$ orientation and the coercivity increases. The higher lattice mismatch of 14% presents nearly isotropic behavior and a very high coercivity, simultaneously. Thus, the results indicate that the changes in magnetocrystalline anisotropy due to epitaxial strain are much larger than the changes we observed earlier in the case of uniaxial anisotropy.

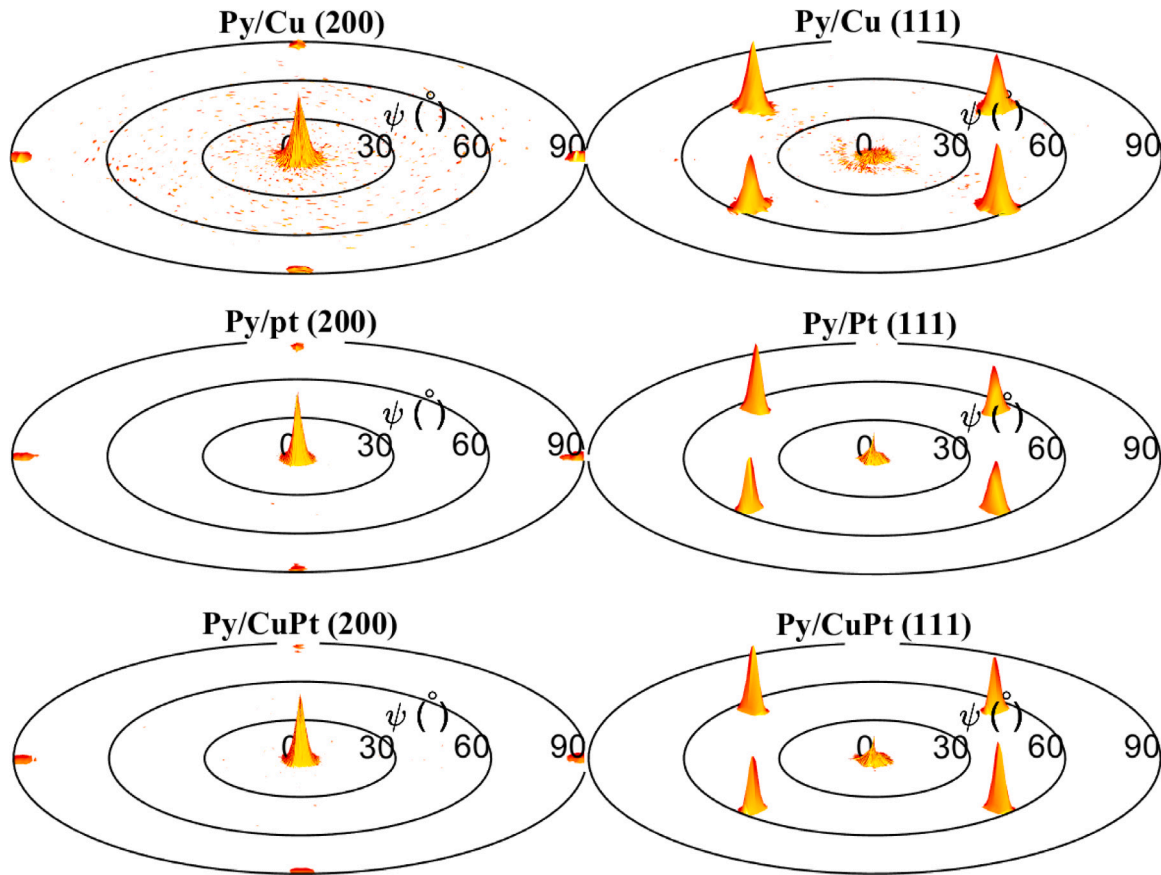


Fig. 7. Comparison of the {002} and {111} pole figures from the various superlattices, $[\text{Py/Cu}]_{20}$, $[\text{Py/Pt}]_{20}$ and $[\text{Py/CuPt}]_{20}$, deposited on (001) MgO at substrate temperature of 100 °C. The background is removed for better illustration.

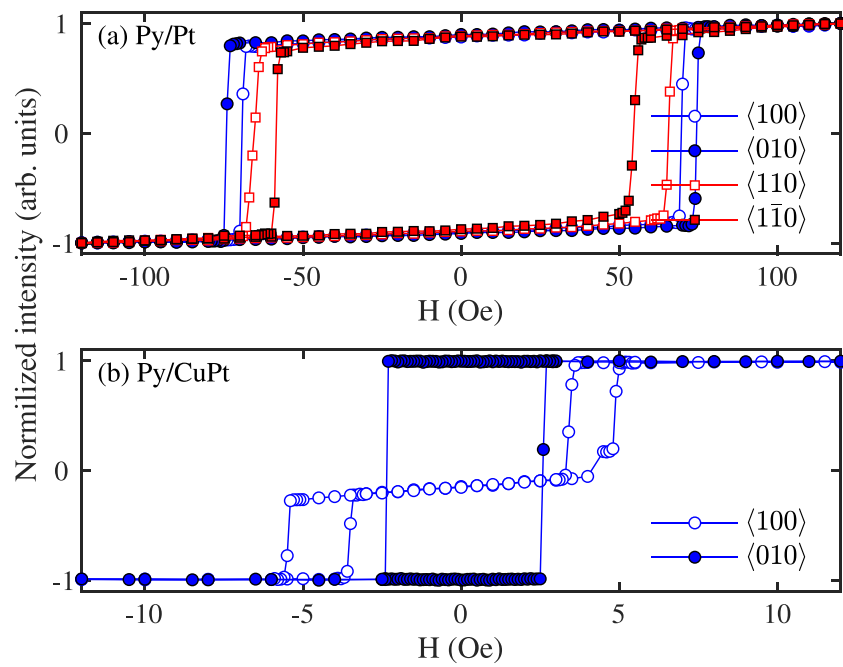


Fig. 8. MOKE response from (a) $[\text{Py/Pt}]_{20}$ and (b) $[\text{Py/CuPt}]_{20}$ superlattices. The legend indicate probing direction in the substrate plane.

CRediT authorship contribution statement

Movaffaq Kateb: Methodology, Investigation, Data curation, Writing, Visualization. **Jon Tomas Gudmundsson:** Conceptualization, Validation, Resources, Writing – review & editing. **Snorri Ingvarsson:** Supervision, Resources, Writing – review & editing, Funding acquisition.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Data availability

Data will be made available on request.

Acknowledgments

The authors would like to acknowledge helpful comments and experimental help from Dr. Fridrik Magnus and Einar B. Thorsteinnsson. This work was partially supported by the Icelandic Research Fund Grant Nos. 228951, 196141, 130029 and 120002023.

References

- [1] M.N. Baibich, J.M. Broto, A. Fert, F.N. Van Dau, F. Petroff, P. Etienne, G. Creuzet, A. Friederich, J. Chazelas, Giant magnetoresistance of (001) Fe/(001) Cr magnetic superlattices, *Phys. Rev. Lett.* 61 (21) (1988) 2472.
- [2] G. Binasch, P. Grünberg, F. Saurenbach, W. Zinn, Enhanced magnetoresistance in layered magnetic structures with antiferromagnetic interlayer exchange, *Phys. Rev. B* 39 (7) (1989) 4828.
- [3] S.S.P. Parkin, N. More, K.P. Roche, Exchange coupling and magnetoresistance in metallic superlattice structures: Co/Ru, Co/Cr and Fe/Cr, *Phys. Rev. Lett.* 64 (19) (1990) 2304–2308.
- [4] S. Mizukami, Y. Ando, T. Miyazaki, The study on ferromagnetic resonance linewidth for NM/80NiFe/NM (NM = Cu, Ta, Pd and Pt) films, *Japan. J. Appl. Phys.* 40 (2R) (2001) 580.
- [5] S. Ingvarsson, L. Ritchie, X. Liu, G. Xiao, J. Slonczewski, P. Trouilloud, R. Koch, Role of electron scattering in the magnetization relaxation of thin $\text{Ni}_{81}\text{Fe}_{19}$ films, *Phys. Rev. B* 66 (21) (2002) 214416.
- [6] S. Ingvarsson, G. Xiao, S.S.P. Parkin, R.H. Koch, Tunable magnetization damping in transition metal ternary alloys, *Appl. Phys. Lett.* 85 (21) (2004) 4995–4997.
- [7] M.T. Johnson, P.J.H. Bloemen, F.J.A. Den Broeder, J.J. de Vries, Magnetic anisotropy in metallic multilayers, *Rep. Progr. Phys.* 59 (11) (1996) 1409.
- [8] A. Fert, Nobel lecture: Origin, development, and future of spintronics, *Rev. Modern Phys.* 80 (2008) 1517–1530.
- [9] X. Zhou, H. Wadley, Atomistic simulations of the vapor deposition of Ni/Cu/Ni multilayers: the effects of adatom incident energy, *J. Appl. Phys.* 84 (4) (1998) 2301–2315.
- [10] X. Zhou, H. Wadley, Misfit dislocations in gold/permalloy multilayers, *Phil. Mag.* 84 (2) (2004) 193–212.
- [11] X. Zhou, R. Johnson, H. Wadley, Misfit-energy-increasing dislocations in vapor-deposited CoFe/NiFe multilayers, *Phys. Rev. B* 69 (14) (2004) 144113.
- [12] C.B. Ene, G. Schmitz, R. Kirchheim, A. Hütten, Stability and thermal reaction of GMR NiFe/Cu thin films, *Acta Mater.* 53 (12) (2005) 3383–3393.
- [13] M. Kateb, J.T. Gudmundsson, S. Ingvarsson, Tailoring interface mixing and magnetic properties in (111) Permalloy/Pt multilayers, *J. Magn. Magn. Mater.* 538 (2021) 168288.
- [14] M.A. Corrêa, R. Dutra, T.L. Marcondes, T.J.A. Moric, F. Bohn, R.L. Sommer, Exploring the magnetization dynamics of NiFe/Pt multilayers in flexible substrates, *Mater. Sci. Eng. B* 211 (2016) 115–120.
- [15] D. Ley Domínguez, R.J. Sáenz-Hernández, A.F. Arzate, A.I. Arteaga Duran, C.E. Ornelas Gutiérrez, O. Solís Canto, M.E. Botello-Zubiate, F.J. Rivera-Gómez, A. Azevedo, G.L. da Silva, S.M. Rezende, J.A. Matutes-Aquino, High-resolution electron microscopy in spin pumping NiFe/Pt interfaces, *J. Appl. Phys.*, 17, 17D910 117.
- [16] K. Rook, A.M. Zeltser, J.O. Artman, D.E. Laughlin, M.H. Kryder, R.M. Chrenko, Multilayer permalloy films grown by molecular-beam epitaxy, *J. Appl. Phys.* 69 (8) (1991) 5670–5672.
- [17] L. van Loyen, D. Elefant, D. Tietjen, C.M. Schneider, M. Hecker, J. Thomas, Annealing of $\text{Ni}_{80}\text{Fe}_{20}/\text{Cu}$, *J. Appl. Phys.* 87 (9) (2000) 4852–4854.
- [18] M. Hecker, D. Tietjen, H. Wendrock, C. M. Schneider, N. Cramer, L. Malkinski, R.E. Camley, Z. Celinski, Annealing effects and degradation mechanism of NiFe/Cu GMR multilayers, *J. Magn. Magn. Mater.* 247 (1) (2002) 62–69.
- [19] S. Heitmann, A. Hütten, T. Hempel, W. Schepper, G. Reiss, C. Aloff, Interplay of antiferromagnetic coupling in copper/permalloy combination multilayers, *J. Appl. Phys.* 87 (9) (2000) 4849–4851.
- [20] J. Shen, Z. Gai, J. Kirschner, Growth and magnetism of metallic thin films and multilayers by pulsed-laser deposition, *Surf. Sci. Rep.* 52 (5–6) (2004) 163–218.
- [21] M. Ueno, S. Tanoue, Magnetic properties of ion-beam sputter deposited NiFe ultrathin films, *J. Vac. Sci. Technol. A* 13 (4) (1995) 2194–2198.
- [22] M. Kateb, J.T. Gudmundsson, S. Ingvarsson, Effect of atomic ordering on the magnetic anisotropy of single crystal $\text{Ni}_{80}\text{Fe}_{20}$, *AIP Adv.* 9 (3) (2019) 035308.
- [23] M. Kateb, S. Ingvarsson, Correlation of uniaxial magnetic anisotropy axes and principal resistivities in polycrystalline ferromagnetic films, *J. Magn. Magn. Mater.* 532 (2021) 167982.
- [24] M. Kateb, J.T. Gudmundsson, P. Brault, A. Manolescu, S. Ingvarsson, On the role of ion potential energy in low energy HiPIMS deposition: An atomistic simulation, *Surf. Coat. Technol.* 426 (2021) 127726.
- [25] J.T. Gudmundsson, Physics and technology of magnetron sputtering discharges, *Plasma Sources. Sci. Technol.* 29 (11) (2020) 113001.
- [26] J.T. Gudmundsson, N. Brenning, D. Lundin, U. Helmersson, The high power impulse magnetron sputtering discharge, *J. Vac. Sci. Technol. A* 30 (3) (2012) 030801.
- [27] D. Lundin, T. Minea, J.T. Gudmundsson (Eds.), High power impulse magnetron sputtering: fundamentals, technologies, challenges and applications, Elsevier, Amsterdam, The Netherlands, 2020.
- [28] M. Kateb, H. Hajihoseini, J.T. Gudmundsson, S. Ingvarsson, Role of ionization fraction on the surface roughness, density, and interface mixing of the films deposited by thermal evaporation, dc magnetron sputtering, and HiPIMS: an atomistic simulation, *J. Vac. Sci. Technol. A* 37 (3) (2019) 031306.
- [29] M. Kateb, J.T. Gudmundsson, S. Ingvarsson, Effect of substrate bias on microstructure of epitaxial film grown by HiPIMS: an atomistic simulation, *J. Vac. Sci. Technol. A* 38 (4) (2020) 043006.
- [30] M. Kateb, S. Ingvarsson, Thickness-dependent magnetic and magnetoresistance properties of permalloy prepared by field assisted tilt sputtering, in: 2017 IEEE Sensors Applications Symposium (SAS), IEEE, Glassboro, New Jersey, 2017, pp. 1–5.
- [31] M. Kateb, E. Jacobsen, S. Ingvarsson, Application of an extended van der Pauw method to anisotropic magnetoresistance measurements of ferromagnetic films, *J. Phys. D: Appl. Phys.* 52 (7) (2018) 075002.
- [32] M. Kateb, H. Hajihoseini, J.T. Gudmundsson, S. Ingvarsson, Comparison of magnetic and structural properties of permalloy grown by dc and high power impulse magnetron sputtering, *J. Phys. D: Appl. Phys.* 51 (28) (2018) 285005.
- [33] H. Hajihoseini, M. Kateb, S. Ingvarsson, J.T. Gudmundsson, Oblique angle deposition of nickel thin films by high-power impulse magnetron sputtering, *Beilstein J. Nanotechnol.* 10 (1) (2019) 1914–1921.
- [34] M. Kateb, Induced uniaxial magnetic anisotropy in polycrystalline, single crystal and superlattices of permalloy (Ph.D. thesis), University of Iceland, School of Engineering and Natural Sciences, Faculty of Physical Sciences, 2019.
- [35] S. Ingvarsson, M. Kateb, C. Scheuner, Resistivity tensor in Permalloy films by modified van der Pauw method, in: Bulletin of the American Physical Society, 62, (4) APS, 2017, APS March Meeting 2017, abstract E47.012.
- [36] R. Loloe, M.A. Crimp, Effect of growth temperature on the structure and magnetic properties of sputtered biepitaxial (111) permalloy films, *J. Appl. Phys.* 92 (8) (2002) 4541–4544.
- [37] L.G. Parratt, Surface studies of solids by total reflection of x-rays, *Phys. Rev.* 95 (2) (1954) 359–369.
- [38] R. Moubah, F. Magnus, T. Warnatz, G.K. Pálsson, V. Kapaklis, V. Ukleev, A. Devishvili, J. Palisaitis, P. Persson, B. Hjörvarsson, Discrete layer-by-layer magnetic switching in Fe/MgO (001) superlattices, *Phys. Rev. Appl.* 5 (4) (2016) 044011.
- [39] T. Warnatz, B.E. Skovdal, F. Magnus, H. Stopfel, D. Primetzhofer, A. Stein, R. Brucas, B. Hjörvarsson, The influence of diameter on the magnetic saturation in $\text{Fe}_{84}\text{Cu}_{16}/\text{MgO}$ (001) multilayered islands, *J. Magn. Magn. Mater.* 496 (2020) 165864.
- [40] S.S.P. Parkin, Oscillations in giant magnetoresistance and antiferromagnetic coupling in $[\text{Ni}_{81}\text{Fe}_{19}/\text{Cu}]_N$ multilayers, *Appl. Phys. Lett.* 60 (4) (1992) 512–514.
- [41] J. Tiilikainen, J.-M. Tilli, V. Bosund, M. Mattila, T. Hakkarainen, J. Sormunen, H. Lipsanen, Accuracy in x-ray reflectivity analysis, *J. Phys. D: Appl. Phys.* 40 (23) (2007) 7497–7501.
- [42] F. Michelini, L. Ressler, J. Degauque, P. Baulés, A.R. Fert, J.P. Peyrade, J.F. Bobo, Permalloy thin films on MgO(001): Epitaxial growth and physical properties, *J. Appl. Phys.* 92 (12) (2002) 7337–7340.